

ACCELERATED PUBLICATION

Solar cell efficiency tables (version 41)

Martin A. Green^{1*}, Keith Emery², Yoshihiro Hishikawa³, Wilhelm Warta⁴ and Ewan D. Dunlop⁵¹ Australian Centre for Advanced Photovoltaics, University of New South Wales, Sydney, 2052, Australia² National Renewable Energy Laboratory, 15013 Denver West Parkway, Golden, CO, 80401, USA³ National Institute of Advanced Industrial Science and Technology (AIST), Research Center for Photovoltaics (RCPV), Central 2, Umezono 1-1-1, Tsukuba, Ibaraki, 305-8568, Japan⁴ Fraunhofer-Institute for Solar Energy Systems, Department: Solar Cells - Materials and Technology, Heidenhofstr. 2, D-79110 Freiburg, Germany⁵ European Commission – Joint Research Centre, Renewable Energy Unit, Institute for Energy, Via E. Fermi 2749, IT-21027 Ispra (VA), Italy

ABSTRACT

Consolidated tables showing an extensive listing of the highest independently confirmed efficiencies for solar cells and modules are presented. Guidelines for inclusion of results into these tables are outlined, and new entries since June 2012 are reviewed. Copyright © 2012 John Wiley & Sons, Ltd.

KEYWORDS

solar cell efficiency; photovoltaic efficiency; energy conversion efficiency

*Correspondence

Martin A. Green, ARC Photovoltaics Centre of Excellence, University of New South Wales, Sydney, 2052, Australia.

E-mail: m.green@unsw.edu.au

Received 14 November 2012; Accepted 26 November 2012

1. INTRODUCTION

Since January 1993, *Progress in Photovoltaics* has published six monthly listings of the highest confirmed efficiencies for a range of photovoltaic cell and module technologies [1–3]. By providing guidelines for the inclusion of results into these tables, this not only provides an authoritative summary of the current state-of-the-art but also encourages researchers to seek independent confirmation of results and to report results on a standardised basis. In Version 33 of these Tables [2], results were updated to the new internationally accepted reference spectrum (IEC 60904–3, Ed. 2, 2008), where this was possible.

The most important criterion for inclusion of results into the Tables is that they must have been independently measured by a recognised test centre listed elsewhere [1]. A distinction is made between three different eligible areas: total area, aperture area and designated illumination area, as also defined elsewhere [1]. ‘Active area’ efficiencies are not included. There are also certain minimum values of the area sought for the different device types (above 0.05 cm² for a concentrator cell, 1 cm² for a one-sun cell and 800 cm² for a module).

Results are reported for cells and modules made from different semiconductors and for sub-categories within each semiconductor grouping (e.g. crystalline, polycrystalline and thin film). From Version 36 onwards, spectral

response information is included when available in the form of a plot of the external quantum efficiency (EQE) versus wavelength, either as absolute values or normalised to the peak measured value. Current–voltage (*I*–*V*) curves have also been included where possible from Version 38 onwards.

2. NEW RESULTS

Highest confirmed ‘one sun’ cell and module results are reported in Tables I and II. Any changes in the tables from those previously published [3] are set in bold type. In most cases, a literature reference is provided that describes either the result reported, or a similar result. Table I summarises the best measurements for cells and submodules whereas Table II shows the best results for modules. Table III contains what might be described as ‘notable exceptions’. Although not conforming to the requirements to be recognised as a class record, the cells and modules in this Table have notable characteristics that will be of interest to sections of the photovoltaic community, with entries based on their significance and timeliness.

To encourage discrimination, Table III is limited to nominally 10 entries with the present authors having voted for their preferences for inclusion. Readers who have suggestions of results for inclusion into this Table are

Table I. Confirmed terrestrial cell and submodule efficiencies measured under the global AM1.5 spectrum (1000 W/m²) at 25 °C (IEC 60904-3: 2008, ASTM G-173-03 global).

| Classification ^a | Effic. ^b (%) | Area ^c (cm ²) | V _{oc} (V) | J _{sc} (mA/cm ²) | FF ^d (%) | Test centre ^e (and date) | Description |
|----------------------------------|------------------------------|---|--------------------------|--|------------------------|--|---|
| Silicon | | | | | | | |
| Si (crystalline) | 25.0 ± 0.5 | 4.00 (da) | 0.706 | 42.7 ^f | 82.8 | Sandia (3/99) ^g | UNSW PERL [18] |
| Si (multicrystalline) | 20.4 ± 0.5 | 1.002 (ap) | 0.664 | 38.0 | 80.9 | NREL (5/04) ^g | FhG-ISE [19] |
| Si (thin film transfer) | 20.1 ± 0.4 | 242.6 (ap) | 0.682 | 38.14^h | 77.4 | NREL (10/12) | Solexel (43 µm thick) [4] |
| Si (thin film submodule) | 10.5 ± 0.3 | 94.0 (ap) | 0.492 ⁱ | 29.7 ⁱ | 72.1 | FhG-ISE (8/07) ^g | CSG Solar (1–2 µm on glass; 20 cells) [20] |
| III–V Cells | | | | | | | |
| GaAs (thin film) | 28.8 ± 0.9 | 0.9927 (ap) | 1.122 | 29.68 ^j | 86.5 | NREL (5/12) | Alta Devices [21] |
| GaAs (multicrystalline) | 18.4 ± 0.5 | 4.011 (t) | 0.994 | 23.2 | 79.7 | NREL (11/95) ^g | RTI, Ge substrate [22] |
| InP (crystalline) | 22.1 ± 0.7 | 4.02 (t) | 0.878 | 29.5 | 85.4 | NREL (4/90) ^g | Spire, epitaxial [23] |
| Thin Film Chalcogenide | | | | | | | |
| CIGS (cell) | 19.6 ± 0.6 ^k | 0.996 (ap) | 0.713 | 34.8 ^l | 79.2 | NREL (4/09) | NREL, on glass [24] |
| CIGS (submodule) | 17.4 ± 0.5 | 15.993 (da) | 0.6815 ⁱ | 33.84 ⁱ | 75.5 | FhG-ISE (10/11) | Solibro, 4 serial cells [25] |
| CdTe (cell) | 18.3 ± 0.5 | 1.005 (ap) | 0.857 | 26.95^h | 77.0 | NREL (10/12) | GE Global Research [5] |
| Amorphous/ | | | | | | | |
| Nanocrystalline Si | | | | | | | |
| Si (amorphous) | 10.1 ± 0.3 ^m | 1.036 (ap) | 0.886 | 16.75 ^f | 67.8 | NREL (7/09) | Oerlikon Solar Lab, Neuchatel [26] |
| Si (nanocrystalline) | 10.1 ± 0.2 ⁿ | 1.199 (ap) | 0.539 | 24.4 | 76.6 | JQA (12/97) | Kaneka (2 µm on glass) [27] |
| Photochemical | | | | | | | |
| Dye sensitised | 11.9 ± 0.4 ^o | 1.005 (da) | 0.744 | 22.47 ^h | 71.2 | AIST (9/12) | Sharp [6] |
| Dye sensitised (submodule) | 9.9 ± 0.4 ^o | 17.11 (ap) | 0.719 ⁱ | 19.4 ⁱ | 71.4 | AIST (8/10) | Sony, 8 parallel cells [28] |
| Organic | | | | | | | |
| Organic thin-film | 10.7 ± 0.3 ^o | 1.013 (da) | 0.872 | 17.75 ^h | 68.9 | AIST (10/12) | Mitsubishi Chemical (4.4 mm × 23.0 mm) [10] |
| Organic (submodule) | 6.8 ± 0.2^o | 395.9 (da) | 0.798ⁱ | 13.50ⁱ | 62.8 | AIST (10/12) | Toshiba (15 series cells) [13] |
| Multijunction Devices | | | | | | | |
| InGaP/GaAs/InGaAs | 37.7 ± 1.2 | 1.047 (ap) | 3.014 | 14.57^h | 86.0 | AIST (9/12) | Sharp [14] |
| a-Si/nc-Si/nc-Si (thin film) | 13.4 ± 0.4 ^p | 1.006 (ap) | 1.963 | 9.52 ^h | 71.9 | NREL (7/12) | LG Electronics [15] |
| a-Si/nc-Si (thin film cell) | 12.3 ± 0.3% ^q | 0.962 (ap) | 1.365 | 12.93 ^r | 69.4 | AIST (7/11) | Kaneka [29] |
| a-Si/nc-Si (thin film submodule) | 11.7 ± 0.4 ^{n,s} | 14.23 (ap) | 5.462 | 2.99 | 71.3 | AIST (9/04) | Kaneka [30] |

Any changes in the tables from those previously published [3] are set in bold type.

^aCIGS, CuInGaSe₂; a-Si, amorphous silicon/hydrogen alloy; nc-Si, nanocrystalline or microcrystalline silicon.

^bEffic., efficiency.

^c(ap), aperture area; (t), total area; (da), designated illumination area.

^dFF, fill factor.

^eFhG-ISE, Fraunhofer Institut für Solare Energiesysteme; JQA, Japan Quality Assurance; AIST, Japanese National Institute of Advanced Industrial Science and Technology.

^fSpectral response reported in Version 36 of these Tables.

^gRecalibrated from original measurement.

^hSpectral response and current–voltage curve reported in the present version of these Tables.

ⁱReported on a ‘per cell’ basis.

^jSpectral response and current–voltage curve reported in Version 40 of these Tables.

^kNot measured at an external laboratory.

^lSpectral response reported in Version 37 of these Tables.

^mLight soaked at Oerlikon prior to testing at NREL (1000 h, 1 sun, 50 °C).

ⁿMeasured under IEC 60904–3 Ed. 1: 1989 reference spectrum.

^oStability not investigated. References 9, 11 and 12 review the stability of similar devices.

^pLight soaked under 100 mW/cm² white light at 50 °C for over 1000 h.

^qStabilised by manufacturer.

^rSpectral response and current–voltage curve reported in Version 39 of these Tables.

^sStabilised by 174 h, 1 sun illumination after 20 h, 5 sun illumination at a sample temperature of 50 °C.

Table II. Confirmed terrestrial module efficiencies measured under the global AM1.5 spectrum (1000 W/m²) at a cell temperature of 25°C (IEC 60904-3: 2008, ASTM G-173-03 global).

| Classification ^a | Effic. ^b (%) | Area ^c (cm ²) | V _{oc} (V) | I _{sc} (A) | FF ^d (%) | Test centre (and date) | Description |
|-----------------------------------|-------------------------------|---|------------------------|------------------------|------------------------|--------------------------------|--------------------------------------|
| | | | | | | | |
| Si (crystalline) | 22.9 ± 0.6 | 778 (da) | 5.60 | 3.97 | 80.3 | Sandia (9/96) ^e | UNSW/Goehrmann [31] |
| Si (large crystalline) | 21.4 ± 0.6 | 15780 (ap) | 68.6 | 6.293 | 78.4 | NREL (10/09) | SunPower [32] |
| Si (multicrystalline) | 18.5 ± 0.4 | 14661 (ap) | 38.97 | 9.149 ^f | 76.2 | FhG-ISE (1/12) | Q-Cells (60 serial cells) [33] |
| Si (thin-film polycrystalline) | 8.2 ± 0.2 | 661 (ap) | 25.0 | 0.320 | 68.0 | Sandia (7/02) ^e | Pacific Solar (1–2 µm on glass) [34] |
| GaAs (thin film) | 24.1 ± 1.0 | 858.5 (ap) | 10.89 | 2.255 ^g | 84.2 | NREL (11/12) | Alta Devices [35] |
| CIGS | 15.7 ± 0.5 | 9703 (ap) | 28.24 | 7.254 ^h | 72.5 | NREL (11/10) | Miasole [36] |
| CIGSS (Cd free) | 13.5 ± 0.7 | 3459 (ap) | 31.2 | 2.18 | 68.9 | NREL (8/02) ^e | Showa Shell [37] |
| CdTe | 15.3 ± 0.5 | 6750.9 (ap) | 64.97 | 2.183 ^f | 72.9 | NREL (1/12) | First Solar [38] |
| a-Si/a-SiGe/hc-Si (tandem) | 10.5 ± 0.4ⁱ | 14316 (t) | 224.3 | 0.991 | 67.9 | AIST (9/12)^g | LG Electronics [15] |

Any changes in the tables from those previously published [3] are set in bold type.

^aCIGSS, CuInGaSe; a-Si, amorphous silicon/hydrogen alloy; a-SiGe, amorphous silicon/germanium/hydrogen alloy; nc-Si, nanocrystalline or microcrystalline silicon.^bEffic., efficiency.^c(t), total area; (ap), aperture area; (da), designated illumination area.^dFF, fill factor.^eRecalibrated from original measurement.^fSpectral response and/or current-voltage curve reported in Version 40 of these Tables.^gSpectral response and current-voltage curve reported in present version of these Tables.^hSpectral response reported in Version 37 of these Tables.ⁱStabilised at the manufacturer under the light-soaking conditions of IEC61646.

Table III. 'Notable Exceptions': 'top ten' confirmed cell and module results, not class records measured under the global AM1.5 spectrum (1000 W m^{-2}) at 25°C (IEC 60904-3: 2008, ASTM G-173-03 global).

| Classification ^a | Effic. ^b (%) | Area ^c (cm^2) | V_{oc} (V) | J_{sc} (mA/cm^2) | FF (%) | Test centre (and date) | Description |
|-----------------------------|----------------------------|--|------------------------|---|-------------|----------------------------|---|
| Cells (silicon) | | | | | | | |
| Si (MCZ crystalline) | 24.7 ± 0.5 | 4.0 (da) | 0.704 | 42.0 | 83.5 | Sandia (7/99) ^d | UNSW PERL, SEH MCZ substrate [39] |
| Si (large crystalline) | 24.2 ± 0.7 | 155.1(t) | 0.721 | 40.5 ^e | 82.9 | NREL (5/10) | Sunpower <i>n</i> -type CZ substrate [40] |
| Si (large crystalline) | 23.9 ± 0.6 | 102.7(t) | 0.748 | 38.89 ^f | 82.2 | AIST (2/12) | Panasonic HIT, <i>n</i> -type [41] |
| Si (large multicrystalline) | 19.5 ± 0.4 | 242.7(t) | 0.652 | 39.0 ^e | 76.7 | FhG ISE (3/11) | Q-Cells, laser fired contacts [42] |
| Cells (other) | | | | | | | |
| ClGS (thin film) | 20.3 ± 0.6 | 0.5015 (ap) | 0.740 | 35.4 ^e | 77.5 | FhG-ISE (6/10) | ZSW Stuttgart, ClGS on glass [43] |
| CZTSS (thin film) | 11.1 ± 0.3 | 0.4496 (ap) | 0.4598 | 34.54 ^g | 69.8 | Newport (2/12) | IBM solution grown [44] |
| CZTS (thin film) | 8.4 ± 0.2 | 0.4463 (ap) | 0.661 | 19.5^h | 65.8 | Newport (4/11) | IBM, thermal evaporation [16] |
| Organic (thin film) | 11.1 ± 0.3^i | 0.159 (ap) | 0.867 | 17.81^f | 72.2 | AIST (10/12) | Mitsubishi Chemical [10] |
| Luminescent submodule | 7.1 ± 0.2 | 25(ap) | 1.008 | 8.84 ^e | 79.5 | ESTI (9/08) | ECN Petten, GaAs cells [45] |

Any changes in the tables from those previously published [3] are set in bold type.

^aClGS, CuInGaSe₂; CZTSS, Cu₂ZnSnS_{4- γ} Se _{γ} ; CZTS, Cu₂ZnSnS₄.^bEffic., efficiency.^c(ap), aperture area; (t), total area, (da), designated illumination area.^dRecalibrated from original measurement.^eSpectral response reported in Version 37 of these Tables.^fSpectral response and current-voltage curve reported in Version 40 of these Tables.^gSpectral response and current-voltage curves reported in Version 39 of these Tables.^hSpectral response and current-voltage curves reported in the present version of these Tables.ⁱStability not investigated.

Table IV. Terrestrial concentrator cell and module efficiencies measured under the ASTM G-173-03 direct beam AM1.5 spectrum at a cell temperature of 25 °C.

| Classification | Effic. ^a | Area ^b (cm ²) | Intensity ^c (suns) | Test centre | | Description |
|----------------------------------|-------------------------|---|----------------------------------|----------------------------|--|--|
| | (%) | | | (and date) | | |
| Single Cells | | | | | | |
| GaAs | 29.1 ± 1.3 ^d | 0.0505 (da) | 117 | FhG-ISE (3/10) | | Fraunhofer ISE |
| Si | 27.6 ± 1.0 ^f | 1.00 (da) | 92 | FhG-ISE (11/04) | | Amonix back-contact [46] |
| Multijunction cells (monolithic) | | | | | | |
| GaInP/GaAs/GaInNAS | 44.0 ± 3 ^g | 0.3104 (ap) | 942 | NREL (10/12) | | Solar Junction [17] |
| InGaP/GaAs/InGaAs | 43.5 ± 2.6 ^h | 0.167 (da) | 306 | FhG-ISE (4/12) | | Sharp, inverted metamorphic [14] |
| GaInP/GaInAs/Ge | 41.6 ± 2.5 ^e | 0.3174(da) | 364 | NREL (8/09) | | Spectrolab, lattice-matched [47] |
| Submodule | | | | | | |
| GaInP/GaAs; GaInAsP/GaInAs | 38.5 ± 1.9 ^j | 0.202 (ap) | 20 | NREL (8/08) | | DuPont <i>et al.</i> , split spectrum [48] |
| Modules | | | | | | |
| Si | 20.5 ± 0.8 ^d | 1875 (ap) | 79 | Sandia (4/89) ^j | | Sandia/UNSW/ENTECH (12 cells) [49] |
| Triple Junction | 33.5 ± 0.5 ^k | 10,674.8 (ap) | N/A | NREL (5/12) | | Amonix [50] |
| 'Notable Exceptions' | | | | | | |
| Si (large area) | 21.7 ± 0.7 | 20.0 (da) | 11 | Sandia (9/90) ^j | | UNSW laser grooved [51] |

Any changes in the tables from those previously published [3] are set in bold type.

^aEffic., efficiency.^b(da), designated illumination area; (ap), aperture area.^cOne sun corresponds to direct irradiance of 1000 Wm⁻².^dNot measured at an external laboratory.^eSpectral response reported in Version 36 of these Tables.^fMeasured under a low aerosol optical depth spectrum similar to ASTM G-173-03 direct [52].^gCurrent-voltage curve reported in the present version of these Tables.^hSpectral response and current-voltage curve reported in present version of these Tables.ⁱSpectral response reported in Version 37 of these Tables.^jRecalibrated from original measurement.^kBased on ASTM E2527 rating, May 2012 (850 W/m² direct irradiance, 20 °C ambient, 4 m/s wind speed).

welcome to contact any of the authors with full details. Suggestions conforming to the guidelines will be included on the voting list for a future issue.

Table IV shows the best results for concentrator cells and concentrator modules (a smaller number of ‘notable exceptions’ for concentrator cells and modules additionally is included in Table IV).

Thirteen new results are reported in the present version of these Tables. The first new result in Table I is a new record for a large (156 mm × 156 mm) but thin (43 micron) silicon cell transferred from a reusable template. An efficiency of 20.1% has been measured at the National Renewable Energy Laboratory (NREL) for a 243-cm² device fabricated by Solixel, Inc. (Milpitas, CA, USA) [4].

The second new result is for a 1-cm² CdTe cell with 18.3% efficiency reported for a cell fabricated by GE Global Research [5] and measured by NREL. This improves upon the 17.3% cell result from First Solar reported in the previous version of these Tables [3] (Note: The current-density J_{sc} for the 17.3% result was incorrectly reported as 28.99 mA/cm² [3] rather than the correct value of 27.20 mA/cm²).

A third new result in Table I is an improvement in the performance of a 1-cm² dye-sensitised solar cell to 11.9%. The cell was fabricated by Sharp [6] and measured

at the Japanese National Institute of Advanced Industrial Science and Technology (AIST). Although slightly higher values for smaller area dye-sensitised cells have been reported in the journal *Science* [7], these higher values appear to be based solely on ‘in-house’ measurements [8], with such measurements known to be notably unreliable (editors of, and reviewers for, reputable journals are encouraged to ensure that any published cell result claiming to be the best in its field has been independently certified by an appropriately qualified laboratory). Along with other emerging technology devices, the stability of this device was not investigated, although the stability of earlier devices is reviewed elsewhere [9].

A fourth new result in Table I is an improvement of a 1-cm² organic solar cell efficiency to a new high of 10.7%. The rectangular cell (4.4 mm × 23.0 mm) was fabricated by the Mitsubishi Chemical Group Science and Technology Research Center, Inc. [10] and measured at AIST. Again, the stability of this device was not investigated, although that of earlier devices is reviewed elsewhere [11,12].

A fifth new result in Table I is an improvement in the efficiency to 6.8% for a 396-cm² organic cell submodule fabricated by Toshiba [13] and measured by AIST. The stability of this device also was not investigated.

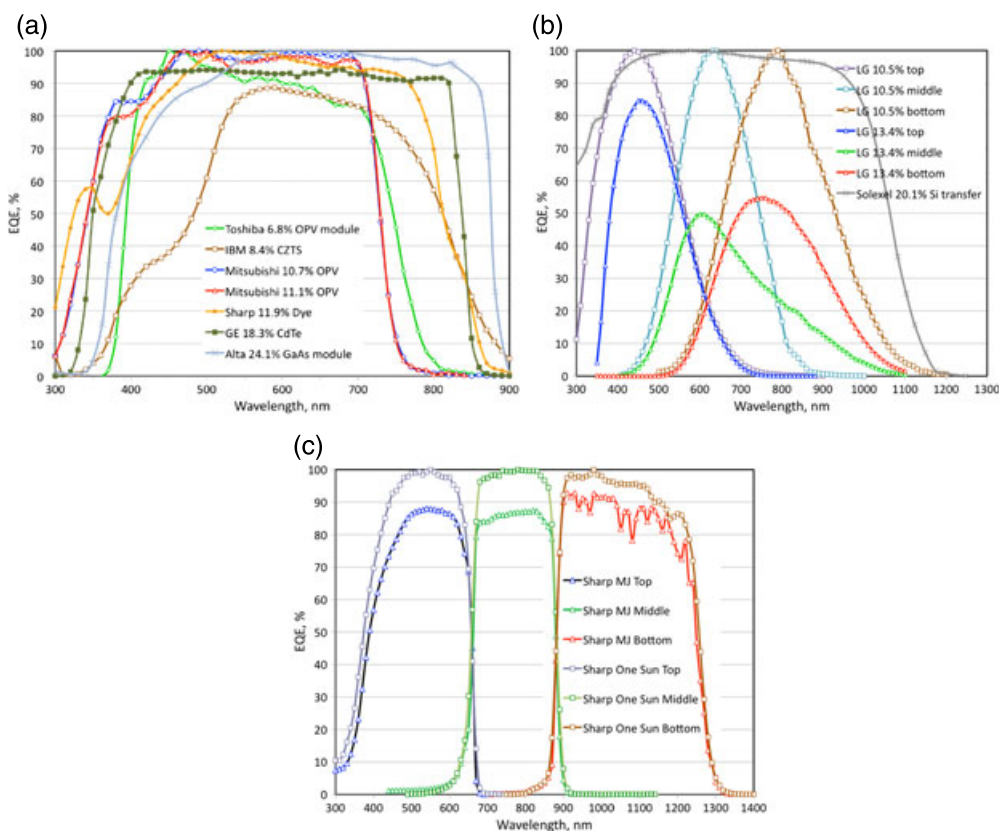


Figure 1. (a) External quantum efficiency (EQE) for the new CdTe and CZTS cell (absolute values) as well as normalised values for the GaAs module and dye-sensitised and organic cell and submodule results in this issue; (b) EQE for the new silicon cell (normalised values) and a-Si/nc-Si/nc-Si cell (absolute values) and a-Si/a-SiGe/nc-Si module (normalised values) entries in this issue; (c) EQE for two new III–V multijunction cells in this issue (normalised and absolute values).

A sixth major new result in Table I is a new record for energy conversion efficiency for any photovoltaic converter that does not use sunlight concentration. An efficiency of 37.7% is reported for a 1-cm² InGaP/GaAs/InGaAs monolithic multijunction cell fabricated by Sharp [14] and again measured at AIST.

The final new result in Table I is an improvement in the stabilised efficiency of a 1-cm² a-Si/nc-Si/nc-Si triple junction cell to 13.4%. The cell was fabricated by the LG Electronics Advanced Research Institute [15] and measured at NREL. Related to this result, in Table II, a new efficiency record of 10.5% is reported for a large (1.4 m² total area) a-Si/a-SiGe/nc-Si module again fabricated by LG Electronics [15] but measured at AIST. Another new result in Table II is a new record reported for independently confirmed global solar module performance. An efficiency of 24.1% was measured for a 860-cm² GaAs module fabricated by Alta Devices and measured by NREL.

The first new result in Table III relates to an efficiency increase to 8.4% for a small area (0.45 cm²) pure sulphide CZTS solar cell fabricated by the IBM T.J. Watson Research Center [16] using thermal evaporation and measured at the Newport Technology and Application Center's Photovoltaic Lab.

The second new result in Table III relates to an efficiency increase to 11.1% for a small area (0.159 cm²) organic solar cell again fabricated by Mitsubishi Chemical [10] and measured at AIST. This cell is much smaller than the 1-cm² size required for classification as an outright record.

Table IV reports two new results for concentrator cells. A new record of 44.0% for the conversion of sunlight by any means is reported for a 0.3 cm² MJ cell operating at a concentration of 942 suns (direct irradiance of 942 kW/m²). The cell was a GaInP/GaAs/GaInNAs triple junction device fabricated by Solar Junction [17] and measured at NREL. Demonstrating that such high efficiencies are not unique to a specific fabrication approach or measurement centre, a new efficiency of 43.5% is also reported for a 0.167-cm² inverted metamorphic triple-junction cell (InGaP/GaAs/InGaAs) fabricated by Sharp [14] and measured at the Fraunhofer Institute for Solar Energy Systems (FhG-ISE).

The EQEs for the new CdTe and CZTS cell and GaAs module results as well as for the dye-sensitised and organic cell and submodule results of Table I are shown in Figure 1 (a). Figure 1(b) shows the EQE of the new silicon cell and a-Si/a-SiGe/nc-Si cell and module results reported in the present issue of these Tables. Figure 1(c) shows the EQE of two of the new III–V multijunction cell results.

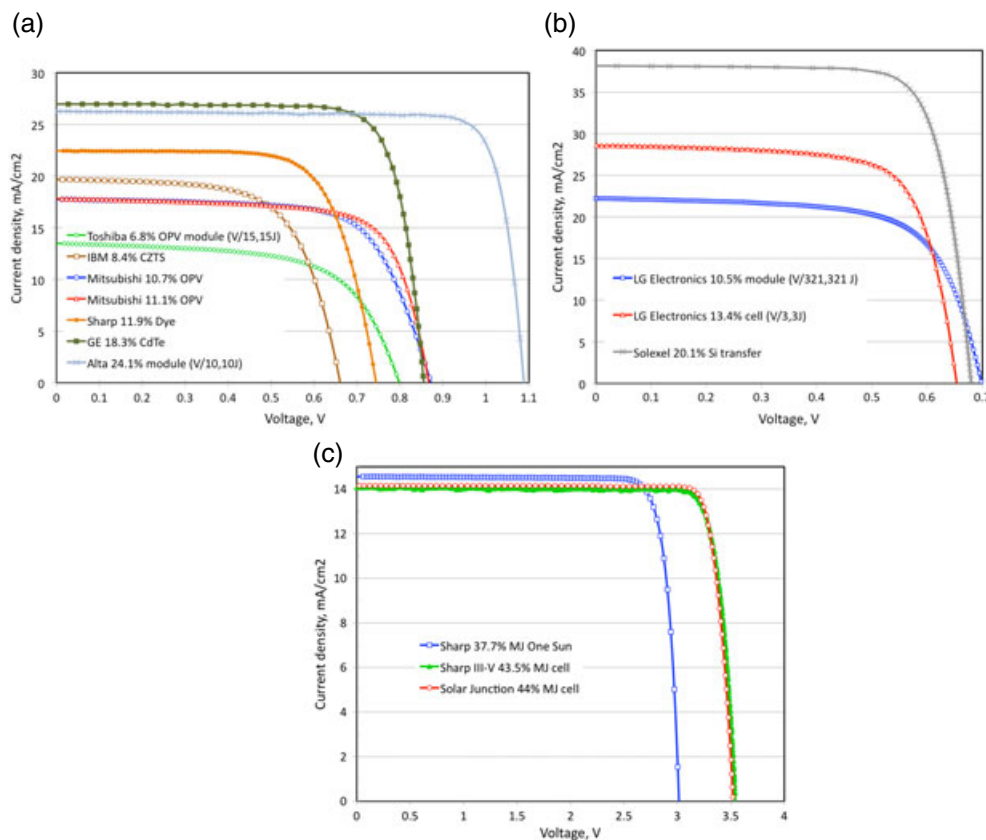


Figure 2. (a) Current density–Voltage (J – V) curve for the new CdTe and CZTS cell and GaAs module results, as well as for the dye-sensitised and organic cell and submodule results in this issue; (b) J – V curves for the new silicon and a-Si/nc-Si/nc-Si cell and a-Si/a-SiGe/nc-Si module entries in this issue; (c) J – V curves for the new multijunction cells in this issue (for the concentrator cells, the current density is normalised to an irradiance of 1 kW/m²).

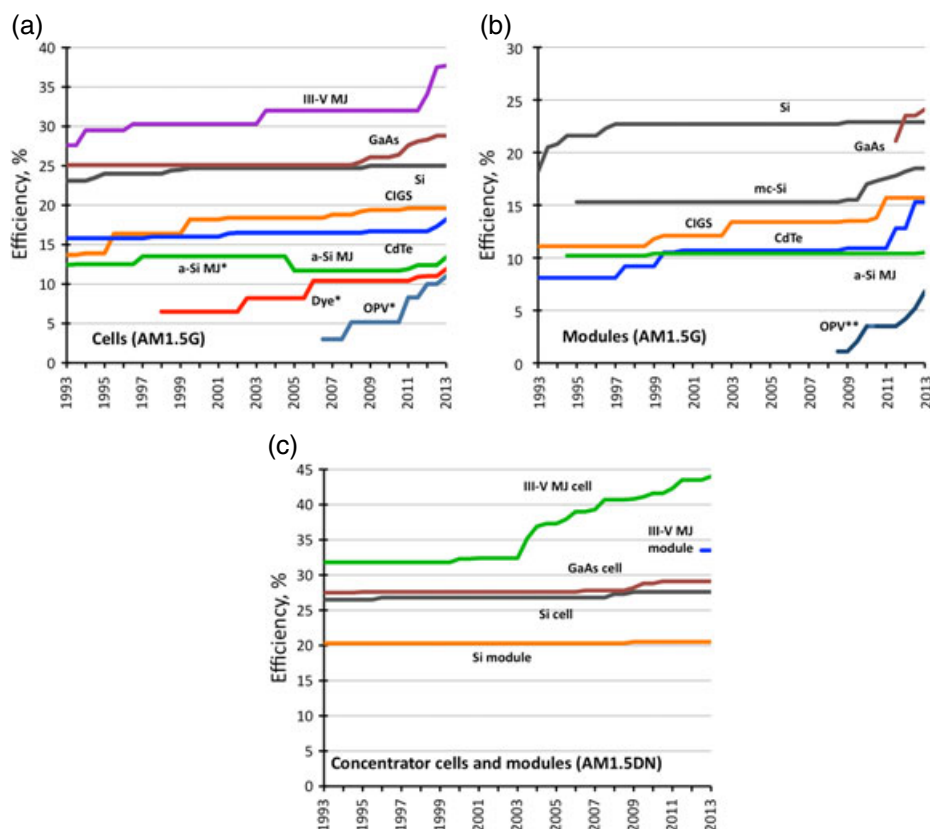


Figure 3. Twenty years of progress: (a) Highest confirmed efficiencies for $\geq 1\text{-cm}^2$ area cells fabricated using the different technologies shown (*the results for the OPV and dye-sensitised results are unstabilised results as are those for a-Si multi-junction cells prior to 2005); (b) highest confirmed module results for modules sizes $\geq 800\text{-cm}^2$, except for OPV where the module results are unstabilised and module sizes range from 200–400 cm^2 ; (c) highest confirmed concentrator cell and module results.

Figure 2 shows the current density–voltage (J – V) curves for the corresponding devices and for one additional device for which the EQE is not reported. For the case of modules and some tandem devices, the measured I – V data has been reported on a ‘per cell’ basis (measured voltage has been divided by the number of cells in series, whereas measured current has been multiplied by this quantity and divided by the module area).

Figure 3 reports 20 years of progress in confirmed cell and module efficiencies since the first version of these Tables was published in 1993. Figure 3(a) shows progress with ‘one-sun’ cells of $\geq 1\text{-cm}^2$ area. Recent progress with OPV, GaAs and MJ III–V cells has been most notable. Figure 3(b) shows similar progress with photovoltaic modules with OPV, CdTe and the mainstream multicrystalline-Si (mc-Si) being the recent standouts. Figure 3 (c) shows the results for concentrator cells and modules. Impressive progress has been made with monolithic III–V MJ cells where efficiency has been improved from 31.8% to 44.0% over the 20-year period (efficiency in this case is boosted relative to Figure 3(a) and (b) by being based on only the direct normal component of the solar spectrum).

3. DISCLAIMER

While the information provided in the tables is provided in good faith, the authors, editors and publishers cannot accept direct responsibility for any errors or omissions.

ACKNOWLEDGEMENTS

The Australian Centre for Advanced Photovoltaics commenced in January 2013 with support from the Australian Solar Institute.

REFERENCES

- Green MA, Emery K, Hishikawa Y, Warta W, Dunlop ED. Solar cell efficiency tables (version 39). *Progress in Photovoltaics: Research and Applications* 2012; **20**: 12–20.
- Green MA, Emery K, Hishikawa Y, Warta W. Solar cell efficiency tables (version 33). *Progress in Photovoltaics: Research and Applications* 2009; **17**: 85–94.

3. Green MA, Emery K, Hishikawa Y, Warta W, Dunlop ED. Solar cell efficiency tables (version 40). *Progress in Photovoltaics: Research and Applications* 2012; **20**: 606–614.
4. Moslehi MM, Kapur P, Kramer J, Rana V, Seutter S, Deshpande A, Stalcup T, Kommera S, Ashjaee J, Calcaterra A, Grupp D, Dutton D, Brown R. World-record 20.6% efficiency 156 mm × 156 mm full-square solar cells using low-cost kerfless ultrathin epitaxial silicon and porous silicon lift-off technology for industry-leading high-performance smart PV modules. PV Asia Pacific Conference (APVIA/PVAP), 24 October 2012.
5. www.ge-energy.com/products_and_services/products/solar_power/cdte_thin_film_solar_module78.jsp (accessed 13 November 2012).
6. Komiya R, Fukui A, Murofushi N, Koide N, Yamanaka R, Katayama H. Improvement of the conversion efficiency of a monolithic type dye-sensitized solar cell module. *Technical Digest, 21st International Photovoltaic Science and Engineering Conference*, Fukuoka, November 2011; 2C-50-08.
7. Yella A, Lee H-W, Tsao HN, Yi C, Chandiran AK, Nazeeruddin MDK, Diau EW-G, Yeh C-Y, Zakeeruddin SM, Grätzel M. Porphyrin-sensitized solar cells with cobalt (II/III)-based redox electrolyte exceed 12 percent efficiency. *Science* 2011; **334**: 629–633.
8. Yella A, Lee H-W, Tsao HN, Yi C, Chandiran AK, Nazeeruddin MDK, Diau EW-G, Yeh C-Y, Zakeeruddin SM, Grätzel M. Supporting online material for porphyrin-sensitized solar cells with cobalt (II/III)-based redox electrolyte exceed 12 percent efficiency. *Science* 2011 (DOI: 10.1126/science.1209688).
9. Asghar MI, Miettunen K, Halme J, Vahermaa P, Toivola M, Aitola K, Lund P. Review of stability for advanced dye solar cells. *Energy Environmental Science* 2010; **3**: 418–426.
10. Service R. Outlook brightens for plastic solar cells. *Science* 2011; **332**(6027): 293.
11. Tanenbaum DM, Hermenau M, Voroshazi E, Lloyd MT, Galagan Y, Zimmermann B, Hoesel M, Dam HF, Jørgensen M, Gevorgyan SA, Kudret S, Maes W, Lutsen L, Vanderzande D, Wuerfel U, Andriessen R, Roesch R, Hopper H, Teran-Escobar G, Lira-Cantu M, Rivaton A, Uzunoğlu GY, Germack D, Andreasen B, Madsen MV, Norrmany K, Krebs FC. The ISOS-3 inter-laboratory collaboration focused on the stability of a variety of organic photovoltaic devices. *RSC Advances* 2012; **2**: 882–893.
12. Krebs FC (ed). Stability and degradation of organic and polymer solar cells, Wiley, Chichester, 2012; Jørgensen M, Norrman K, Gevorgyan SA, Tromholt T, Andreasen, B and Krebs FC. Stability of polymer solar cells. *Advanced Materials* 2012; **24**: 580–612.
13. Hosoya M, Oooka H, Nakao H, Gotanda T, Hayase R, Nakano Y, Saito M. Development of organic thin film photovoltaic modules. *Proceedings, the 73th Fall Meeting of Japan Society of Applied Physics*, 2012: 12–380.
14. Yoshida A, Agui T, Katsuya N, Murasawa K, Juso H, Sasaki K, Takamoto T. Development of InGaP/GaAs/InGaAs inverted triple junction solar cells for concentrator application. *21st International Photovoltaic Science and Engineering Conference (PVSEC-21)*, Fukuoka, Japan 2011.
15. Ahn SW, Lee SE, Lee HM. Toward commercialization of triple-junction thin-film silicon solar panel with >12% efficiency. *27th European Photovoltaic Solar Energy Conference*, 3AO5.1, Frankfurt, September 2012.
16. Shin B, Gunawan O, Zhu Y, Bojarczuk NA, Chey SJ, Guha S. Thin film solar cell with 8.4% power conversion efficiency using an earth-abundant Cu₂ZnSnS₄ absorber. *Progress in Photovoltaics: Research and Applications* 2013; **1**: 72–76.
17. www.sj-solar.com.
18. Zhao J, Wang A, Green MA, Ferrazza F. Novel 19.8% efficient “honeycomb” textured multicrystalline and 24.4% monocrystalline silicon solar cells. *Applied Physics Letters* 1998; **73**: 1991–1993.
19. Schultz O, Glunz SW, Willeke GP. Multicrystalline silicon solar cells exceeding 20% efficiency. *Progress in Photovoltaics: Research and Applications* 2004; **12**: 553–558.
20. Keevers MJ, Young TL, Schubert U, Green MA. 10% efficient CSG minimodules. *22nd European Photovoltaic Solar Energy Conference*, Milan, September 2007.
21. Kayes BM, Nie H, Twist R, Spruytte SG, Reinhardt F, Kizilyalli IC, Higashi GS. 27.6% conversion efficiency, a new record for single-junction solar cells under 1 sun illumination. *Proceedings of the 37th IEEE Photovoltaic Specialists Conference*, 2011.
22. Venkatasubramanian R, O’Quinn BC, Hills JS, Sharps PR, Timmons ML, Hutchby JA, Field H, Ahrenkiel A, Keyes B. 18.2% (AM1.5) efficient GaAs solar cell on optical-grade polycrystalline Ge substrate. *Conference Record, 25th IEEE Photovoltaic Specialists Conference*, Washington, May 1997; 31–36.
23. Keavney CJ, Haven VE, Vernon SM. Emitter structures in MOCVD InP solar cells. *Conference Record, 21st IEEE Photovoltaic Specialists Conference*, Kissimmee, May, 1990; 141–144.
24. Repins I, Contreras MA, Egaas B, DeHart C, Scharf J, Perkins CL, To B and Noufi R. 19.9%-efficient ZnO/CdS/CuInGaSe₂ solar cell with 81.2% fill factor. *Progress in Photovoltaics: Research and Applications* 2008; **16**: 235–239.
25. Wallin E, Malm U, Jarmar T, Lundberg O, Edoff M, Stolt L. World-record Cu(In,Ga)Se₂-based thin-film

- sub-module with 17.4% efficiency. *Progress in Photovoltaics: Research and Applications* 2012; published online DOI: 10.1002/pip.2246.
26. Benagli S, Borrello D, Vallat-Sauvain E, Meier J, Kroll U, Hötzel J, Spitznagel J, Steinhauser J, Castens L, Djeridane Y. High-efficiency amorphous silicon devices on LPCVD-ZNO TCO prepared in industrial KAI-M R&D Reactor. *24th European Photovoltaic Solar Energy Conference*, Hamburg, September 2009.
 27. Yamamoto K, Toshimi M, Suzuki T, Tawada Y, Okamoto T, Nakajima A. Thin film poly-Si solar cell on glass substrate fabricated at low temperature. *MRS Spring Meeting*, April, 1998, San Francisco.
 28. Morooka M, Ogura R, Orihashi M, Takenaka M. Development of dye-sensitized solar cells for practical applications. *Electrochemistry* 2009; **77**: 960–965.
 29. <http://www.kaneka-solar.com>.
 30. Yoshimi M, Sasaki T, Sawada T, Suezaki T, Meguro T, Matsuda T, Santo K, Wadano K, Ichikawa M, Nakajima A, Yamamoto K. High efficiency thin film silicon hybrid solar cell module on 1 m²-class large area substrate. *Conf. Record, 3rd World Conference on Photovoltaic Energy Conversion*, Osaka, May, 2003; 1566–1569.
 31. Zhao J, Wang A, Yun F, Zhang G, Roche DM, Wenham SR, Green MA. 20,000 PERL silicon cells for the “1996 World Solar Challenge” solar car race. *Progress in Photovoltaics* 1997; **5**: 269–276.
 32. Swanson RM. Solar cells at the cusp. Presented at *19th International Photovoltaic Science and Engineering Conference*, Korea, November 2009.
 33. www.pvtech.org/news/q_cells_sets_two_new_world_records_for_multi_crystalline_and_quasi_mono_sol.
 34. Basore PA. Pilot production of thin-film crystalline silicon on glass modules. *Conf. Record, 29th IEEE Photovoltaic Specialists Conference*, New Orleans, May, 2002, 49–52.
 35. Mattos LS, Scully SR, Syfu M, Olson E, Yang L, Ling C, Kayes BM, He G. New module efficiency record: 23.5% under 1-sun illumination using thin-film single-junction GaAs solar cells. *Proceedings of the 38th IEEE Photovoltaic Specialists Conference*, 2012.
 36. <http://www.miasole.com>.
 37. Tanaka Y, Akema N, Morishita T, Okumura D, Kushiya K. Improvement of V_{oc} upward of 600 mV/cell with CIGS-based absorber prepared by selenization/sulfurization. *Conf. Proceedings, 17th EC Photovoltaic Solar Energy Conference*, Munich, October, 2001; 989–994.
 38. Press release, First Solar, 16 January 2012.
 39. Zhao J, Wang A and Green, MA. 24.5% efficiency silicon PERT cells on MCZ substrates and 24.7% efficiency PERL cells on FZ substrates. *Progress in Photovoltaics* 1999; **7**: 471–474.
 40. Cousins PJ, Smith DD, Luan HC, Manning J, Dennis TD, Waldhauer A, Wilson KE, Harley G, Mulligan GP. Gen III: improved performance at lower cost. *35th IEEE PVSC*, Honolulu, HI, June 2010.
 41. Kinoshita T, Fujishima D, Yano A, Ogane A, Tohoda S, Matsuyama K, Nakamura Y, Tokuoka N, Kanno H, Sakata H, Taguchi M, Maruyama E. The approaches for high efficiency HIT solar cell with very thin (<100 nm) silicon wafer over 23%. *26th EUPVSC Proceedings* 2011; 871–874.
 42. Engelhart P, Wendt J, Schulze A, Klenke C, Mohr A, Petter K, Stenzel F, Hörnlein S, Kauert M, Junghänel M, Barkenfelt B, Schmidt S, Rychtarik D, Fischer M, Müller JW, Wawer P. R&D pilot line production of multi-crystalline Si solar cells exceeding cell efficiencies of 18 %. *Energy Procedia, 1st International Conference on Silicon Photovoltaics*, Freiburg, 17–20 April, 2010 (www.Elsevier.com/locate/procedia).
 43. Jackson P, Hariskos D, Lotter E, Paetel S, Wuerz R, Menner R, Wischmann W, Powalla M. New world record efficiency for Cu(In,Ga)Se₂ thin-film solar cells beyond 20%. *Progress In Photovoltaics: Research and Applications* 2011; published online DOI: 10.1002/pip.1078 (Presented at *25th EU PVSEC WCPEC-5*, Valencia, Spain, 2010).
 44. Todorov TK, Tang J, Bag S, Gunawan O, Gokmen T, Zhu Y, Mitzi DB. Beyond 11% efficiency: Characteristics of state-of-art Cu₂ZnSn(S₂,S)₄ solar cells. *Advanced Energy Materials* 2012; published online DOI: 10.1002/aenm.201200348.
 45. Slooff LH, Bende EE, Burgers AR, Budel T, Pravettoni M, Kenny RP, Dunlop ED, Buechtemann A. A luminescent solar concentrator with 7.1% power conversion efficiency. *Phys. Stat. Sol. (RRL)* 2008; **2** (6): 257–259.
 46. Slade A, Garboushian V. 27.6% efficient silicon concentrator cell for mass production. *Technical Digest, 15th International Photovoltaic Science and Engineering Conference*, Shanghai, October 2005; 701.
 47. King RR, Boca A, Hong W, Liu X-Q, Bhusari D, Larrabee D, Edmondson KM, Law DC, Fetzer CM, Mesropian S, Karam NH. Band-gap-engineered architectures for high-efficiency multijunction concentrator solar cells. Presented at the *24th European Photovoltaic Solar Energy Conference and Exhibition*, Hamburg, Germany, 21–25 Sep. 2009.
 48. McCambridge JD, Steiner MA, Unger BA, Emery KA, Christensen EL, Wanlass MW, Gray AL, Takacs L, Buelow R, McCollum TA, Ashmead JW, Schmidt GR, Haas AW, Wilcox JR, Meter JV, Gray JL, Moore

- DT, Barnett AM, Schwartz RJ. Compact spectrum splitting photovoltaic module with high efficiency. *Progress In Photovoltaics: Research and Applications* 2011; **19**: 352–360.
49. Chiang CJ, Richards EH. A 20% efficient photovoltaic concentrator module. *Conf. Record, 21st IEEE Photovoltaic Specialists Conference*, Kissimmee, May, 1990, 861–863.
50. Gordon R, Slade A, Garboushian V. A 30% efficient (>250 Watt) module using multijunction solar cells and their one-year on-sun field performance, in high and low concentration for solar electric applications II. In *Proceedings of the SPIE: Bellingham, WA*, Vol. 6649, Symko-Davies M (ed)., 2007; 664902.
51. Zhang F, Wenham SR, Green MA. Large area, concentrator buried contact solar cells. *IEEE Trans. on Electron Devices* 1995; **42**: 144–149.
52. Gueymard CA, Myers D, Emery K. Proposed reference irradiance spectra for solar energy systems testing. *Solar Energy* 2002; **73**: 443–467.