


PASS

SUBMITTER

Ajanta Silk
A-4003-4004, Radha Krishna Logistic Park, Near Bharat Cancer Hospital, Saroli, Surat, Gujarat, 385010, India

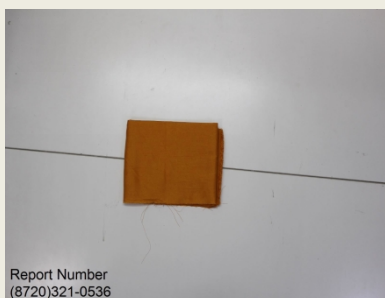

Report Number
(8720)321-0536

**STYLE
NUMBER**

DESERT SUN 16-1149

**PRODUCT
DESCRIPTION**

POLY RAW SLUB, DESERT SUN 16-1149

**EXECUTIVE
SUMMARY**

The submitted sample(s) MEET all the tested requirement(s).

REMARKS

/

**TECHNICAL
QUESTIONS**

Vijith K P
Directline +91-080-40701600.Ext:684
vijith.kp@in.bureauveritas.com

SIGNATURES

Bureau Veritas Consumer Products Services (I) Pvt Ltd



**GENERAL
INFORMATION**

Pradipta Kr. Lenka
Directline +91-080-40701600.Ext:632
pradipta.kumar@in.bureauveritas.com

Vijith K P
Program Manager
Softlines Department

Note: The submitted samples were not drawn by the laboratory



BUREAU
VERITAS

Test Report: (8720)321-0536
MYNTRA JABONG INDIA (P) LTD

Received Date: November 16, 2020

Report Date: November 18, 2020

BRAND	Sztori
TEST ITEM	Fabric
SAMPLE QUANTITY	2 MTR
COLOUR	DESERT SUN 16-1149
STYLE REFERENCE NO.	DESERT SUN 16-1149
COUNTRY OF ORIGIN	INDIA
FABRIC MILL NAME	AJANTA EXPORTS
MANUFACTURER	AJANTHA SILK
ORDER/PO NO.	N/A
PI / PO NO.	/
FABRIC CONSTRUCTION	100% POLYESTER
SEASON	SS-21
FABRIC WEIGHT	75 GSM
WOVEN OR KNITS OR DENIM	Woven
DIVISION/DEPARTMENT	Women's
TOPS OR BOTTOM	Tops
COUNTRY OF DESTINATION	INDIA
END USE	WOMEN'S WEAR
YARN COUNT	N/A
SIZE	N/A
AGE RANGE	N/A
TYPE OF FINISH/DYE	DYED
TYPE OF PRINT	DYEING
SOLE MATERIAL	/
ORDER QUANTITY	1550 MTR
ADDITIONAL INFORMATION	/
SUBMITTED FIBER CONTENT	100% POLYESTER
ACTUAL FIBER CONTENT	/
SUGGESTED FIBER CONTENT	/



BUREAU
VERITAS

Test Report: (8720)321-0536
MYNTRA JABONG INDIA (P) LTD

Received Date: November 16, 2020

Report Date: November 18, 2020

SUBMITTED CARE INSTRUCTION(S)	MACHINE WASH COLD TUMBLE DRY LOW
CLIENT EXPECTED CARE INSTRUCTION	/
SUGGESTED CARE INSTRUCTION(S)	/
RANGE	/
GENDER	/
VENDOR ARTICLE NO.	/
PROTOCOL NUMBER	MYNT-SL-PTCL-00301-IND-WOVEN FABRIC DENIM FABRIC-V9
PROTOCOL STAR LEVEL	/
FAIL RETEST	NO
PREVIOUS REPORT NUMBER	/
RETEST SAMPLE NUMBER	/
FABRIC REPORT NUMBER	/
REPORT EXPIRATION DATE	/



**BUREAU
VERITAS**

Test Report: (8720)321-0536 MYNTRA JABONG INDIA (P) LTD

Received Date: November 16, 2020

Report Date: November 18, 2020

TEST RESULTS FOR POLY RAW SLUB

TESTED PROPERTY	REQUIREMENTS	RESULTS	RATING
Linear Density of Yarn Removed from Woven Fabric (ISO 7211-5:1984)			
Desert Sun 16-1149			DATA
warp (D)	MYNT-SL-301-IND-V9 -5 to 5 %	52.2 D	
weft ('S)	-5 to -5 %	1/26.2'S	
Fabric count of woven fabric (ASTM D3775-17e1)			
Desert Sun 16-1149			DATA
Ends	MYNT-SL-301-IND-V9 Provide test results. No PASS/FAIL comment.	108 per inch	
Picks	(As Claim (N/A))	72 per inch	
Dimensional Changes of Fabrics in Washing (ISO 3759:2011 / ISO 5077:2007 / ISO 6330:2012 (Mod))###			
3N, TUMBLE DRY LOW, 3 MACHINE WASHES			PASS
Desert Sun 16-1149			
		Dimensional Change(%)	
Lengthwise	Dimensional Change -3 to 3 %	-0.6	
Widthwise	Dimensional Change -3 to 3 %	0.0	
Tear properties of fabrics: Ballistic Pendulum Method (Elmendorf) (ISO 13937-1:2000)			
Desert Sun 16-1149			PASS
Across Warp	MYNT-SL-301-IND-V9 Min. 800 gf	1305.6 gf	
Across Weft	Min. 700 gf	2598.4 gf	
Colourfastness to rubbing (ISO 105-X12:2016)			
Desert Sun 16-1149			PASS
Colour Staining - Dry	MYNT-SL-301-IND-V9 Min. Grade 3-4	Grade 4-5	
Colour Staining - Wet	Min. Grade 2-3	Grade 4-5	
Colourfastness to washing (AATCC 61-13 / SASO ISO 105-C10:2006)###			
Desert Sun 16-1149			PASS
Colour Change	MYNT-SL-301-IND-V9 Min. Grade 4	Grade 4	
Colour Staining on Acetate	Min. Grade 3-4	Grade 4-5	
Colour Staining on Cotton		Grade 4-5	
Colour Staining on Polyamide		Grade 4-5	
Colour Staining on Polyester		Grade 4-5	
Colour Staining on Acrylic		Grade 4-5	
Colour Staining on Wool		Grade 4-5	
Colorfastness Rating			



Test Report: (8720)321-0536
MYNTRA JABONG INDIA (P) LTD

Received Date: November 16, 2020

Report Date: November 18, 2020

TEST RESULTS FOR POLY RAW SLUB

TESTED PROPERTY	REQUIREMENTS	RESULTS	RATING
Color Change		Color Stain / Self Staining	
5 - Negligible or No Change		5 - Negligible or No Staining	
4 - Slightly Changed		4 - Slightly Stained	
3 - Noticeably Changed		3 - Noticeably Stained	
2 - Considerably Changed		2 - Considerably Stained	
1 - Much Changed		1 - Heavily Stained	

Non-accredited test under NABL scope

END OF REPORT