


PASS

SUBMITTER

AJANTA SILK
GUJARAT, INDIA

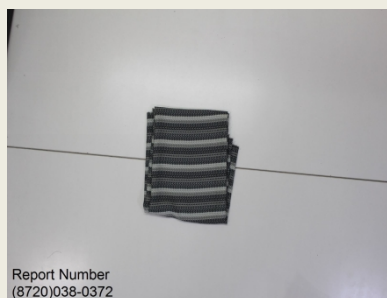

Report Number
(8720)038-0372

**STYLE
NUMBER**

GEO STRIPE COMBO-1 GREY

**PRODUCT
DESCRIPTION**

100% POLYESTER POLY MOSS CREPE

**EXECUTIVE
SUMMARY**

The submitted sample(s) MEET all the tested requirement(s).

REMARKS

/

**TECHNICAL
QUESTIONS**

Vijith K P
Directline +91-080-40701600.Ext:684
Vijith.kp@in.bureauveritas.com

SIGNATURES

Bureau Veritas Consumer Products Services (I) Pvt Ltd



**GENERAL
INFORMATION**

Pradipta Kr. Lenka
Directline +91-080-40701600.Ext:632
Pradipta.kumar@in.bureauveritas.com

Vijith K P
Program Manager
Softlines Department



BUREAU
VERITAS

Test Report: (8720)038-0372
MYNTRA JABONG INDIA (P) LTD

Received Date: February 07, 2020

Report Date: February 10, 2020

BRAND	dressberry
TEST ITEM	Fabric
SAMPLE QUANTITY	2MTR
COLOUR	GREY
STYLE REFERENCE NO.	N/A
COUNTRY OF ORIGIN	INDIA
FABRIC MILL NAME	/
MANUFACTURER	AJANTA SILK
ORDER/PO NO.	N/A
PI / PO NO.	/
FABRIC CONSTRUCTION	100% POLYESTER
SEASON	SS20
FABRIC WEIGHT	115 GSM
WOVEN OR KNITS OR DENIM	Woven
DIVISION/DEPARTMENT	Women's
TOPS OR BOTTOM	Tops
COUNTRY OF DESTINATION	INDIA
END USE	WOMEN'S WEAR
YARN COUNT	N/A
SIZE	N/A
AGE RANGE	N/A
TYPE OF FINISH/DYE	PRINT
TYPE OF PRINT	DISPERSE PRINT
SOLE MATERIAL	/
ORDER QUANTITY	1580 MTR
ADDITIONAL INFORMATION	/
SUBMITTED FIBER CONTENT	100% POLYESTER
ACTUAL FIBER CONTENT	/
SUGGESTED FIBER CONTENT	/



**BUREAU
VERITAS**

Test Report: (8720)038-0372
MYNTRA JABONG INDIA (P) LTD

Received Date: February 07, 2020

Report Date: February 10, 2020

SUBMITTED CARE INSTRUCTION(S)	MACHINE WASH COLD, TUMBLE DRY LOW
CLIENT EXPECTED CARE INSTRUCTION	/
SUGGESTED CARE INSTRUCTION(S)	/
RANGE	/
GENDER	/
VENDOR ARTICLE NO.	/
PROTOCOL NUMBER	MYNT-SL-PTCL-00301-IND-WOVEN FABRIC DENIM FABRIC-V8
PROTOCOL STAR LEVEL	/
FAIL RETEST	NO
PREVIOUS REPORT NUMBER	/
RETEST SAMPLE NUMBER	/
FABRIC REPORT NUMBER	/
REPORT EXPIRATION DATE	/



**BUREAU
VERITAS**

Test Report: (8720)038-0372 MYNTRA JABONG INDIA (P) LTD

Received Date: February 07, 2020

Report Date: February 10, 2020

TEST RESULTS FOR 100% POLYESTER POLY MOSS CREPE

TESTED PROPERTY	REQUIREMENTS	RESULTS	RATING
Linear Density of Yarn Removed from Woven Fabric (ISO 7211-5:1984)			
100% Polyester Poly Moss Crepe			DATA
Warp	MYNT-SL-301-IND-V8 -5 to 5 %	78.9 D	
Weft		158.6 D	
Fabric count of woven fabric (ASTM D3775-17e1)			
100% Polyester Poly Moss Crepe			DATA
Ends	MYNT-SL-301-IND-V8 Provide test results. No PASS/FAIL comment. (As Claim (N/A))	164 per inch	
Picks		76 per inch	
Dimensional Changes of Fabrics in Washing (ISO 3759:2011 / ISO 5077:2007 / ISO 6330:2012 (Mod))###			
100% Polyester Poly Moss Crepe			PASS
		Dimensional Change(%)	
Lengthwise	Dimensional Change -3 to 3 %	-0.4	
Widthwise	Dimensional Change -3 to 3 %	-0.5	
Tear properties of fabrics: Ballistic Pendulum Method (Elmendorf) (ISO 13937-1:2000)			
100% Polyester Poly Moss Crepe			PASS
Across Warp	MYNT-SL-301-IND-V8 Min. 800 gram(s)	4377.6 gram(s)	
Across Weft	Min. 700 gram(s)	4186.8 gram(s)	
Colourfastness to rubbing (ISO 105-X12:2016)			
100% Polyester Poly Moss Crepe			PASS
Colour Staining - Dry	MYNT-SL-301-IND-V8 Min. Grade 3-4	Grade 4-5	
Colour Staining - Wet	Min. Grade 2-3	Grade 4-5	



**BUREAU
VERITAS**

Test Report: (8720)038-0372 MYNTRA JABONG INDIA (P) LTD

Received Date: February 07, 2020

Report Date: February 10, 2020

TEST RESULTS FOR 100% POLYESTER POLY MOSS CREPE

TESTED PROPERTY	REQUIREMENTS	RESULTS	RATING
Colourfastness to washing (AATCC 61-13 / SASO ISO 105-C10:2006)###			
100% Polyester Poly Moss Crepe			PASS
Colour Change	MYNT-SL-301-IND-V8 Min. Grade 4	Grade 4	
Self Staining	/	Grade 4-5	
Colour Staining on Acetate	Min. Grade 3-4	Grade 4-5	
Colour Staining on Cotton		Grade 4-5	
Colour Staining on Polyamide		Grade 4-5	
Colour Staining on Polyester		Grade 4-5	
Colour Staining on Acrylic		Grade 4-5	
Colour Staining on Wool		Grade 4-5	

Colorfastness Rating

Color Change	Color Stain / Self Staining
5 - Negligible or No Change	5 - Negligible or No Staining
4 - Slightly Changed	4 - Slightly Stained
3 - Noticeably Changed	3 - Noticeably Stained
2 - Considerably Changed	2 - Considerably Stained
1 - Much Changed	1 - Heavily Stained

Non-accredited test under NABL scope

END OF REPORT