

1. SPECIFICATION

1.1 Drawing No. : 26305537

1.2 Mechanical

1.2.1 Dimensions : Refer to Page 3

1.2.2 Material

1.2.2.1 Header : SPCC filled with glass on the eyelet (SamMyung)

Tensile Strength	340 Mpa
Elongation (%)	27 – 31
Conductivity Thermal (W/m°C)	54.7 W/m-K @ Temperature 200 °C
	60.2 W/m-K @ Temperature 100 °C
	65.2 W/m-K @ Temperature 0 °C
CTE (µm/m-°C)	12.6 – 13.1 µm/m-°C @ Temperature 0 - 400 °C

1.2.2.2 Leads : NiCo 2918 (KOVAR)

Tensile Strength / Hardness (Mpa)	517 Mpa / 68 RB
Elongation (%)	30
Conductivity Thermal (W/m°C)	17
CTE (µm/m-°C)	4.90 µm/m-°C @ Temperature 30 - 400 °C

1.2.2.3 Electroless : Sn 99.3%, Cu 0.7% (Pb free)

Plating : Plating thickness 2 - 4 µm

1.3 Electrical

Not Applicable

1.4 Visual Requirements

1.4.1 Surface Quality : Residues are not allowed, plating must be evenly distributed; no voids, stain or rust permissible.

1.4.2 Size of voids on welding areas : < 20 µm

1.4.3 Punching part : Free of edges

1.5 Test Requirements

1.5.1 Glass-to-Metal Seal : Black transmission from 0.2 µm to 20 µm wavelength ≤ 0.1%

1.5.2 Transmission of glass melting : Output voltage should be < 40 mV using Excelitas test set-up. Calibrate with Excelitas calibration headers. See Figure 1.

1.5.3 Insulation resistance : > 10¹⁰ Ω (Lead-ground, supply voltage 100 V DC)

					NAME	DATE	DEPARTMENT	
				DRAWN BY	CHUA SH	25.09.2014	ENGINEERING	
				CHECKED BY	JONI	25.09.2014	ENGINEERING	
				DESCRIPTION				PART/ BAU NO
				BASEPLATE TO39 (3+1P) H2.00 L13.20 (SY)				26305537
0	ECN 19733	14.11.16	JONI					
REV	ECN NO.	DATE	NAME	SUBSTITUTE FOR :		DATED :		PAGE 1 OF 3

- 1.5.4 Leakage rate for Helium at : 10^{-8} bar $\text{cm}^3 \text{s}^{-1}$ max.
1 bar pressure difference (After thermal shock at 20°C - 500°C within 1 min.)
- 1.5.5 Gross Leak Test : No visible bubble is allowed from both sides of the header
- 1.5.6 Bubble Test : Per MIL-STD 883J and MIL-STD 38510

1.6 Incoming Quality

- 1.6.1 Inspection : Magnification 20X
- 1.6.2 Incoming Acceptance Level : 200 DPPM

2. REFERENCE

- 2.1 Supplier Mfg P/No. : TBD
- 2.2 Jedec Standard No. 9

3. DOCUMENTS FROM VENDOR


- 3.1 To provide transmission data of glass melting per delivery.
- 3.2 To enclose a copy of outgoing report and Certificate of Conformance for every shipment lot.

4. PACKING

- 4.1 Headers packed in dust-free sealed containers.
- 4.2 Maximum quantity : 5000 pcs/per container.
- 4.3 Shipment on pallet.
- 4.4 Each container must be identified with Bau. No., quantity, lot no. and manufacturing date.

5. STORAGE / HANDLING

- 5.1 No handling by bare hands, only with finger cots.

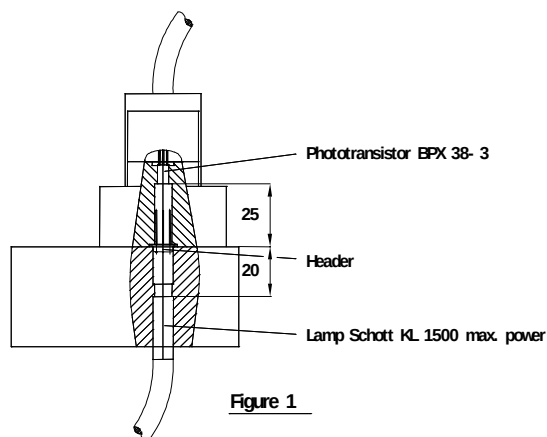

		NAME	DATE	DEPARTMENT	
	DRAWN BY	CHUA SH	25.09.2014	ENGINEERING	
	CHECKED BY	JONI	25.09.2014	ENGINEERING	
	DESCRIPTION				PART/ BAU NO
	BASEPLATE TO39 (3+1P) H2.00 L13.20 (SY)				26305537
	SUBSTITUTE FOR :		DATED :		PAGE 2 OF 3

