GLORIA ALLUMINIUM INDIA PVT LTD

Plot No. B-18, Chakan Industrial Area,Phase II,MIDC,Vasuli,Khed,Pune-410501

TEST REPORT

CUSTOMER NAME :- NIHVA TECHNOLOGIES

Test Report No-GLO/648F	
Date of Testing- 31-01-2023	
Date of Reporting-31-01-2023	
Die no:- GNT 002	
Invoice No:-	1188
Date:-	10-02-2023

Sample Identification -	Alluminium Sections
Matrix	Al_Low Alloys
Test Required -	Chemical Composition By Optical Emission Spectrometer
Test Method -	As per IS 733-1983
Special Requirements -	Actual Hardness:-67 BHN
Material Specifications -	Alloy 6063-T6

RESULT OF ANALYSIS

Sr No	Elements	Burn 1	Burn 2	Specifications		Observed (Mean)
				Min	Max	
1	Si (%)	0.4956	0.4991	0.20	0.60	0.4974
2	Fe (%)	0.3249	0.3272	-	0.35	0.3261
3	Cu (%)	0.0325	0.0327	-	0.10	0.0326
4	Mg (%)	0.5051	0.5126	0.45	0.90	0.5089
5	Mn (%)	0.0327	0.0324	-	0.10	0.0326
6	Ti (%)	0.0133	0.0137	-	0.10	0.0135
7	Zn (%)	0.0139	0.0084	-	0.10	0.0112
8	Ni (%)	0.0000	0.0000	-	-	0.0000
9	Pb (%)	0.0000	0.0000	-	-	0.0000
10	Sn (%)	0.0276	0.0200	-	-	0.0238
11	Cr (%)	0.0078	0.0072	-	0.10	0.0075
12	Be (%)	0.0000	0.0000	-	-	0.0000
13	Sr (%)	0.0000	0.0000	-	-	0.0000
14	Zr (%)	0.0015	0.0000	-	-	0.0008
15	Ca (%)	0.0056	0.0057	-	-	0.0057
16	V (%)	0.0117	0.0118	-	-	0.0118
17	Al (%)	98.5276	98.5290	-	-	98.5283

NOTE -

1) **All Elements are Reported in Percentage Except where Unit Specified.**
2) **Sample will be disposed after 30 days from the date of material testing.**

GLORIA ALLUMINIUM INDIA PVT. LTD.

Authorized Sign

GLORIA ALLUMINIUM INDIA PVT LTD

Plot No. B-18, Chakan Industrial Area,Phase II,MIDC,Vasuli,Khed,Pune-410501

TEST REPORT

CUSTOMER NAME :- NIHVA TECHNOLOGIES

Test Report No-GLO/648F	
Date of Testing- 31-01-2023	
Date of Reporting-31-01-2023	
Die no:- GNT 006	
Invoice No:-	1188
Date:-	10-02-2023

Sample Identification -	Alluminium Sections
Matrix	Al_Low Alloys
Test Required -	Chemical Composition By Optical Emission Spectrometer
Test Method -	As per IS 733-1983
Special Requirements -	Actual Hardness:-67 BHN
Material Specifications -	Alloy 6063-T4

RESULT OF ANALYSIS

Sr No	Elements	Burn 1	Burn 2	Specifications		Observed (Mean)
				Min	Max	
1	Si (%)	0.4956	0.4991	0.20	0.60	0.4974
2	Fe (%)	0.3249	0.3272	-	0.35	0.3261
3	Cu (%)	0.0325	0.0327	-	0.10	0.0326
4	Mg (%)	0.5051	0.5126	0.45	0.90	0.5089
5	Mn (%)	0.0327	0.0324	-	0.10	0.0326
6	Ti (%)	0.0133	0.0137	-	0.10	0.0135
7	Zn (%)	0.0139	0.0084	-	0.10	0.0112
8	Ni (%)	0.0000	0.0000	-	-	0.0000
9	Pb (%)	0.0000	0.0000	-	-	0.0000
10	Sn (%)	0.0276	0.0200	-	-	0.0238
11	Cr (%)	0.0078	0.0072	-	0.10	0.0075
12	Be (%)	0.0000	0.0000	-	-	0.0000
13	Sr (%)	0.0000	0.0000	-	-	0.0000
14	Zr (%)	0.0015	0.0000	-	-	0.0008
15	Ca (%)	0.0056	0.0057	-	-	0.0057
16	V (%)	0.0117	0.0118	-	-	0.0118
17	Al (%)	98.5276	98.5290	-	-	98.5283

NOTE -

1) **All Elements are Reported in Percentage Except where Unit Specified.**
2) **Sample will be disposed after 30 days from the date of material testing.**

GLORIA ALLUMINIUM INDIA PVT. LTD.

Authorized Sign

GLORIA ALLUMINIUM INDIA PVT LTD

Plot No. B-18, Chakan Industrial Area,Phase II,MIDC,Vasuli,Khed,Pune-410501

TEST REPORT

CUSTOMER NAME :- NIHVA TECHNOLOGIES

Test Report No-GLO/630F
Date of Testing- 31-01-2023
Date of Reporting-31-01-2023
Die no:- GNT 007

Invoice No:- 1188
Date:- 10-02-2023

Sample Identification -	Alluminium Sections
Matrix	Al_Low Alloys
Test Required -	Chemical Composition By Optical Emission Spectrometer
Test Method -	As per IS 733-1983
Special Requirements -	Actual Hardness:-67 BHN
Material Specifications -	Alloy 6063-T6

RESULT OF ANALYSIS

Sr No	Elements	Burn 1	Burn 2	Specifications		Observed (Mean)
				Min	Max	
1	Si (%)	0.4956	0.4991	0.20	0.60	0.4974
2	Fe (%)	0.3249	0.3272	-	0.35	0.3261
3	Cu (%)	0.0325	0.0327	-	0.10	0.0326
4	Mg (%)	0.5051	0.5126	0.45	0.90	0.5089
5	Mn (%)	0.0327	0.0324	-	0.10	0.0326
6	Ti (%)	0.0133	0.0137	-	0.10	0.0135
7	Zn (%)	0.0139	0.0084	-	0.10	0.0112
8	Ni (%)	0.0000	0.0000	-	-	0.0000
9	Pb (%)	0.0000	0.0000	-	-	0.0000
10	Sn (%)	0.0276	0.0200	-	-	0.0238
11	Cr (%)	0.0078	0.0072	-	0.10	0.0075
12	Be (%)	0.0000	0.0000	-	-	0.0000
13	Sr (%)	0.0000	0.0000	-	-	0.0000
14	Zr (%)	0.0015	0.0000	-	-	0.0008
15	Ca (%)	0.0056	0.0057	-	-	0.0057
16	V (%)	0.0117	0.0118	-	-	0.0118
17	Al (%)	98.5276	98.5290	-	-	98.5283

NOTE -

1) **All Elements are Reported in Percentage Except where Unit Specified.**
2) **Sample will be disposed after 30 days from the date of material testing.**

GLORIA ALLUMINIUM PVT. LTD. PUNE

Authorized Sign

Gloria Alluminium India Pvt Ltd

Plot no-B/18,Chakan Industrial Area,Phase II,MIDC,Vasuli Khed,Pune

Alloy:- 6082 - T6

PART NO:- GNT-007	Pre-Dispatch Inspetion Report	Rev:-
CUSTOMER NAME:- NRHVA		DATE:- 31/01/2023
Operation Disc.:-Extrusion		CASTING NO: 630

SR.NO.	PARAMETER	SPECIFICATION	INSPECTION METHOD	INPROCESS INSPECTION					REMARK
				1	2	3	4	5	
1	Dim	99.0 ± 1.00	Vc	99.17	99.20	99.22	99.19	99.16	OK
2	〃	63.3 ± 0.20	VC	63.22	63.16	63.19	63.25	63.24	OK
3	〃	46.5 ± 0.20	VC	46.61	46.60	46.70	46.65	46.68	OK
4		21.00	〃	20.92	20.94	20.91	20.93	20.95	OK
5	THK	2.5 ± 0.20	〃	2.23	2.31	2.29	2.28	2.25	OK
6	〃	2.6	〃	2.35	2.25	2.30	2.34	2.37	OK

Note: We are consider tolerance ±0.20mm and all dimensions are in mm.

Accepted/Rejected


Inspected By: Akash singh AKS

Verified By: Ajeet singh AJS

GLORIA ALLUMINIUM INDIA PVT. LTD. PUNE

PRODUCED BY AN AUTODESK EDUCATIONAL PRODUCT

Die No. GNT007

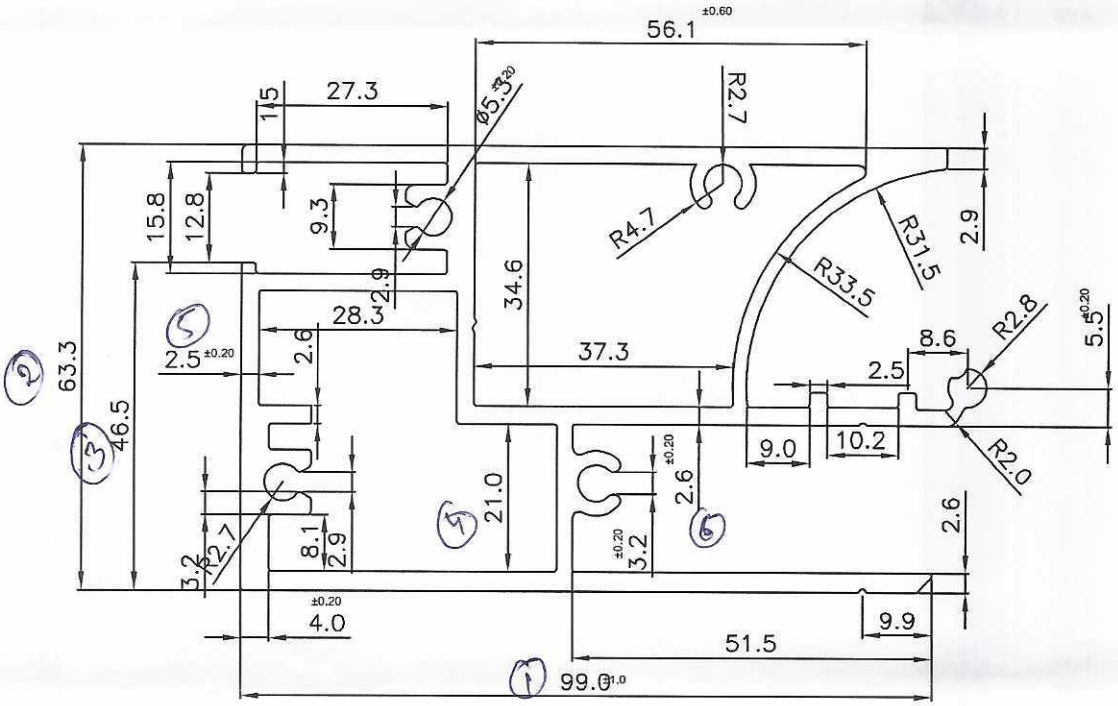

Scale - 1:1

Note :-

01) All dim. are in mm

02) Twist & Bend :- 1.5mm/mtr.

03) Flatness :- 0.5 Concave or convex/ mtr.

04) Angularity tolerance : - ±1°

05) Critical dimension :- * Marks

Container OD mm		Die OD- mm		Area- mm 2	1330.53	Drawn By	
Die Plate- mm		Bolster No		Perimeter- mm	1002.60	Chkd By	
Mandrel - mm		Backer No.		Weight/Mt.-Kg.	3.59-3.60	Date	19.07.19
Backer- mm		Cavity No.		Aluminium Alloy	6060-T6	App. Date	
Pocket Deep		Ext.Ratio		Unspecified Tol.	±0.20	Rev.no.	
GLORIA ALLUMINIUM INDIA PVT. LTD. CHAKAN , PUNE				Party:- Nihva Technologies india pvt ltd		Ref:-Drg no. GNT007	

PRODUCED BY AN AUTODESK EDUCATIONAL PRODUCT

Gloria Alluminium India Pvt Ltd

Plot no-B/18,Chakan Industrial Area,Phase II,MIDC,Vasuli Khed,Pune

Alloy:- 6063-T4

PART NO:- GNT-026

CUSTOMER NAME:- NIKHVA

Operation Disc.:-Extrusion

Pre-Dispatch Inspetion Report

Rev:-

DATE:- 31/01/2023

CASTING NO:N648F

SR.NO.	PARAMETER	SPECIFICATION	INSPECTION METHOD	INPROCESS INSPECTION					REMARK
				1	2	3	4	5	
1	Dim	60.0±0.60	Vc	60.01	59.99	60.00	60.04	60.05	OK
2	"	63.0	"	63.03	63.00	63.04	63.07	63.06	"
3	"	47.5	"	47.46	47.51	47.47	47.52	47.50	"
4	"	20+0.20	"	20.19	20.15	20.14	20.18	20.20	"
5	THK	3.00	"	3.06	3.08	3.10	3.12	3.11	"
6	"	2.0+0.20	"	1.97	2.04	1.96	1.94	1.95	"

Note: We are consider tolerance ±0.20mm and all dimensions are in mm.

Accepted/Rejected


Inspected By: Akash singh

Verified By: Arpit singh

GLORIA ALLUMINIUM INDIA PVT. LTD. PUNE

PRODUCED BY AN AUTODESK EDUCATIONAL PRODUCT

Die No. GNT006

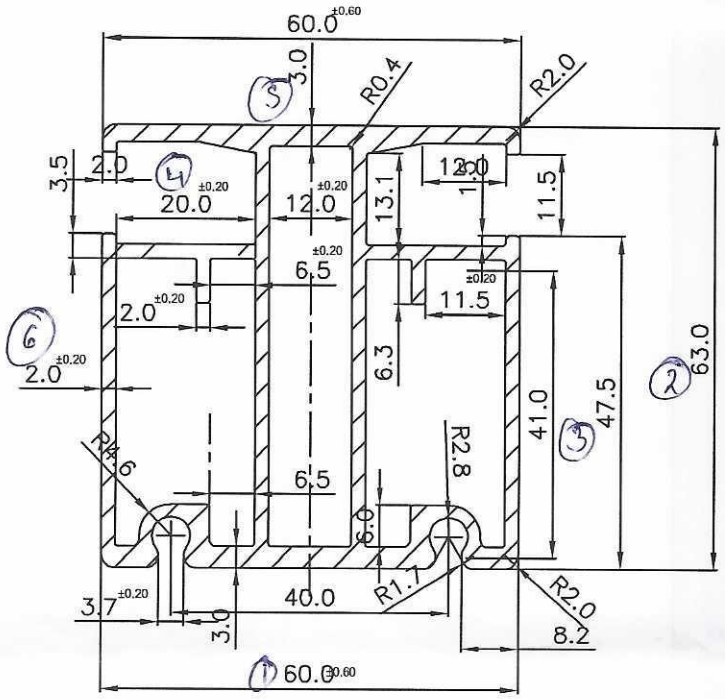

Scale - 1:1

Note :-

01) All dim. are in mm

02) Twist & Bend :- 1.5mm/mtr.

03) Flatness :- 0.5 Concave or convex/ mtr.

04) Angularity tolerance : - ±1°

05) Critical dimension :- * Marks

Container OD mm		Die OD- mm		Area- mm 2	882.22	Drawn By	
Die Plate- mm		Bolster No		Perimeter- mm	761.53	Chkd By	
Mandrel - mm		Backer No.		Weight/Mt.-Kg.	2.38-2.50	Date	19.07.19
Backer- mm		Cavity No.		Aluminium Alloy	6060-T6	App. Date	
Pocket Deep		Ext.Ratio		Unspecified Tol.	±0.20	Rev.no.	
GLORIA ALLUMINIUM INDIA PVT. LTD. CHAKAN , PUNE			Party:- Nihva Technologies india pvt ltd		Ref:-Drg no. GNT006		

PRODUCED BY AN AUTODESK EDUCATIONAL PRODUCT

Gloria Alluminium India Pvt Ltd

Plot no-B/18,Chakan Industrial Area,Phase II,MIDC,Vasuli Khed,Pune

Alloy:- 6063 - T6

PART NO:- GNT-502

CUSTOMER NAME:- NZHVA

Operation Disc.:-Extrusion

Pre-Dispatch Inspetion Report

Rev:-

DATE:- 31/01/2023

CASTING NO: 648

SR.NO.	PARAMETER	SPECIFICATION	INSPECTION METHOD	INPROCESS INSPECTION					REMARK
				1	2	3	4	5	
1	Dim	134.00	Vc	134.02	133.98	134.04	134.00	133.99	OK
2	"	94.5±0.90	"	94.60	94.62	94.69	94.63	94.70	"
3	"	12.8	"	12.65	12.64	12.66	12.63	12.67	"
4	"	45.00	"	45.02	45.01	45.03	45.05	45.03	"
5	"	14.4	"	14.28	14.29	14.25	14.26	14.29	"
6	THK	2.0	"	1.98	1.96	2.00	2.01	2.02	"
7	"	1.9	"	1.89	1.86	1.92	1.92	1.93	"

Note: We are consider tolerance ±0.20mm and all dimensions are in mm.

Accepted/Rejected


Inspected By: Alkesh Singh — AKS

Verified By: Ajeet Singh AKS

GLORIA ALLUMINIUM INDIA PVT. LTD. PUNE

PRODUCED BY AN AUTODESK EDUCATIONAL PRODUCT

Die No. GNT002

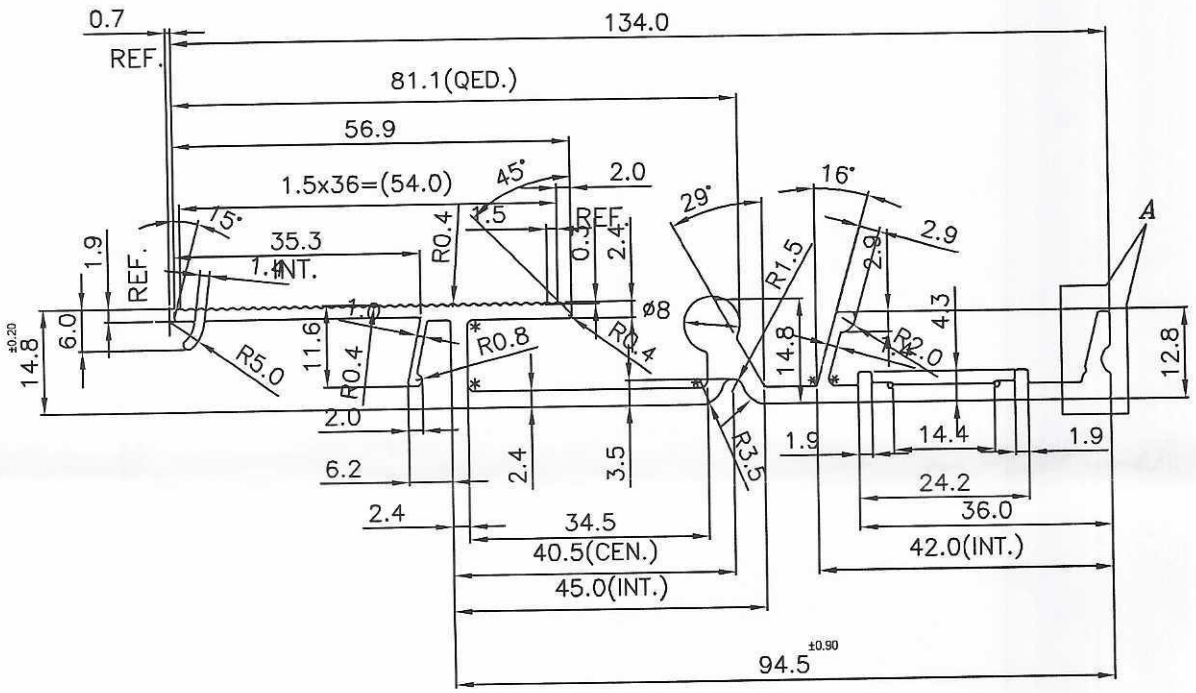

Scale - 1:1

Note :-

01) All dim. are in mm

02) Twist & Bend :- 1.5mm/mtr.

03) Flatness :- 0.5 Concave or convex/ mtr.

04) Angularity tolerance : - ±1°

05) Critical dimension :- * Marks

* = 1.0 RADIUS

Container OD mm		Die OD- mm		Area- mm 2	489.94	Drawn By	
Die Plate- mm		Bolster No		Perimeter- mm		Chkd By	
Mandrel - mm		Backer No.		Weight/Mt.-Kg.	1.30-1.20	Date	06.07.19
Backer- mm		Cavity No.		Aluminium Alloy	6060-T6	App. Date	
Pocket Deep		Ext.Ratio		Unspecified Tol.	±0.20	Rev.no.	
GLORIA ALLUMINIUM INDIA PVT. LTD. CHAKAN , PUNE				Party:- Nihva Technologies india pvt ltd		Ref:-Drg no. GNT002	

PRODUCED BY AN AUTODESK EDUCATIONAL PRODUCT

PRODUCED BY AN AUTODESK EDUCATIONAL PRODUCT

PRODUCED BY AN AUTODESK EDUCATIONAL PRODUCT

GLORIA ALLUMINIUM INDIA PVT.LTD									
PACKING SLIP									
CUSTOMER NAME :- NIHVA TECHNOLOGIES									10.02.23
SR.NO	SECTION NAME	DESCRIPTION	CUT LENGTH	WEIGHT	SERIAL NO.	PIECES	TOTAL WEIGHT	TOTAL PIECES	WEIGHT RANGE (PER PIECE)
1	GNT 007		2500 MM	18.36		2	273.34	30	9.180
2				36.42		4			9.105
3				36.4		4			9.100
4				36.36		4			9.090
5				36.44		4			9.110
6				36.48		4			9.120
7				36.44		4			9.110
8				36.44		4			9.110
9	GNT 002		6000 MM	47.38		6	259.58	33	7.897
10				47.36		6			7.893
11				46.92		6			7.820
12				46.84		6			7.807
13				24.1		3			8.033
14				46.98		6			7.830
15	GNT 006		6500 MM	31.18		2	1058.76	68	15.590
16				46.64		3			15.547
17				46.52		3			15.507
18				46.54		3			15.513
19				46.52		3			15.507
20				46.44		3			15.480
21				46.48		3			15.493
22				46.72		3			15.573
23				46.6		3			15.533
24				46.66		3			15.553
25				46.74		3			15.580
26				46.78		3			15.593
27				46.76		3			15.587
28				46.74		3			15.580
29				46.58		3			15.527
30				46.9		3			15.633
31				46.72		3			15.573
32				46.94		3			15.647
33				46.96		3			15.653
34				46.86		3			15.620
35				46.84		3			15.613
36				46.82		3			15.607
37				46.82		3			15.607
38	GNT 006		5000 MM	36.1		3	131.74	11	12.033
39				36.12		3			12.040
40				59.52		5			11.904
41	GNT 006		6000 MM	43.34		3	43.34	3	14.447
			TOTAL	1766.76		145	1766.76	145	
	TOTAL BUNDLE			41					