

HBS formation as a second-order phase transition

A Landau functional for SCIANTIX

E. Cappellari

September 10, 2026

SCIANTIX status

The model

Results

Model applied to SCIANTIX

SCIANTIX status

SCIANTIX had three formation models for the restructured volume fraction

option	form	driven by
1	KJMA, Barani (2020) ¹	effective burnup
2	KJMA + $bu_{inc} = 15$, Biswas and Aagesen (2025) ²	effective burnup
3	KJMA on ρ_d , Veshchunov ³ + Zullo (2026)	local burnup

All three are **transformation kinetics**: a sigmoid fitted in burnup. None of them produces the **mean misorientation** Θ of the subgrains, or the **subgrain radius** r_n .

¹ Barani et al., *J. Nucl. Mater.* 539 (2020) 152296.

² Biswas and Aagesen, *Comput. Mater. Sci.* 258 (2025) 114052, Eq. 45.

³ Veshchunov and Shestak, *J. Nucl. Mater.* 384 (2009) 12–18.

The data this model is built on

EBSD — Zacharie-Aubrun *et al.* (2022), Onofri *et al.* (2025). 42 radial positions on 7 rods, with TRANSURANUS local conditions.

quantity	N	what it is
mean misorientation Θ	41	$[A_{\text{Mis}}(f_1 - f_{10}) + 10f_{10}]/100$
restructured fraction X	27	f_{10} , area fraction above 10°
subgrain radius r_n	14	ECD50 % /2

1° is the lower bin edge of the dataset.

What KJMA is, and what it assumes

Nuclei appear *at random* in the untransformed material and grow *isotropically*; count the transformed volume as if the growing regions could overlap freely, the **extended volume** V_e , and the overlap correction is statistical:

$$dX = (1 - X) \frac{dV_e}{V} \implies X = 1 - \exp(-K t^n)$$

What you get

K and n , and a sigmoid. n carries the dimensionality of growth and the nucleation regime.

What it assumes

Randomly placed nuclei, a growth law independent of where you are in the transformation, and a *time dependence*.

The time dependence in the KJMA model

- 1 **Effective burnup**, $n = 3.54$, $K = 2.77 \times 10^{-7}$, fitted on restructured-fraction data.
- 2 Same, with an **incubation burnup** $bu_{inc} = 15 \text{ MWd/kgHM}$ below which nothing happens. Biswas & Aagesen get it from a balance between the energy stored in dislocations and the energy of forming a subgrain used to shift the origin of an empirical curve rather than to build the curve.
- 3 KJMA not on burnup but on the **dislocation density** $\rho_d(bu, T)$, with a threshold $\rho_{crit} = 6 \times 10^{14} \text{ m}^{-2}$. The first to make the driver a **microstructural state variable** and the only one that feels temperature.

What none of them can do

They are calibrated on X alone. There is no misorientation angle neither subgrain size.

Why a phase transition could be the right shape for this problem

The HBS forms *continuously*

Not by nucleating new grains, but by low-angle boundaries absorbing dislocations until their misorientation drifts through the 10° HAGB threshold. In the metallurgical literature this is *continuous* dynamic recrystallization, and it is a well-posed alternative to the nucleation-and-growth picture KJMA describes.⁵

A continuous transformation has an order parameter

If a single continuous quantity distinguishes the two states, Landau's argument applies: expand the free energy in it, and keep only the terms symmetry allows.⁶

$$F(\eta) = C_0 + C_2\eta^2 + C_4\eta^4$$

Odd powers are forbidden here since the energy of a boundary cannot depend on the *sign* of the misorientation across it.

C_2 changing sign produces the transition between a null order parameter and a non-zero one, i.e. the development of misorientation.

⁵Gourdet & Montheillet, *Acta Mater.* 51 (2003) 2685; Humphreys & Hatherly (2017), chs. 6 and 10.

⁶Landau (1937); Landau & Lifshitz, *Statistical Physics I*, §143.

Landau against KJMA, side by side

	KJMA (options 1–3)	Landau (option 4)
what is solved	a <i>kinetic</i> law along a path	the <i>equilibrium</i> of a state
driver	burnup or ρ threshold	$\rho(bu)$ through C_2
free parameters	K , n fitted on X	β , k , ρ_c fitted on Θ , r_n
predicts X	by construction	yes
predicts Θ , r_n	no	yes
reversible?	no, monotone by construction	yes — see below

The price of using an equilibrium theory

A drop in ρ_{tot} would un-restructure the fuel. Restructuring is irreversible, so the implementation carries a **monotonic lock** on Θ . However, this is easy if one considers the dislocation density generated by irradiation, and eventually includes the annealing phenomena within the evolution of the Landau free energy.

The model

HBS as a second-order phase transition

Order parameter

$$\eta = \frac{\theta}{\theta_{\max}}, \quad \theta_{\max} \equiv \theta_{\text{HAGB}} = 10^\circ$$

the mean misorientation normalised to the LAGB/HAGB boundary.

External condition: the local burnup, entering *only* through the dislocation density

$$\rho_{\text{tot}}(bu) = 10^{2.2 \times 10^{-2} bu + 13.8}$$

Nogita & Une (1994)

Free energy

$$F(bu, \eta) = C_0 + C_2 \eta^2 + C_4 \eta^4$$

Only even powers: the energy cannot depend on the *sign* of a misorientation.

Minimising F gives Θ ; the same wall geometry gives r_n ; the lever rule gives X .

Three adjustable parameters

β (wall geometry), k (sweeping), ρ_c (strain-field cut-off).

The geometric wall

A low-angle boundary *is* a wall of dislocations.

1. Spacing sets the angle $\theta = b/d$

so a wall of n dislocation families carries a line length per unit *wall area*

$$L_A = n\theta/b$$

2. Wall area per unit volume or low angle grain boundary surface

$$S/V = 3\sqrt{\rho_{\text{LAGB}}} / \beta$$

β : the one geometric parameter (Rest & Hofman 2000).
 $n = 2$, Gourdet & Montheillet, not fitted (between 1-3).

Close the two on each other:

$$\rho_{\text{LAGB}} = L_A \cdot S/V$$

$$\Rightarrow \sqrt{\rho_{\text{LAGB}}} = \frac{3n\theta}{\beta b}$$

Everything follows from θ alone

$$\rho_{\text{LAGB}} = \left(\frac{3n\theta}{\beta b} \right)^2, \quad r_n \simeq \frac{\beta^2 b}{6n\theta}$$

The dislocation balance

Every dislocation is in exactly one of three states, and they must add up to ρ_{tot} :

$$\underbrace{\rho_{\text{ord}} = \rho_{\text{LAGB}}^{\text{max}} \eta^2}_{\text{condensed into low-angle walls}} + \underbrace{\rho_{\text{swept}} = (\rho_{\text{tot}} - \rho_{\text{ord}}) \frac{\Delta R}{R}}_{\text{annihilated by moving boundaries}} + \underbrace{\rho_{\text{free}}}_{\text{still a random array}} = \rho_{\text{tot}}$$

Each population carries the line energy of the state it is in:

$$F = \rho_{\text{free}} A_1 G b^2 + \rho_{\text{ord}} A_2 G b^2, \quad A_i = \frac{f(\nu)}{4\pi} \ln \frac{R_i}{b}$$

free ones screened at ρ_c , wall ones by the wall itself at ρ_{tot} ; the swept ones carry nothing.

The functional, collected

$$C_0 = \rho_{\text{tot}} A_1 G b^2, \quad C_4 = \rho_{\text{LAGB}}^{\max} \left. \frac{\Delta R}{R} \right|_{\max} A_1 G b^2$$

$$C_2 = \underbrace{\rho_{\text{LAGB}}^{\max} (A_2 - A_1) G b^2}_{\text{walls: the screening gain}} - \underbrace{\rho_{\text{tot}} \left. \frac{\Delta R}{R} \right|_{\max} A_1 G b^2}_{\text{sweep}}$$

The engine of the transition is $A_2 - A_1$. As burnup rises, ρ_{tot} rises, the screening length due to wall formation shrinks, A_2 falls below A_1 , and it becomes cheaper to store dislocations in walls than to leave them random.

Equilibrium

$$\frac{\partial F}{\partial \eta} = 0 \implies \eta^2 = -\frac{C_2}{2C_4}, \quad \text{clipped at 0}$$

$$\eta = 0 \text{ wherever } C_2 \geq 0.$$

Condition on the minimisation problem: dislocation balance

The walls cannot hold more dislocations than exist, so $\rho_{\text{ord}} \leq \rho_{\text{tot}}$. The equilibrium is the minimum of F on the **admissible interval**, not the free stationary point:

Eq. (7b) — admissibility

$$\eta_{\text{bal}} = \sqrt{\min\left(\frac{\rho_{\text{tot}}}{\rho_{\text{LAGB}}^{\text{max}}}, 1\right)}, \quad \eta_{\text{eq}} = \min\left(\sqrt{-\frac{C_2}{2C_4}}, \eta_{\text{bal}}\right)$$

Results

Calibration

Joint fit of β, k, ρ_c on Θ and the subgrain sizes, while the restructured fraction is *not* in the objective.


$$J = \frac{\langle \Delta \Theta^2 \rangle}{\text{var } \Theta} + w \frac{\langle \Delta r^2 \rangle}{\text{var } r}$$

n (not fitted)	2
β	33.547
k	0.04697
ρ_c	1.166e15 m ⁻²

The calibration results are summarized in the table below.

	RMSE / R^2
Θ ($N = 41$, calibrated)	1.7616° / 0.772
X ($N = 27$, <i>not</i> fitted)	0.2122 / 0.710
r_n ($N = 14$, calibrated)	0.0678 μm / 0.774
PIE fraction ($N = 8$, <i>out-of-sample</i>)	0.1461 / +0.433

Validation against both datasets

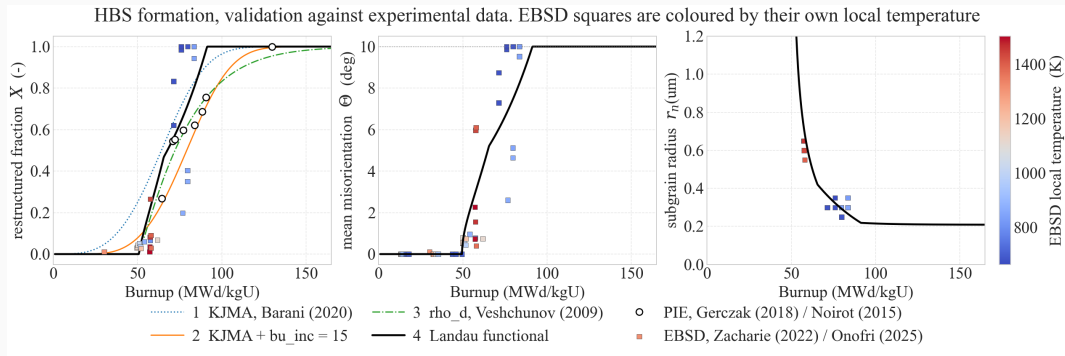

Against the three models SCIANTIX already had


Burnup [MWd/kgU] at which α_r first reaches:

threshold	1 KJMA	2 KJMA+ bu_{inc}	3 ρ_d	4 Landau
1 %	19.5	34.5	51.2	51.1
10 %	37.8	52.8	54.8	53.5
50 %	64.2	79.3	72.3	67.7
90 %	90.1	105.2	112.3	87.7
99 %	109.7	124.6	161.7	91.1

- At the onset, option 4 lands **within 0.1 MWd/kgU of option 3**.
- They part at the top: the lever rule **saturates** when Θ hits the 10° cap, whereas KJMA approaches 1 asymptotically. Option 4 is done by 91 MWd/kgU, option 3 not before 162.
- Option 4 spans the transition in **40 MWd/kgU** against 90 for option 1.

Model applied to SCIANTIX

Does the new formation model disturb the porosity model?

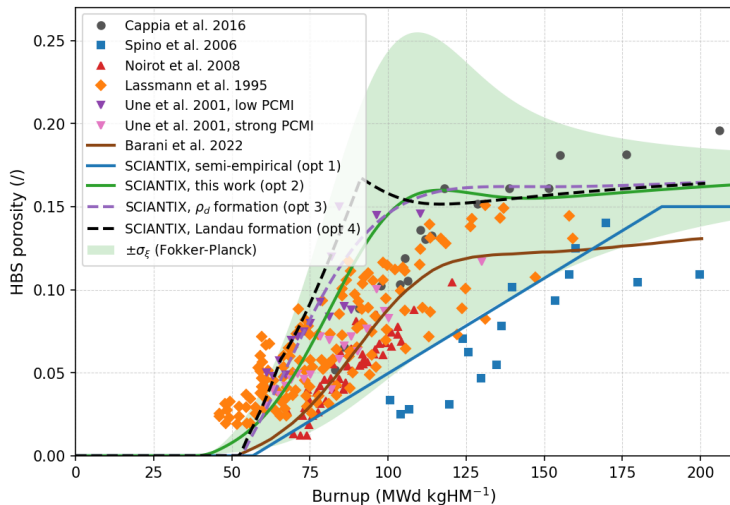

Largest deviation **+0.044**
absolute at
91.3 MWd/kgHM
(+36 %), exactly the
saturation burnup. Held

against option 2 in
test_U02HBS; all four
options end within **0.17 %**
of the same porosity.

Summary

- [1] L.D. Landau, *On the theory of phase transitions*, Zh. Eksp. Teor. Fiz. **7** (1937) 19; L.D. Landau, E.M. Lifshitz, *Statistical Physics*, Part 1, 3rd ed., §143.
- [2] A.N. Kolmogorov, Izv. Akad. Nauk SSSR, Ser. Mat. **1** (1937) 355–359.
- [3] W.A. Johnson, R.F. Mehl, Trans. AIME **135** (1939) 416–442.
- [4] M. Avrami, *J. Chem. Phys.* **7** (1939) 1103–1112; **8** (1940) 212–224; **9** (1941) 177–184.
- [5] J.W. Christian, *The Theory of Transformations in Metals and Alloys*, Part I, 3rd ed., Pergamon (2002), ch. 12, *Formal Theory of Transformation Kinetics*.
- [6] F.J. Humphreys, *A unified theory of recovery, recrystallization and grain growth, based on the stability and growth of cellular microstructures — I. The basic model*, *Acta Mater.* **45** (1997) 4231–4240.

- [7] F.J. Humphreys, G.S. Rohrer, A.D. Rollett, *Recrystallization and Related Annealing Phenomena*, 3rd ed., Elsevier (2017), ch. 6 (recovery) and ch. 10 (growth and stability of cellular microstructures).
- [8] S. Gourdet, F. Montheillet, *A model of continuous dynamic recrystallization*, *Acta Mater.* **51** (2003) 2685–2699. *n*, and the sweeping term
- [9] W.T. Read, W. Shockley, *Dislocation models of crystal grain boundaries*, *Phys. Rev.* **78** (1950) 275–289. $\theta = b/d$, and the wall energy
- [10] J.F. Nye, *Some geometrical relations in dislocated crystals*, *Acta Metall.* **1** (1953) 153–162.
- [11] G.S. Rohrer, *Grain boundary energy anisotropy: a review*, *J. Mater. Sci.* **46** (2011) 5881–5895.

- [12] J. Rest, G.L. Hofman, *An alternative explanation for evidence that xenon depletion, pore formation and grain subdivision begin at different local burnups*, *J. Nucl. Mater.* **277** (2000) 231–238. *the analogue of β*
- [13] M. Muramatsu, Y. Aoyagi, Y. Tadano, K. Shizawa, *Phase-field simulation of static recrystallization considering nucleation from subgrains and nucleus growth with incubation period*, *Comput. Mater. Sci.* **87** (2014) 112–122.
- [14] T. Barani *et al.*, *Modeling high burnup structure in oxide fuels. . . Part I: HBS formation*, *J. Nucl. Mater.* **539** (2020) 152296. *option 1*
- [15] T. Barani *et al.*, . . . *Part II: Porosity evolution*, *J. Nucl. Mater.* **563** (2022) 153627. *porosity options 2–3*
- [16] S. Biswas, L.K. Aagesen, *Comput. Mater. Sci.* **258** (2025) 114052, Eq. 45. *option 2, bu_{inc}*

- [17] M.S. Veshchunov, V.E. Shestak, *Model for evolution of crystal defects in UO_2 under irradiation up to high burn-ups*, *J. Nucl. Mater.* **384** (2009) 12–18. *option 3, $\rho_d(\text{bu}, T)$*
- [18] G. Khvostov *et al.*, *Approaches to modeling of high burn-up structure... in the START-3 code*, WRFPM-2005, Kyoto.
- [19] K. Nogita, K. Une, *Radiation-induced microstructural change in high burnup UO_2 fuel pellets*, *Nucl. Instrum. Methods B* **91** (1994) 301–306. *Eq. (1), $\rho_{\text{tot}}(\text{bu})$*
- [20] K. Nogita, K. Une, *Irradiation-induced recrystallization in high burnup UO_2 fuel*, *J. Nucl. Mater.* **226** (1995) 302–310.
- [21] Hj. Matzke, M. Kinoshita, *Polygonization and high burnup structure in nuclear fuels*, *J. Nucl. Mater.* **247** (1997) 108–115.
- [22] J. Spino *et al.*, *J. Nucl. Mater.* **354** (2006) 66–84. *porosity option 1, and the swelling data*

- [23] I. Zacharie-Aubrun *et al.*, *Restructuring in high burn-up UO_2 fuels: experimental characterization by electron backscattered diffraction*, *J. Appl. Phys.* **132** (2022) 195903. *28 of the 42 EBSD points*
- [24] C. Onofri *et al.*, *Experimental characterizations by EBSD and TEM of sub-grain boundaries and dislocations in low irradiated UO_2 fuels*, *J. Nucl. Mater.* **615** (2025) 155981. *the other 14*
- [25] NEA, *Recommendations on nuclear fuel properties*, NEA/NSC/R(2024)1 (2025), p. 124. *Eq. (2), G and ν*
- [26] D. Pizzocri *et al.*, *SCIANTIX: a new open source multi-scale code for fission gas behaviour modelling*, *J. Nucl. Mater.* **532** (2020) 152042.
- [27] G. Zullo *et al.*, *The SCIANTIX code for fission gas behaviour: status, upgrades, separate-effect validation and future developments*, *J. Nucl. Mater.* **587** (2023) 154744.

Backup — the equations

$$(1) \quad \rho_{\text{tot}}(bu) = 10^{2.2 \times 10^{-2} bu + 13.8}$$

$$(2) \quad G(T, P, x, q), \quad \nu(T, P, x, q) \quad \text{NEA/NSC/R(2024)1 p. 124;} \quad f(\nu) = \frac{1-\nu/2}{1-\nu}$$

$$(3) \quad \rho_{\text{LAGB}}^{\text{max}} = \left(\frac{3n\theta_{\text{max}}}{\beta b} \right)^2, \quad (S/V)_{\text{max}} = \frac{9n\theta_{\text{max}}}{\beta^2 b}, \quad \left. \frac{\Delta R}{R} \right|_{\text{max}} = \frac{k \rho_{\text{LAGB}}^{\text{max}}}{\rho_{\text{tot}}}$$

$$(4) \quad A_1 = \frac{f(\nu)}{4\pi} \ln \frac{\rho_{\text{c}}^{-1/2}}{b}, \quad A_2 = \frac{f(\nu)}{4\pi} \ln \frac{\rho_{\text{tot}}^{-1/2}}{b}$$

$$(5,6) \quad F = \rho_{\text{free}} A_1 G b^2 + \rho_{\text{ord}} A_2 G b^2 = C_0 + C_2 \eta^2 + C_4 \eta^4$$

$$(7,7b) \quad \eta_{\text{eq}} = \min(\sqrt{-C_2/2C_4}, \eta_{\text{bal}}), \quad \eta_{\text{bal}} = \sqrt{\min(\rho_{\text{tot}}/\rho_{\text{LAGB}}^{\text{max}}, 1)}$$

$$(8) \quad \Theta = \min(\eta_{\text{eq}} \theta_{\text{max}} \cdot \frac{180}{\pi}, \theta_{\text{HAGB}})$$

$$(9) \quad r_n = \min\left(\frac{1.5}{(S/V)}\left(1 + \frac{\Delta R}{R}\right), R_{\text{grain}}\right)$$

$$(10) \quad X = \text{clip}\left(\frac{\Theta - \theta_u}{\theta_{\text{HAGB}} - \theta_u}, 0, 1 - 10^{-9}\right)$$

Backup — regimes and parameters

Regimes (T -, P -, x -independent)	
condition	bu [GWd/tU]
$C_2 = 0$, Θ leaves 0	49.56
$\Theta = \theta_u$, X leaves 0	50.81
$\Theta = \theta_{\text{HAGB}}$	91.32


The balance bound sets η over roughly **65.6–91.3 GWd/tU**, and at 11 of the 41 EBSD points.

Fixed constants

b	3.889e-10 m
θ_{max}	$= \theta_{\text{HAGB}}$
θ_{HAGB}	10°
θ_u	1.00°
n	2


θ_u is the lower end member of the mixture Eq. (10) inverts, and it is set by the **measurement convention**, not fitted: the EBSD data reports a restructured fraction *at* 1° (f_1) and one *at* 10° (f_{10}), so 1° is the edge below which a boundary is not counted at all. A map whose whole resolved population sits there carries no restructuring — which is $X = 0$. It fixes only *where* X leaves zero: Θ and r_n do not depend on it.

Backup — the model on its own, $T = 600$ K, $P = 0.05$

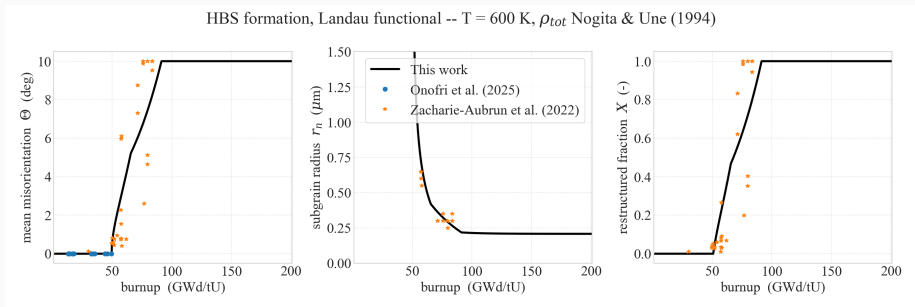

```
python3 hbs_formation_landau.py --plot
```

Backup — the four regression cases, as they ship

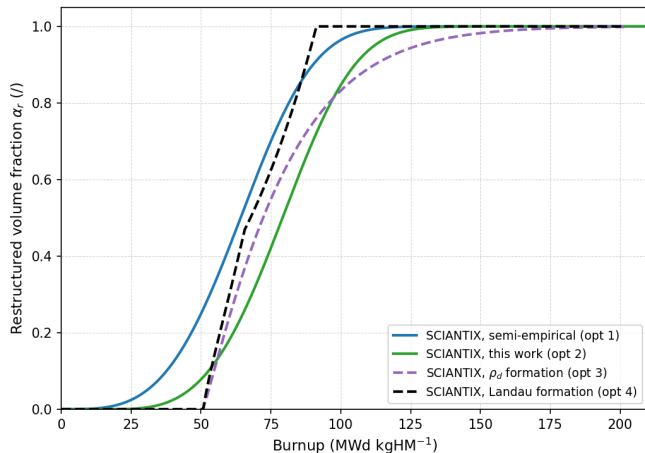

Not the controlled comparison of the previous figure: each case pairs its formation option with the porosity model it was built around (1, 2, 3, 3), so part of the spread is the porosity model.

This is what a user of each regression case actually gets;
`formation_options.png` is what isolates the formation model.

Backup — the four formation options in a full run

HBS formation options on the same irradiation, porosity model 3 throughout

