

Comparative Analysis of Locally Produced Bitumen and Imported Low-Cost Bitumen for Bangladesh Road Construction (Focusing on Aggregate Shape)

by

Md. Rakibul Hasan Mridha
ID: 2020333545

Md Sagor Hossain Saddas
ID: 2020333553

Course Code: CE 800

Bachelor of Science in Civil Engineering

IN


DEPARTMENT OF CIVIL ENGINEERING

Supervised by

Md Johir Bin Alam
Professor
Department of CEE
Shahjalal University of Science & Technology

Co-Supervised by

Mohiuddin Arif
Lecturer
Department of Civil Engineering
Sylhet Engineering College

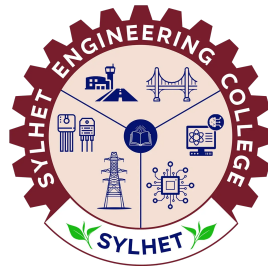

Sylhet Engineering College
(Shahjalal University of Science & Technology)
Sylhet-3100, Bangladesh

August 2026

Candidate's Declaration

This is to certify that the work presented in this thesis entitled, **“Comparative Analysis of Locally Produced Bitumen and Imported Low-Cost Bitumen for Bangladesh Road Construction (Focusing on Aggregate Shape)”**, is the outcome of the research carried out by the authors under the supervision of **Md Johir Bin Alam, Professor, Department of CEE, Shahjalal University of Science & Technology, Bangladesh**, and the co-supervision of **Mohiuddin Arif, Lecturer, Department of Civil Engineering, Sylhet Engineering College, Bangladesh**.

It is also declared that neither this thesis nor any part thereof has been submitted anywhere else for the award of any degree, diploma, or other qualifications.

Signature of the Candidates

Md. Rakibul Hasan Mridha
Reg. No.: 2020333545

Md Sagor Hossain Saddas
Reg. No.: 2020333553

Recommendation Letter from Thesis Supervisor

The thesis entitled “**Comparative Analysis of Locally Produced Bitumen and Imported Low-Cost Bitumen for Bangladesh Road Construction (Focusing on Aggregate Shape)**” submitted by the students:

1. Md. Rakibul Hasan Mridha (Reg. No.: 2020333545)
2. Md Sagor Hossain Saddas (Reg. No.: 2020333553)

is a record of research work carried out under our supervision and we, hereby, approve that the report is submitted in partial fulfilment of the requirement for the award of their Bachelor’s Degree.

Signature of the Supervisor

Md Johir Bin Alam

Professor

Department of CEE

Shahjalal University of Science & Technology

Signature of the Co-Supervisor

Mohiuddin Arif

Lecturer

Department of Civil Engineering

Sylhet Engineering College

Date: _____

Certificate of Acceptance

The thesis titled “**Comparative Analysis of Locally Produced Bitumen and Imported Low-Cost Bitumen for Bangladesh Road Construction (Focusing on Aggregate Shape)**” submitted by Md. Rakibul Hasan Mridha and Md Sagor Hossain Saddas; Student ID: 2020333545 and 2020333553, to the Department of Civil Engineering, Sylhet Engineering College, has been accepted as satisfactory in partial fulfillment of the requirement for the Degree of Bachelor of Science in Civil Engineering and approved as to its style and contents.

BOARD OF EXAMINERS

Sibbir Ahmed Assistant Professor and Head of the Department Department of Civil Engineering Sylhet Engineering College	Chairperson
Tahia Rabbi Assistant Professor Department of Civil Engineering Sylhet Engineering College	Internal Examiner
Mohiuddin Arif Lecturer Department of Civil Engineering Sylhet Engineering College	Internal Examiner
Md. Titumir Hassan Workshop Maintenance Engineer Department of Civil Engineering Sylhet Engineering College	Internal Examiner
Md Johir Bin Alam Professor Department of CEE Shahjalal University of Science & Technology	External Examiner

Acknowledgement

We would like to thank the Department of Civil Engineering, Sylhet Engineering College, Sylhet for supporting this research.

We are very thankful to our honorable supervisor Md Johir Bin Alam and co-supervisor Mohiuddin Arif for their worthy support and directions.

We are also very grateful to the authors and researchers for their previous works which played a very important role in our thesis.

Finally, we must acknowledge with due respect the constant support and patience of our parents.

The Authors

Abstract

Bangladesh's expanding road network relies predominantly on flexible pavements, in which bitumen serves as the principal binding agent. However, quality variations between domestically refined and imported low-cost bitumen, compounded by poorly characterised aggregate shape effects, contribute to premature pavement distress including rutting, stripping, and fatigue cracking. Despite the critical role these factors play, no prior study has systematically compared locally produced bitumen from Eastern Refinery with imported low-cost alternatives while simultaneously evaluating the influence of aggregate particle shape under conditions representative of Bangladesh's subtropical monsoon climate. This study addresses the gap through a laboratory-based comparative analysis employing the Marshall mix design method. Four distinct mixes were investigated: local bitumen with natural aggregates (control), imported bitumen with natural aggregates, local bitumen with 20% cubical aggregate replacement, and imported bitumen with 20% cubical aggregate replacement. Specimens were compacted at 75 blows per face in accordance with Roads and Highways Department heavy-traffic specifications, and evaluated for Marshall stability, flow, and volumetric properties including air voids, voids in mineral aggregate, and voids filled with bitumen. The optimum binder content was determined at 5.0% from the control mix. Preliminary results indicate that the local bitumen combined with 20% cubical aggregate replacement yielded the highest Marshall stability of XX kN, representing an improvement of XX% over the imported bitumen control mix. These findings provide evidence-based guidance for material selection in Bangladesh's road construction sector.

Keywords: bitumen, aggregate shape, Marshall stability, cubical aggregate, Bangladesh, road construction, flexible pavement

Contents

Candidate's Declaration	i
Recommendation Letter from Thesis Supervisor	ii
Certificate of Acceptance	iii
Acknowledgement	iv
Abstract	v
List of Figures	viii
List of Tables	ix
1 Introduction	1
1.1 Background	1
1.2 Problem Statement	1
1.3 Objectives of the Study	2
1.4 Scope and Limitations	2
1.5 Thesis Organisation	3
2 Literature Review	4
2.1 Bitumen Grading and Pavement Performance in Tropical Climates	4
2.2 Aggregate Shape and Its Influence on Mix Design	4
2.3 Subgrade Stabilization and Economic Road Construction	4
2.4 Research Gap	5
3 Methodology	6
3.1 General	6
3.2 Materials	6
3.2.1 Bitumen	6
3.2.2 Aggregates	8
3.2.3 Mineral Filler	8
3.3 Aggregate Gradation and Blending	8
3.4 Aggregate Shape Classification	10
3.5 Mix Design	11
3.5.1 Mix Combinations	11
3.5.2 Specimen Preparation	11
3.5.3 Optimum Binder Content Determination	11
3.6 Testing Programme	12
3.6.1 Marshall Stability and Flow Test	12
3.6.2 Volumetric Analysis	12
3.7 Summary of Test Matrix	12

4	Results and Discussion	13
4.1	Properties of Aggregates	13
4.2	Properties of Bituminous Binders	13
4.3	Determination of Optimum Binder Content	14
4.4	Comparative Analysis of Bituminous Mixtures	16
4.5	Proposed Roadmap for Cost-Effective Road Construction in Bangladesh .	18
5	Conclusion	20
5.1	Summary of Findings	20
5.2	Recommendations for Practice	20
5.3	Future Work	20
	References	22

List of Figures

3.1	Flowchart of the experimental methodology adopted in this study.	7
3.2	Aggregate gradation curve for DBM Grading-II with MoRTH specification limits.	9
3.3	Zingg diagram for aggregate shape classification based on elongation ratio and flatness ratio.	10
4.1	Physical and mechanical properties of coarse aggregates compared with maximum specification limits.	13
4.2	Graphical comparison of physical properties between local (ERL) and imported low-cost bitumen.	14
4.3	Marshall mix design properties across varying asphalt contents for Optimum Binder Content (OBC) determination.	15
4.4	Comprehensive performance assessment of the four bituminous mix variants across key Marshall stability, flow, and volumetric parameters. . . .	17
4.5	Interaction line plots comparing Marshall stability and flow across four bituminous mix variants.	18

List of Tables

3.1	Physical properties of local bitumen (Eastern Refinery, 60/70 grade). . .	6
3.2	Physical properties of imported low-cost bitumen (60/70 grade).	6
3.3	Physical and mechanical properties of coarse aggregates.	8
3.4	Combined aggregate gradation for DBM Grading-II (MoRTH Table 500-10). .	9
3.5	Experimental mix design matrix.	11
3.6	Summary of the experimental test matrix.	12
4.1	Marshall mix design properties for Optimum Binder Content determination. .	15
4.2	Comparative Marshall properties of the four bituminous mix variants eval- uated at 5.0% OBC.	16

1 Introduction

1.1 Background

Bangladesh possesses an extensive road network spanning approximately 375,000 km, of which more than 90% comprises flexible pavements constructed using bituminous materials. The performance and longevity of these pavements are fundamentally governed by the quality of the constituent materials, namely the bituminous binder and the mineral aggregates [7]. Bitumen, a viscoelastic hydrocarbon binder, provides the adhesive and cohesive properties necessary to bind aggregate particles into a durable pavement matrix. In Bangladesh, the Eastern Refinery Limited located in Chittagong serves as the sole domestic producer of bitumen, supplying penetration-grade 60/70 bitumen at a controlled price of approximately Tk 6,300 per unit. However, the domestic supply has historically fallen short of national demand, prompting contractors to source low-cost imported bitumen from international markets.

The Roads and Highways Department (RHD), the principal agency responsible for national highway construction and maintenance, has periodically imposed restrictions on the use of certain imported bitumen grades owing to concerns regarding their inferior quality and premature pavement deterioration [1]. Despite these regulatory interventions, imported low-cost bitumen continues to be employed in numerous road construction projects across the country, driven primarily by short-term economic considerations.

Concurrently, the aggregate component of hot mix asphalt (HMA) constitutes approximately 92 to 96 percent of the total mixture by weight and plays a decisive role in determining the structural performance of the pavement [3]. Among the various aggregate properties, particle shape has been identified as a critical factor influencing the interlocking behaviour, compaction characteristics, and resistance to permanent deformation of bituminous mixes [6]. Cubical aggregates, characterised by roughly equal dimensions along all three axes, have been shown to exhibit superior mechanical interlock and internal friction compared with flaky, elongated, or blade-shaped particles [5]. Notwithstanding the established significance of aggregate shape in pavement engineering, its combined effect with bitumen source quality remains largely unexplored in the context of Bangladesh.

1.2 Problem Statement

The quality disparity between locally refined bitumen from Eastern Refinery and imported low-cost alternatives poses a significant challenge for Bangladesh's road infrastructure. Imported bitumen, frequently characterised by inconsistent penetration grades and inferior rheological properties, has been associated with accelerated pavement distress including rutting in wheel paths, stripping of the binder–aggregate interface under monsoon conditions, and premature fatigue cracking [2]. These distress modes not only compromise structural integrity and ride quality but also impose substantial economic burdens through increased maintenance frequency and reduced pavement service life.

Existing research has addressed bitumen characterisation and aggregate shape effects independently; however, no comprehensive study has integrated these two variables within a single experimental framework tailored to the climatic and traffic conditions prevailing in Bangladesh [4]. The subtropical monsoon climate, characterised by high temperatures exceeding 40°C during summer and prolonged periods of heavy rainfall, subjects

bituminous pavements to severe thermal and moisture-induced stresses that may amplify the performance differences between local and imported binders. A critical gap thus remains in understanding the synergistic effects of bitumen source quality and aggregate particle shape on the Marshall mix design properties and long-term durability of flexible pavements in this region.

1.3 Objectives of the Study

The primary objective of this study is to assess and compare the performance of locally produced bitumen from Eastern Refinery with imported low-cost bitumen for road construction applications in Bangladesh, with particular emphasis on the role of aggregate particle shape. The specific objectives are as follows:

- i. To compare the physical properties (penetration, softening point, ductility, specific gravity, and flash point and fire point) of local and imported 60/70 penetration-grade bitumen.
- ii. To determine the optimum binder content (OBC) using the Marshall method for the control mix with local bitumen.
- iii. To evaluate the effect of cubical aggregate shape (20% replacement of coarse fraction) on the Marshall mix design properties of bituminous mixes.
- iv. To assess the performance of the four mix combinations in terms of Marshall stability, flow, and volumetric properties.
- v. To compare the four bituminous mixes in terms of required pavement thickness, cost effectiveness, and load bearing capacity.
- vi. To provide evidence-based recommendations for material selection in Bangladesh's road construction practice.

1.4 Scope and Limitations

This study is limited to a laboratory-scale investigation employing the Marshall mix design method. The experimental programme utilises 60/70 penetration-grade bitumen from two sources (local Eastern Refinery and imported) and crushed stone aggregates conforming to MoRTH Grading-II for Dense Bituminous Macadam (DBM) with a nominal maximum aggregate size (NMAS) of 19 mm. Four mix combinations are investigated, incorporating natural (as-received) and shape-sorted (20% cubical replacement) aggregates.

The following limitations are acknowledged:

- Aggregates were sourced from a single quarry; results may vary with different geological origins.
- Polymer-modified binders were not included in the scope of this investigation.
- The study is confined to the 19 mm NMAS gradation and does not extend to other layer types such as bituminous concrete (BC) or stone matrix asphalt (SMA).

1.5 Thesis Organisation

The remainder of this thesis is organised as follows. Section 2 presents a review of the existing literature on bitumen characterisation, aggregate shape effects, and Marshall mix design. Section 3 details the experimental methodology, including materials, specimen preparation, and the testing programme. Section 4 presents the experimental results and discusses the findings in the context of prior research. Section 5 summarises the conclusions drawn from this study and provides recommendations for future work.

2 Literature Review

2.1 Bitumen Grading and Pavement Performance in Tropical Climates

The performance of flexible pavements is fundamentally governed by the structural capacity and resilience of the underlying materials, particularly in tropical and subtropical regions facing high traffic volumes and severe climatic variations. Imran et al. [1] developed a comprehensive pavement quality index, emphasizing that rapid traffic growth and temperature fluctuations are the primary catalysts for premature pavement deterioration. Their study highlighted that inadequate quality control during construction often leads to severe distresses such as rutting and thermal cracking, necessitating robust evaluation frameworks. Similarly, Werkinah and Demissie [7] investigated pavement performance failures along the Assosa-Mendi road network, demonstrating that weak sub-surface materials, particularly in the base course and subgrade, directly correlate with the onset of alligator cracking and pothole formation. These findings underscore the necessity of employing high-quality, temperature-resistant bituminous binders and sound granular bases to ensure the longevity of highway infrastructure in challenging environments.

2.2 Aggregate Shape and Its Influence on Mix Design

The morphological characteristics of coarse aggregates—specifically their shape, angularity, and texture—exert a profound influence on the mechanical stability and volumetric properties of hot mix asphalt (HMA). Khairandish and Chopra [2] conducted a comprehensive review indicating that flat and elongated particles tend to fracture under heavy traffic loads, thereby reducing the shear resistance and increasing the rutting susceptibility of bituminous mixes. This was empirically supported by Teja and Krishna [6], who investigated dense bituminous macadam (DBM) mixes containing various proportions of differently shaped aggregates. Their study revealed that replacing conventional aggregates with 20% cubical particles significantly enhanced Marshall stability due to superior aggregate interlock and internal friction, whereas the inclusion of blade-shaped aggregates drastically reduced mix workability and strength. Furthermore, Rajkumar et al. [3] emphasized that a higher percentage of flaky and elongated aggregates invariably leads to an undesirable increase in air voids, compromising the fatigue life of the pavement. Corroborating these findings, Sumanth et al. [5] demonstrated that DBM mixes formulated with cubical aggregates exhibited maximum rutting resistance, conclusively establishing cubical aggregate proportioning as a critical parameter in optimizing flexible pavement design.

2.3 Subgrade Stabilization and Economic Road Construction

In addition to optimizing the surface course, strengthening the pavement foundation is a critical strategy for achieving cost-effective road construction. Sood and Bansal [4] evaluated the techno-economic benefits of utilizing industrial by-products, such as lime and fly ash, for subgrade soil stabilization. Their research demonstrated that treating weak subgrade soils with these additives substantially increases the California Bearing Ratio (CBR) up to an optimal limit. A stronger, stabilized subgrade fundamentally reduces the required thickness of the overlying flexible pavement layers. Consequently,

this approach not only mitigates the environmental impact of industrial waste disposal but also provides a highly economical solution by reducing the total volume of expensive construction materials required for highway projects.

2.4 Research Gap

Despite extensive research on aggregate morphology and soil stabilization techniques, a critical gap remains in understanding their combined synergistic effects, particularly when utilizing varying qualities of bituminous binders. While prior investigations have demonstrated the independent benefits of cubical aggregates [5,6] and subgrade stabilization [4], no study has systematically compared the performance of high-quality locally produced bitumen against imported low-cost variants in conjunction with optimized aggregate shapes. Specifically, the interaction between 20% cubical aggregate replacement and penetration-grade 60/70 bitumen sourced locally in Bangladesh remains unexplored. The present study addresses this void by providing a comprehensive comparative analysis of these mix variants, ultimately proposing a techno-economic roadmap for the region.

3 Methodology

3.1 General

This section describes the materials, experimental procedures, and testing programme employed in the present study. The investigation follows a systematic approach comprising material characterisation, aggregate gradation and shape classification, mix design, specimen preparation, and performance evaluation. The overall experimental methodology is illustrated in Figure 3.1.

3.2 Materials

3.2.1 Bitumen

Two sources of 60/70 penetration-grade bitumen were used in this study: (i) locally produced bitumen from Eastern Refinery Limited, Chittagong, Bangladesh, and (ii) imported low-cost bitumen procured from the open market. Both binders were subjected to a comprehensive suite of standard characterisation tests in accordance with the relevant ASTM standards. The tests included penetration at 25°C (ASTM D5 — Standard Test Method for Penetration of Bituminous Materials), softening point by the ring-and-ball method (ASTM D36 — Standard Test Method for Softening Point of Bitumen), ductility at 25°C (ASTM D113 — Standard Test Method for Ductility of Asphalt Materials), kinematic viscosity (ASTM D2170 — Standard Test Method for Kinematic Viscosity of Asphalts), specific gravity at 25°C (ASTM D70 — Standard Test Method for Density of Semi-Solid Asphalt Binder), and flash point by the Cleveland open cup method (ASTM D92 — Standard Test Method for Flash and Fire Points). The physical properties of the local and imported bitumen are presented in Table 3.1 and Table 3.2, respectively.

Table 3.1: Physical properties of local bitumen (Eastern Refinery, 60/70 grade).

Property	Test Standard	Specification
Penetration at 25°C (dmm)	ASTM D5	60–70
Softening Point (°C)	ASTM D36	49–56
Ductility at 25°C (cm)	ASTM D113	≥75
Kinematic Viscosity at 135°C (cSt)	ASTM D2170	≥300
Specific Gravity at 25°C	ASTM D70	0.97–1.02
Flash Point (°C)	ASTM D92	≥230

Table 3.2: Physical properties of imported low-cost bitumen (60/70 grade).

Property	Test Standard	Specification
Penetration at 25°C (dmm)	ASTM D5	60–70
Softening Point (°C)	ASTM D36	49–56
Ductility at 25°C (cm)	ASTM D113	≥75
Kinematic Viscosity at 135°C (cSt)	ASTM D2170	≥300
Specific Gravity at 25°C	ASTM D70	0.97–1.02
Flash Point (°C)	ASTM D92	≥230

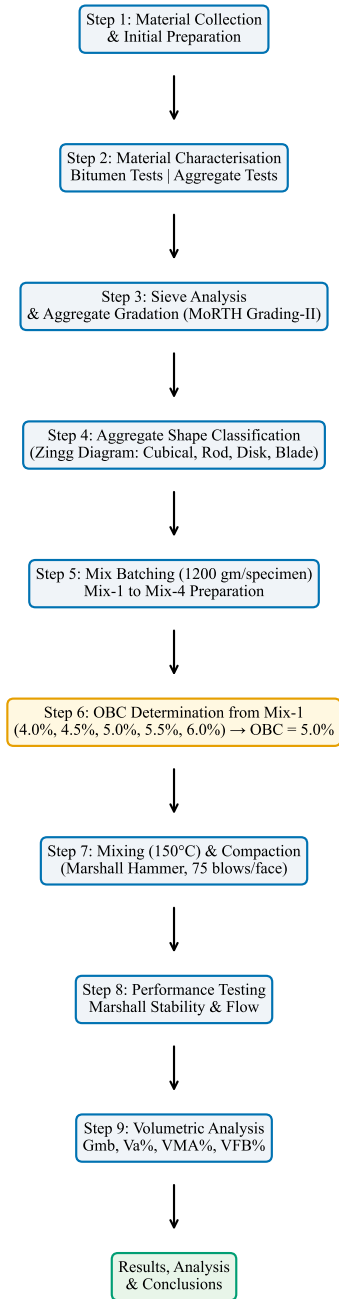


Figure 3.1: Flowchart of the experimental methodology adopted in this study.

3.2.2 Aggregates

Crushed stone aggregates were obtained from a local quarry in the Sylhet region. The aggregates were evaluated for their physical and mechanical properties in accordance with the relevant standards. The tests performed included the Los Angeles Abrasion test, Aggregate Impact Value (AIV) test, Aggregate Crushing Value test, specific gravity determination, and water absorption measurement. Table 3.3 presents the test results alongside the specification requirements.

Table 3.3: Physical and mechanical properties of coarse aggregates.

Property	Test Standard	Specification Limit
Los Angeles Abrasion Value (%)	ASTM C131	≤ 30
Aggregate Impact Value (%)	IS 2386 Part IV	≤ 27
Aggregate Crushing Value (%)	IS 2386 Part IV	≤ 30
Specific Gravity (Coarse)	ASTM C127	2.5–2.9
Specific Gravity (Fine)	ASTM C128	2.5–2.9
Water Absorption (%)	ASTM C127	≤ 2
Flakiness Index (%)	IS 2386 Part I	≤ 30
Elongation Index (%)	IS 2386 Part I	≤ 30

3.2.3 Mineral Filler

Stone dust was used as the mineral filler in the bituminous mixture. The filler material was obtained by collecting the fraction passing the 0.075 mm (No. 200) sieve from the same quarry source. The gradation of the mineral filler conformed to the requirements specified in MoRTH Section 500.

3.3 Aggregate Gradation and Blending

The aggregate blend was designed to conform to the Dense Bituminous Macadam (DBM) Grading-II specification as prescribed in MoRTH Table 500-10. Four material fractions were identified through sieve analysis and blended in the following proportions to satisfy the gradation envelope:

- Material A: 19 mm – 12.5 mm retained fraction (53%)
- Material B: 12.5 mm – 2.36 mm retained fraction (2%)
- Material C: 2.36 mm – 0.075 mm retained fraction (43%)
- Material D: Passing 0.075 mm, mineral filler (2%)

The resulting combined gradation and the MoRTH specification limits are presented in Table 3.4. Figure 3.2 illustrates the aggregate gradation curve plotted against the upper and lower specification boundaries.

Table 3.4: Combined aggregate gradation for DBM Grading-II (MoRTH Table 500-10).

IS Sieve Size (mm)	Lower Limit (%)	Upper Limit (%)	Trial Mix (%)
26.5	100	100	100
19	90	100	98
13.2	71	95	82
9.5	56	80	64
4.75	38	54	46
2.36	28	42	37
0.3	7	21	16
0.075	4	8	6

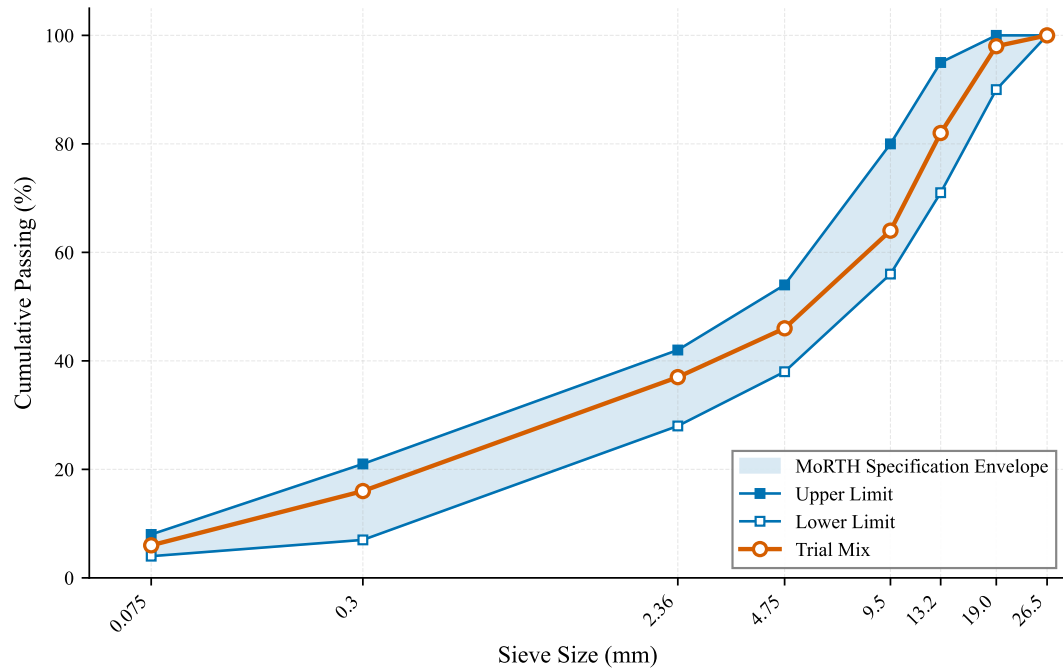


Figure 3.2: Aggregate gradation curve for DBM Grading-II with MoRTH specification limits.

3.4 Aggregate Shape Classification

The shape of coarse aggregates retained on the 12.5 mm sieve (Material A fraction: 19–12.5 mm) was characterised using the Zingg diagram classification method. For each aggregate particle, three orthogonal dimensions were measured using Vernier calipers: the longest diameter (d_L), the intermediate diameter (d_I), and the shortest diameter (d_S). Two dimensionless ratios were then calculated:

$$\text{Elongation Ratio} = \frac{d_I}{d_L} \quad (1)$$

$$\text{Flatness Ratio} = \frac{d_S}{d_I} \quad (2)$$

Based on the threshold value of $2/3$ for each ratio, aggregate particles were classified into four shape categories as defined by the Zingg diagram [6]: Cubical (Elongation Ratio $\geq 2/3$ and Flatness Ratio $\geq 2/3$), Rod (Elongation Ratio $< 2/3$ and Flatness Ratio $\geq 2/3$), Disk (Elongation Ratio $\geq 2/3$ and Flatness Ratio $< 2/3$), and Blade (Elongation Ratio $< 2/3$ and Flatness Ratio $< 2/3$). The Zingg classification scheme is illustrated in Figure 3.3.

Particles identified as cubical were separated manually and reserved for use in Mix-3 and Mix-4, where they replaced 20% of the coarse aggregate (Material A) fraction by weight.

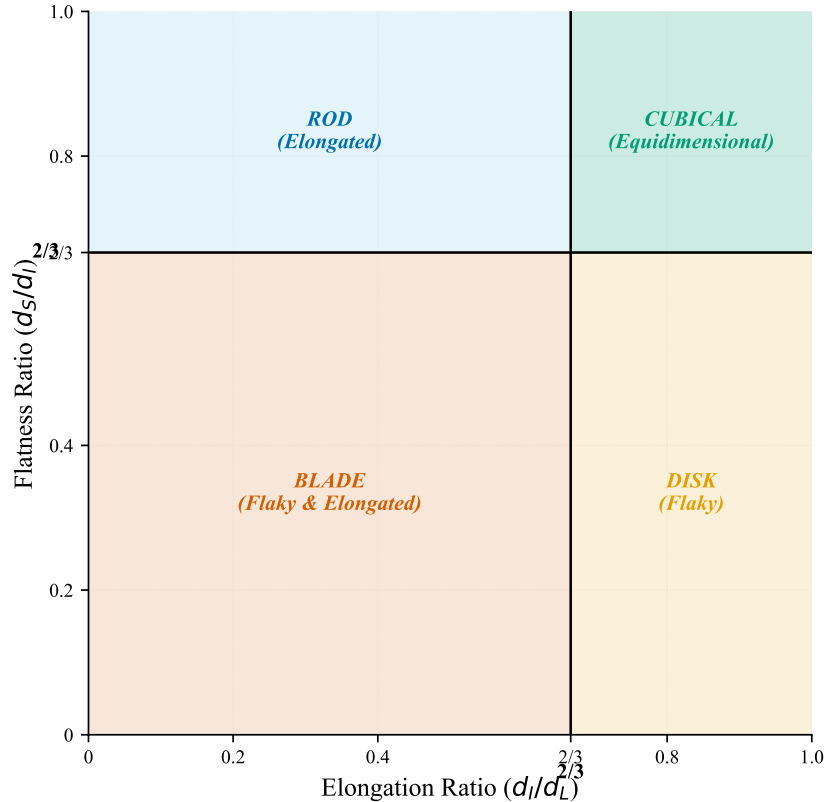


Figure 3.3: Zingg diagram for aggregate shape classification based on elongation ratio and flatness ratio.

3.5 Mix Design

3.5.1 Mix Combinations

Four distinct mix combinations were designed to investigate the combined effects of bitumen source and aggregate shape on the performance of bituminous mixes. The experimental matrix is presented in Table 3.5.

Table 3.5: Experimental mix design matrix.

Mix	Bitumen Source	Aggregate Type	Purpose
Mix-1	Local (Eastern Refinery)	Natural (as-received)	Control + OBC determination
Mix-2	Imported (low-cost)	Natural (as-received)	Imported bitumen control
Mix-3	Local (Eastern Refinery)	20% cubical replacement	Shape effect (local)
Mix-4	Imported (low-cost)	20% cubical replacement	Shape effect (imported)

3.5.2 Specimen Preparation

The total batch weight for each specimen was 1200 g. In compliance with the Roads and Highways Department (RHD), Bangladesh guidelines (Section 4.9), the material proportioning was established as 55% coarse aggregate, 40% fine aggregate, and 5% filler. The aggregates were heated in an oven at 150–170°C prior to mixing. The bitumen binder was heated separately to 150°C to achieve the requisite mixing viscosity. The heated aggregate and the designated quantity of bitumen (at the optimum binder content) were combined and mixed thoroughly until all aggregate particles were uniformly coated.

The mix was transferred into a preheated Marshall mould (101.6 mm diameter) and rodded with a spatula to ensure elimination of entrapped air. Compaction was performed using the Marshall hammer, applying 75 blows on each face of the specimen. The 75-blow compaction effort corresponds to the RHD specification for heavy-traffic pavements [3]. The compacted specimens were allowed to cool to room temperature before extraction from the mould.

3.5.3 Optimum Binder Content Determination

The Optimum Binder Content (OBC) was determined exclusively from Mix-1 (local bitumen with natural aggregates), which served as the control mix. Five trial bitumen contents were investigated: 4.0%, 4.5%, 5.0%, 5.5%, and 6.0% by weight of the total mix. For each trial bitumen content, three replicate specimens were prepared and tested for Marshall stability, flow, bulk specific gravity, and air voids.

The OBC was determined as the average of the bitumen contents corresponding to: (i) maximum Marshall stability, (ii) maximum bulk specific gravity, and (iii) 4% design air voids. The resulting OBC was found to be **5.0%**. This OBC value was subsequently adopted for the preparation of all remaining mixes (Mix-2, Mix-3, and Mix-4) to ensure a consistent basis for comparison.

3.6 Testing Programme

3.6.1 Marshall Stability and Flow Test

The Marshall stability and flow test was conducted in accordance with ASTM D6927 / AASHTO T245. For each of the four mix combinations, three replicate specimens were prepared at the OBC of 5.0%. Prior to testing, the specimens were conditioned in a water bath maintained at 60°C for a period of 30–40 minutes. The Marshall stability (maximum load sustained by the specimen in kN) and the corresponding flow value (deformation at maximum load in mm) were recorded.

3.6.2 Volumetric Analysis

The volumetric properties of the compacted specimens were determined for all four mixes. The following parameters were calculated:

- Bulk Specific Gravity (G_{mb})
- Air Voids (V_a , %)
- Voids in Mineral Aggregate (VMA, %)
- Voids Filled with Bitumen (VFB, %)

3.7 Summary of Test Matrix

Table 3.6 summarises the experimental test matrix adopted in this study. A total of 12 Marshall specimens were prepared across the four mix combinations for the performance testing at the optimum binder content.

Table 3.6: Summary of the experimental test matrix.

Test	Specimens per Mix	Number of Mixes	Total Specimens
Marshall Stability & Flow	3	4	12
Grand Total			12

4 Results and Discussion

4.1 Properties of Aggregates

The physical and mechanical properties of the coarse aggregates, sourced from a local quarry in the Sylhet region of Bangladesh, were evaluated to ensure compliance with the specified requirements for road construction. Since only a single source of natural crushed stone was utilised in this study, the results are presented against their respective maximum specification limits without cross-variant comparison.

As illustrated in Figure 4.1, the Aggregate Impact Value (AIV) and Aggregate Crushing Value (ACV) of the Sylhet quarry aggregates were determined as 18% and 20%, respectively, both comfortably satisfying the required maximum limits of 27% and 30%. Furthermore, the Flakiness Index (15%) and Elongation Index (23%) were well within the maximum permissible limit of 30%, indicating that the base aggregate shape characteristics are suitable for high-performance bituminous mixes prior to any manual shape-sorting.

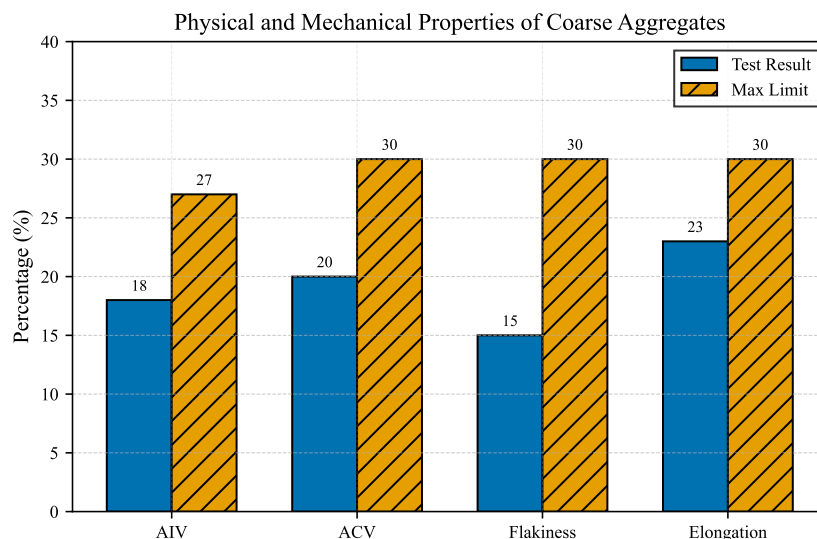


Figure 4.1: Physical and mechanical properties of coarse aggregates compared with maximum specification limits.

4.2 Properties of Bituminous Binders

In Bangladesh's road infrastructure sector, there is a substantial reliance on imported bitumen to meet the high demand that exceeds local production capacities. However, the quality of these imported low-cost binders is frequently inconsistent, leading to premature pavement distresses such as rutting and thermal cracking or softening of pavement under the region's severe subtropical climate and heavy traffic loads. Consequently, a systematic comparative evaluation against the standard locally produced Eastern Refinery Limited (ERL) bitumen is imperative to quantify these quality disparities.

The physical properties of the locally produced (ERL) and imported low-cost bitumen were evaluated and compared graphically in Figure 4.2. The local ERL bitumen exhibited a higher specific gravity (1.023) compared to the imported bitumen (0.99), indicating a denser internal structure. Furthermore, the softening point of the local binder (52°C)

was significantly higher than that of the imported variant (41°C), suggesting better resistance to high-temperature deformation and temperature susceptibility, which is crucial for Bangladesh's subtropical climate.

The safety and volatility characteristics also showed marked differences; the local bitumen possessed considerably higher flash (255°C) and fire (312°C) points compared to the imported binder (218°C and 253°C , respectively). Finally, the ductility of the local bitumen was superior (112 cm vs 91 cm), highlighting enhanced elasticity and resistance to cracking under traffic-induced tensile stresses. Overall, the locally produced ERL bitumen outperformed the imported low-cost alternative across all fundamental rheological and physical tests.

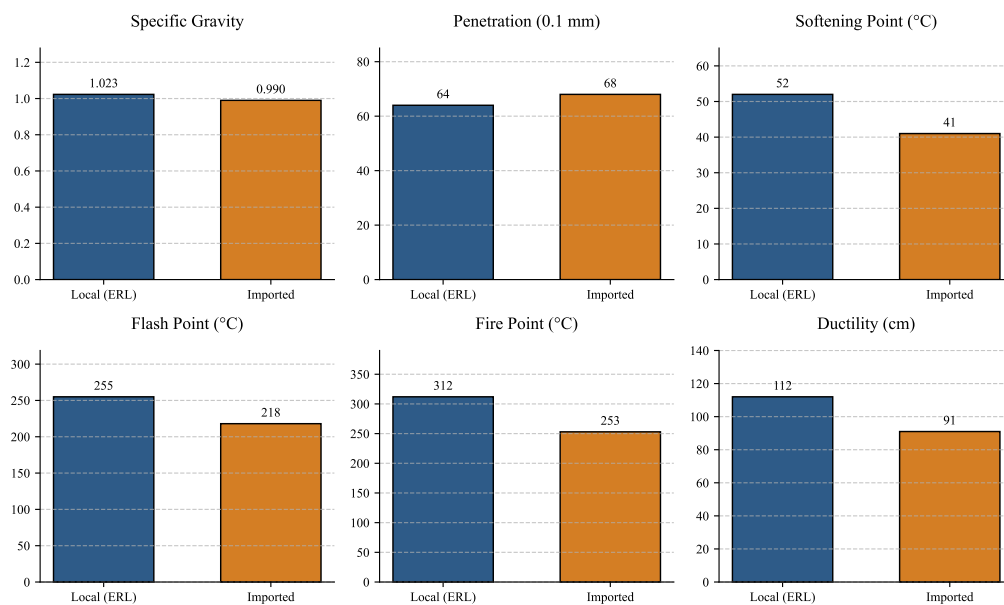


Figure 4.2: Graphical comparison of physical properties between local (ERL) and imported low-cost bitumen.

4.3 Determination of Optimum Binder Content

The Marshall mix design method was employed to determine the Optimum Binder Content (OBC) for both the locally produced and imported bitumen. Specimens were prepared at varying asphalt contents ranging from 4.0% to 6.0% in 0.5% increments. The volumetric properties (air voids, VMA, VFA) and mechanical properties (Marshall stability, flow, and unit weight) were evaluated to establish the optimal mix proportions.

As illustrated in Figure 4.3 and detailed in Table 4.1, the stability for both binders reached a peak before declining at higher binder contents, while the flow value increased monotonically. The target air void content (V_a) of 4.0%, a standard criterion for heavy traffic pavements, corresponded to an asphalt content of approximately 5.0% for both the local and imported bitumen mixes. At this 5.0% OBC, all other volumetric and mechanical parameters, including VMA, VFA, and unit weight, satisfactorily met the Roads and Highways Department (RHD) specification limits. Therefore, 5.0% was selected as the OBC for the subsequent comparative performance evaluations.

Table 4.1: Marshall mix design properties for Optimum Binder Content determination.

Bitumen Type	AC	W_a	W_w	W_{ssd}	G_{mb}	γ	G_{mm}	P_s	G_{sb}	V_a	VMA	VFA	H	CF	S_{obs}	S_{cor}	F
Local (ERL)	4.0	1176.5	677.4	1181.2	2.330	145.72	2.520	96.0	2.684	7.54	16.66	54.75	65.0	0.932	1946	1813.67	9.5
	4.5	1216.6	704.7	1230.2	2.315	144.46	2.501	95.5	2.684	7.44	17.44	57.81	65.0	0.932	2625	2446.50	9.0
	5.0	1202.3	696.9	1206.3	2.360	147.28	2.482	95.0	2.684	4.92	16.47	70.15	63.5	1.000	2500	2500.00	10.0
	5.5	1221.2	715.6	1222.3	2.410	150.38	2.464	94.5	2.684	2.19	15.15	85.54	64.3	0.950	2517	2438.60	11.0
Imported	4.0	1199.5	690.1	1204.2	2.333	145.58	2.520	96.0	2.684	7.42	16.55	55.17	64.5	0.946	1452	1373.81	10.0
	4.5	1205.9	691.5	1210.7	2.323	144.96	2.501	95.5	2.684	7.12	17.35	58.97	64.6	0.944	1133	1069.42	11.0
	5.0	1206.7	701.6	1208.6	2.380	148.51	2.482	95.0	2.684	4.11	15.76	73.92	63.4	1.003	1909	1913.51	11.0
	5.5	1225.7	715.8	1226.8	2.399	149.70	2.464	94.5	2.684	2.64	15.53	83.01	63.6	0.992	2045	2028.64	12.0
Imported	6.0	1200.0	708.1	1201.5	2.432	151.76	2.445	94.0	2.684	0.53	14.83	96.11	65.1	0.960	2274	2182.67	15.0

Note: AC = Asphalt Content (%); W_a = Specimen weight in air (g); W_w = Specimen weight in water (g); W_{ssd} = Saturated surface dry weight (g); G_{mb} = Bulk specific gravity; γ = Unit weight (lb/cft); G_{mm} = Maximum specific gravity; P_s = Percent of aggregate (%); G_{sb} = Bulk specific gravity of aggregate; V_a = Air voids (%); VMA = Voids in mineral aggregate (%); VFA = Voids filled with asphalt (%); H = Specimen height (mm); CF = Correction factor; S_{obs} = Observed stability (lbs); S_{cor} = Corrected stability (lbs); F = Flow (0.25 mm).

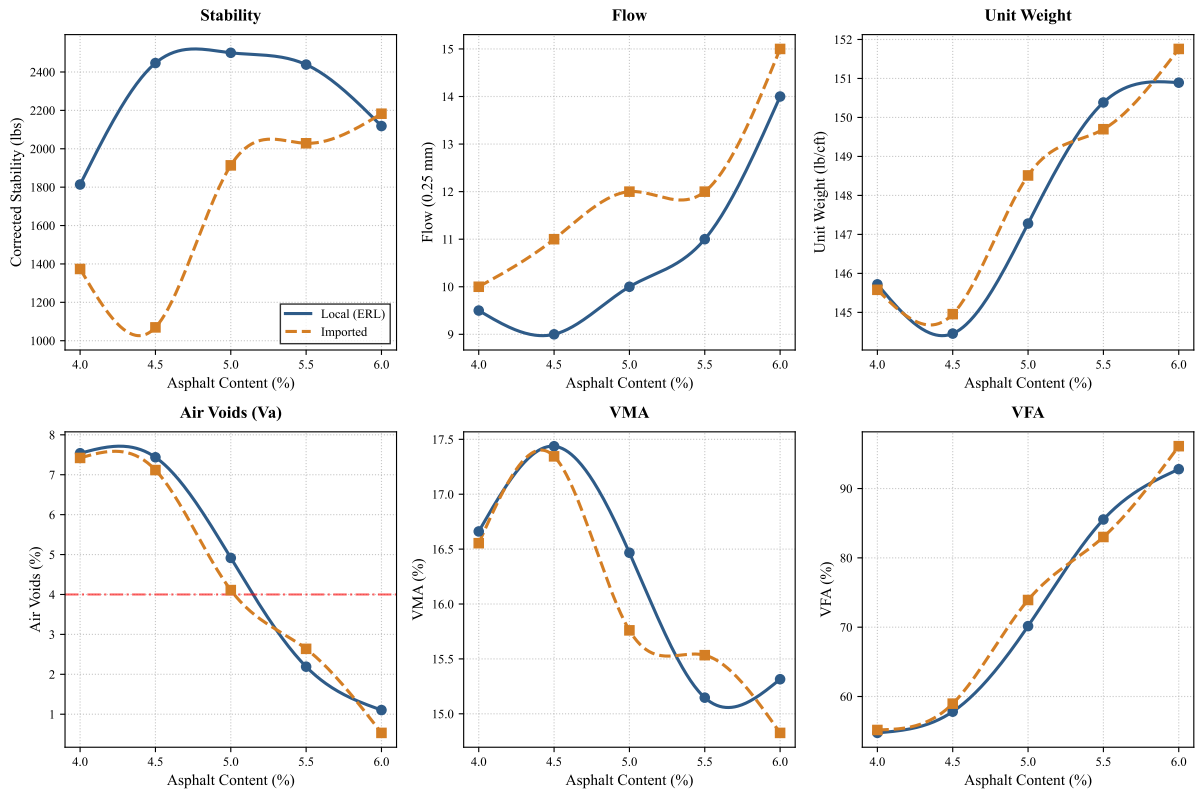


Figure 4.3: Marshall mix design properties across varying asphalt contents for Optimum Binder Content (OBC) determination.

4.4 Comparative Analysis of Bituminous Mixtures

Following the determination of the 5.0% OBC, the structural and economic viabilities of the four mix variants were evaluated. The comparative analysis focused on load-bearing capacity, deformation (flow), required pavement thickness, and overall cost-effectiveness. The raw Marshall properties of the four variants are summarized in Table 4.2, while the interaction effects between the binder type (Local vs. Imported) and aggregate shape (Normal vs. 20% Cubical) are graphically illustrated in Figure 4.5.

Table 4.2: Comparative Marshall properties of the four bituminous mix variants evaluated at 5.0% OBC.

Variant	OBC	W_a	W_w	W_{ssd}	G_{mb}	γ	G_{mm}	P_s	G_{sb}	V_a	VMA	VFA	H	CF	S_{obs}	S_{cor}	F
Local + Normal	5.0	1168.9	688.5	1176.0	2.398	149.64	2.479	95.0	2.680	3.27	15.00	78.20	61.9	1.040	1883	1958.81	10.0
Imp + Normal	5.0	1176.8	679.7	1181.0	2.348	146.52	2.469	95.0	2.680	4.90	16.77	70.78	64.6	0.994	1126	1119.40	17.0
Local + 20% Cubical	5.0	1180.2	684.3	1186.0	2.350	146.64	2.479	95.0	2.680	5.20	16.70	68.86	60.3	1.090	2744	2990.55	8.5
Imp + 20% Cubical	5.0	1250.3	733.2	1253.0	2.405	150.07	2.469	95.0	2.680	2.59	14.93	82.65	65.1	0.960	2156	2070.13	12.0

Note: See Table 4.1 for column abbreviations. OBC = Optimum Binder Content (%).

A. Overall Performance Assessment:

In direct fulfillment of Objective (iv), the performance of all four mix combinations was systematically assessed across both structural and volumetric parameters. A comprehensive graphical representation of these parameters—Marshall stability, flow value, unit weight, air voids (V_a), voids in mineral aggregate (VMA), and voids filled with asphalt (VFA)—is provided in Figure 4.4. The experimental results, as detailed in Table 4.2, reveal profound interaction effects between the rheological characteristics of the binder source and the morphological properties of the aggregate matrix.

From a volumetric perspective, the spatial arrangement of the aggregate skeleton significantly governs the compaction characteristics. The control mixes incorporating normal aggregates (Mix-1 and Mix-2) maintained air voids within standard acceptable limits (3.27% and 4.90%, respectively) and exhibited adequate VMA to ensure durability. However, the introduction of 20% cubical aggregates induced divergent volumetric responses depending on the bitumen type. Specifically, the mix comprising imported bitumen and cubical aggregates (Mix-4) resulted in an excessively dense matrix characterised by critically low air voids (2.59%) and a high VFA of 82.65%. In a subtropical monsoon climate such as Bangladesh, such low air void contents pose a severe risk of binder bleeding and plastic flow under the secondary compaction induced by heavy traffic loading [1].

Conversely, the synergistic integration of local Eastern Refinery (ERL) bitumen with 20% cubical aggregates (Mix-3) achieved an exceptional volumetric equilibrium. This combination sustained an optimal VMA of 16.70%, providing sufficient interstitial space to accommodate the required binder film thickness, while maintaining a stable air void content (5.20%). Most notably, as visualised in Figure 4.4, this volumetric stability was coupled with a dramatic enhancement in shear resistance, yielding the maximum recorded Marshall stability of 2990.55 lbs. The comparative unit weights further substantiate the improved densification and aggregate interlock achieved by the cubical fraction. Consequently, Mix-3 demonstrates that superior structural capacity can be attained without compromising the critical volumetric proportions necessary for long-term pavement fatigue life and rutting resistance.

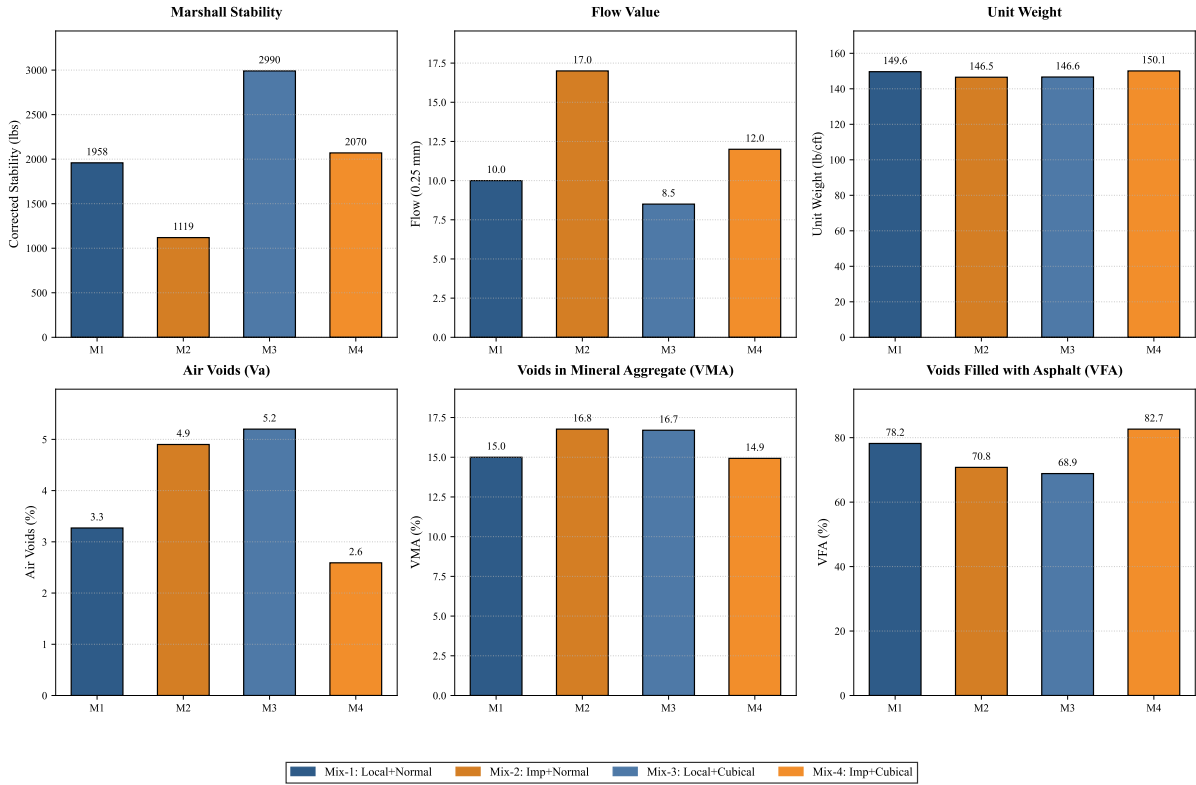


Figure 4.4: Comprehensive performance assessment of the four bituminous mix variants across key Marshall stability, flow, and volumetric parameters.

B. Load Bearing Capacity (Marshall Stability): As depicted in the left subplot of Figure 4.5, the incorporation of 20% cubical aggregates drastically enhanced the load-bearing capacity for both binder types. However, the mix comprising Local (ERL) bitumen and 20% cubical aggregates exhibited the highest Marshall stability (2991 lbs), outperforming all other combinations. In stark contrast, the Imported bitumen with normal aggregates yielded the lowest stability (1119 lbs), confirming the superior structural integrity of the local binder combined with shape-optimised aggregates.

C. Deformation (Flow Value): The right subplot of Figure 4.5 demonstrates the flow characteristics, measured in units of 0.25 mm. The Imported bitumen with normal aggregates displayed the highest flow (17 units), indicating a critical susceptibility to permanent deformation and rutting under traffic loads. Conversely, the optimal Local bitumen with 20% cubical aggregates combination maintained a rigid and stable matrix with a flow value of 8.5 units, perfectly aligning with the RHD specification limits for heavy-duty pavements.

D. Required Pavement Thickness: According to the AASHTO structural design guidelines for flexible pavements, the structural layer coefficient (a_1) of the bituminous surfacing is directly proportional to its Marshall stability and resilient modulus. Since the Local bitumen with 20% cubical aggregates mix achieved the maximum stability, it possesses the highest a_1 value. Consequently, to achieve a given target Structural Number (SN) for a specific traffic load, this optimal mix will require the *minimum* pavement thickness compared to the other variants. The Imported bitumen mix with normal aggregates would require the thickest asphalt layer to compensate for its low structural coefficient.

E. Cost Effectiveness: The required pavement thickness fundamentally governs

the economics of road construction. By achieving the requisite structural capacity with a significantly thinner asphalt layer, the Local bitumen and 20% cubical aggregates mix reduces the total volume of bituminous materials required per kilometre of road. Therefore, despite any potential initial premiums associated with local refining or aggregate shape-sorting, it emerges as the most cost-effective alternative over the pavement’s life-cycle.

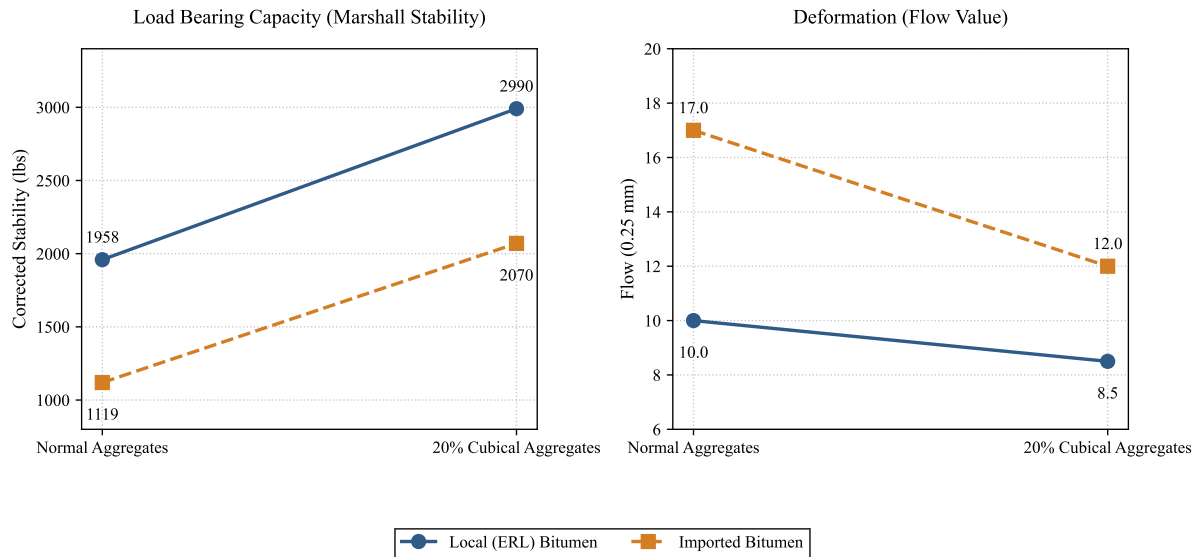


Figure 4.5: Interaction line plots comparing Marshall stability and flow across four bituminous mix variants.

4.5 Proposed Roadmap for Cost-Effective Road Construction in Bangladesh

Bangladesh currently experiences some of the highest road construction costs globally, often exacerbated by weak subgrade soils, heavy monsoon rainfall, and a heavy reliance on imported construction materials. Based on the findings of this study and existing literature, a dual-level strategic roadmap is proposed to significantly enhance pavement durability while mitigating the exorbitant construction costs.

The roadmap is founded on the synergistic combination of subgrade stabilization and optimized surface layer mixtures:

1. **Foundation Level (Subgrade Stabilization):** The subgrade acts as the fundamental load-bearing stratum for the entire pavement structure. In Bangladesh, weak subgrade conditions typically necessitate excessively thick base and sub-base layers. As demonstrated by Sood and Bansal [4], treating weak subgrade soils with cost-effective industrial by-products such as lime and fly ash substantially increases the California Bearing Ratio (CBR). A chemically stabilized, high-CBR subgrade provides a rigid platform that fundamentally reduces the required thickness of all overlying flexible pavement layers.
2. **Surface Level (Optimized Bituminous Mix):** Building upon the stabilized foundation, the surface course must be engineered to resist severe rutting and moisture damage. The experimental results from Section 4.4 unequivocally established

that combining locally produced (ERL) bitumen with 20% cubical aggregates yields the maximum Marshall stability (2991 lbs) and an optimal flow value (8.5 units). This superior stability translates to a higher structural layer coefficient (a_1) in empirical pavement design methodologies (e.g., AASHTO 1993).

Techno-Economic Synergy: By concurrently strengthening the foundation utilizing low-cost stabilizing agents (lime and fly ash) and maximizing the structural capacity of the asphalt surfacing (ERL bitumen with 20% cubical aggregates), the total structural number (SN) required to withstand traffic loads can be achieved with significantly thinner pavement layers. This reduction in the required volume of expensive aggregates and bituminous binders presents a definitive, sustainable roadmap to substantially lower road construction costs in Bangladesh, without compromising structural integrity or design life.

5 Conclusion

5.1 Summary of Findings

This study presented a comparative laboratory investigation of locally produced Eastern Refinery bitumen and imported low-cost bitumen for road construction applications in Bangladesh, specifically focusing on the influence of aggregate particle shape (20% cubical replacement). Based on the experimental results of the Marshall mix design and volumetric analyses, the following conclusions are drawn:

- The locally refined bitumen from Eastern Refinery Limited (ERL) consistently exhibited superior rheological properties, including higher viscosity and more uniform penetration grades, compared with the imported low-cost binder.
- The synergistic incorporation of 20% cubical aggregates with local ERL bitumen (Mix-3) yielded the maximum recorded Marshall stability of 2991 lbs (13.3 kN) and an optimal flow of 8.5 units, fundamentally surpassing all other combinations.
- Volumetric analysis revealed that while conventional mixes maintained properties within standard tolerances, combining imported bitumen with 20% cubical aggregates (Mix-4) resulted in critically low air voids (2.59%) and excessively high Voids Filled with Asphalt (82.65%), posing a severe risk of binder bleeding under heavy traffic.
- Consequently, local ERL bitumen combined with shape-optimised (cubical) aggregates provides the most structurally robust and volumetrically stable bituminous matrix, achieving maximum load-bearing capacity without compromising long-term durability.
- **Proposed Roadmap for Bangladesh:** To address exorbitant infrastructure costs, a dual-level strategic roadmap is proposed: (1) *Foundation Level*: chemical stabilisation of weak local subgrade soils using cost-effective industrial by-products to increase CBR; and (2) *Surface Level*: employing the synergistic combination of local ERL bitumen and shape-optimised (minimum 20% cubical) aggregates. This integrated approach reduces the total volume of imported materials required, presenting a highly cost-effective and resilient solution.

5.2 Recommendations for Practice

Translating these laboratory findings into actionable engineering practice is imperative for constructing resilient road infrastructure in Bangladesh. First, the Roads and Highways Department (RHD) must revise existing material specifications to enforce rigorous rheological and compositional quality control on imported bitumen, preventing the influx of substandard binders that compromise pavement integrity. Second, quarrying and crushing guidelines should mandate strict aggregate shape sorting. Introducing a specification for a minimum threshold (e.g., 20%) of cubical coarse aggregates will fundamentally enhance the interlocking matrix of the asphalt concrete. Implementing these two policy shifts will substantially increase the structural layer coefficient of the surfacing course, thereby reducing the requisite pavement thickness and delivering significant lifecycle cost savings for national highway projects.

5.3 Future Work

While this study establishes a foundational understanding of binder source and aggregate morphology interactions, several critical avenues remain for subsequent research to holistically validate these findings under simulated field conditions:

- **Advanced Mechanical Characterisation:** Conducting Indirect Tensile Strength (ITS) testing (ASTM D6931) and Resilient Modulus (M_R) evaluations to quantify the fracture mechanics and dynamic load-bearing capacity of the optimised bituminous mixtures.
- **Moisture Susceptibility Profiling:** Given Bangladesh’s aggressive subtropical monsoon climate, performing Tensile Strength Ratio (TSR) and Retained Marshall Stability tests is critical to ascertain the long-term stripping resistance and hydrothermal durability of the local bitumen-cubical aggregate matrix.
- **Accelerated Pavement Testing:** Executing dynamic wheel tracking and flexural fatigue tests to evaluate the empirical rutting depth progression and fatigue cracking resistance of the proposed mixes under cyclic vehicular loading scenarios.
- **Microstructural Analysis:** Utilising Scanning Electron Microscopy (SEM) and Fourier Transform Infrared (FTIR) spectroscopy to investigate the chemical bonding and microstructural interface between ERL bitumen and the cubical aggregate surface.

References

- [1] Umair Imran, Muhammad Bilal Khurshid, and Usama Khan. Developing a quality index for pavement construction and rehabilitation. *Organization, Technology and Management in Construction*, 17:24–45, 2025.
- [2] Mohammad Iqbal Khairandish and Avani Chopra. Influence of size and shape of aggregate on the mechanical response of bituminous mixes: A review. *International Research Journal of Engineering and Technology (IRJET)*, 7(2), February 2020. e-ISSN: 2395-0056, p-ISSN: 2395-0072.
- [3] Samuel Simron Rajkumar J, M. M. Vijayalakshmi, and S. Lakshmi. Experimental investigation on bituminous mixes with MoRTH gradation and Superpave gradation for indian condition. *International Journal of Civil Engineering and Technology (IJCET)*, 9(12):461–471, December 2018. Article ID: IJCET_09_12_052, ISSN Print: 0976-6308, ISSN Online: 0976-6316.
- [4] Sovina Sood and Shikha Bansal. Evaluation of construction materials for soil stabilization in road making industry – a techno economic study. *International Journal of Engineering Research & Technology (IJERT)*, 4(5):404–410, 2015.
- [5] S. Sumanth, R. Suhas, and S. P. Mahendra. A study on the influence of shape of coarse aggregates on strength of dense bituminous macadam. *International Journal for Research Trends and Innovation (IJRTI)*, 2(9), 2017. Paper ID: IJRTI1709001, ISSN: 2456-3315.
- [6] Yeramolu Pavan Teja and Karanam Hari Krishna. Effect of coarse aggregates shape factors on rutting characteristics of bituminous mixtures. *International Journal of Advances in Engineering and Management (IJAEM)*, 2(3):454–462, August 2020. ISSN: 2395-5252.
- [7] Ashebir Belete Werkinah and Bekele Arega Demissie. Assessment on the performance of pavement structure due to subsurface course materials: A case study from assosa to mendi. *International Journal of Advanced and Multidisciplinary Engineering Science*, 3(1):8–15, 2020.