# Onset kinetics on a resolved neighbour cell: where a whole-cell threshold and a local one disagree

Siddharth Satte, Independent researcher, Pune, India, 26 October 2026. A pre-registered pilot: predictions commits b09ef1d (Stages 1, 2) and 2657aee (Stage 3), each public before its kinetics ran on an archived history. doi.org/10.5281/zenodo.23279455; github.com/siddharth161204-wq/m50-neighbour-onset-kinetics.

1. With copper busbars (500 mW/K in all) and the largest Databank energy (33.2 kJ), the resolved neighbour's hottest node starts to self-heat at 0.15 K/min 23.4 and 26.4 s before the lumped node (10 and 30 s releases); under the posterior-mean B-CRNN kinetics of Koenig, Zhao and Deng each start is a fresh SEI decomposing at 108.4 C.
2. The smallest busbar conductance at which only the local chemistry starts is 100 mW/K under those kinetics (21.5 kJ).
3. Over 200 draws of their kinetic posterior the lumped node never starts first in any of the 42 cases; at 33.2 kJ, 30 s and 500 mW/K the lead runs from 15.4 to 58.9 s (2.5 to 97.5 %, median 26.3 s).
4. There, over the published spread of the roll's conductivity and heat capacity the hottest node's onset varies 0.027 times as much as over the kinetic posterior (standard deviations; the lumped node's 0.11 times): the kinetics set both.

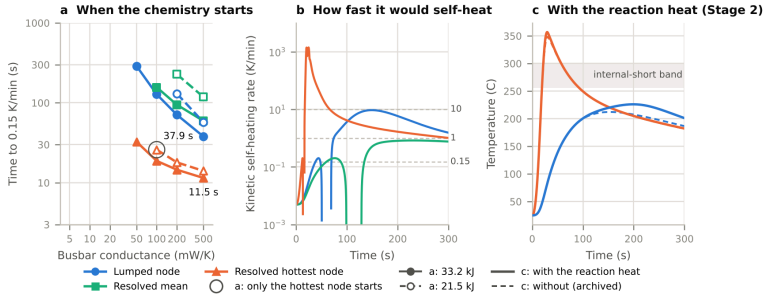



Figure 1. (a) First time each history self-heats at 0.15 K/min, 30 s release, 33.2 kJ (filled) and 21.5 kJ (hollow); ringed where only the hottest node starts. (b) Kinetic self-heating rate along the three histories, 33.2 kJ, 30 s, 500 mW/K; gaps: net endothermic (separator melting). (c) With the reaction heat (solid) and without (dashed): the hottest node enters the internal-short band at 19.2 s either way; the lumped node peaks at 226 C.

## Method

1. Kinetics: the B-CRNN of Koenig, Zhao and Deng (Chem. Eng. J. 507 (2025) 160402), averaged over its trained particles: three NCM811 cathode, seven anode-electrolyte-SEI-binder and one separator reaction, at their cell's reactant mass fractions.
2. Checks against the source: their DSC curves at 5 C/min are reproduced; our emulation of their ARC test gives $T_{in}$ = 179.3 C, inside their main-cluster band of 169.0 to 198.0 C, but $T_{on}$ = 199.8 C at their stated 1 C/min trigger, below their band of 255.7 to 302.1 C.
3. Stage 1, passive: BDF along three archived 0.5 s histories (hottest node, resolved mean, lumped node) of the 49 cases of the two-cell study (doi:10.5281/zenodo.23253738). Stage 2, reactive, one-way, five cases: the reaction heat fed into its solver.
4. Stage 3: 200 joint draws of the posterior's particles on nine cases (42 for P3); 30 Latin hypercube draws of the roll's conductivities and specific heat (O'Regan et al. 2022; Chen et al. 2021) in the published solver; 210 pairs (Figure 2, README).
5. Checks: halving tolerances, steps and grids moves the onsets by at most $7 \times 10^{-5}$ of themselves; energy accounts close to $10^{-11}$ at the published conductivities; with a $10^4$ W/mK roll resolved and lumped agree within 0.8 K.

## Limits

1. The kinetics come from other cells (NCM811 and graphite DSC data, not the M50's silicon-graphite negative). The SEI is fresh; the mean model decomposes it even at 25 C, and with it gone the lead grows to 60 s (exploratory).
2. Stage 1 ignores the reaction heat; Stage 2 is one-way; conduction and radiation only, so ejecta, flame and venting are excluded and none of this is propagation. The internal short is the source's $T_{on}$ band as a temperature, not a model; at its own 1 K/min trigger the lumped node would short too.
3. One geometry without the cap and tabs, constant properties, and a hottest node that is the envelope of local histories.
4. Stage 3 treats the three submodels' particles as independent; its thermal ranges are literature spreads, not measured uncertainties of this cell (contact, busbar, emissivity fixed); its ARC check failed the brief's acceptance, passing only as amended.

## Prediction scorecard

| | Prediction | Result | Measured |
|---|---|---|---|
| P1 | Hottest node over half the lumped time earlier | Held | 85 and 70 % earlier (central 86, 71 %) |
| P2 | The resolved mean starts in exactly 10 named cases | Held | The same 10 |
| P3 | Smallest only-local conductance 100 mW/K | Held | 100 mW/K; also 8.75 kJ at 500, as named |
| P4 | Hottest node at 10 K/min, lumped under 1 K/min | Held | In the 4 named cases |
| P5 | Stage 2: (a) only the hot spot shorts; (b) at 200 mW/K too; (c) neither at 21.5 kJ | (b) failed | (a), (c) held; (b) +0.6, +0.7 K (central 5 to 10 K) |
| | **Stage 3** (33.2 kJ, 30 s, 500 mW/K; P3 over the 42 cases) | | |
| P1 | Hottest node first in over 95 % of draws | Held | 100 % (central 99 %) |
| P2 | 95 % onset interval: hottest under 20 s, lumped over 20 s | Held | 9.3 and 52.9 s (central 8 and 40 s) |
| P3 | Only-local conductance 100 mW/K in over half, never above 200 | Failed | 21 %; 500 mW/K in 10.5 % |
| P4 | Hottest onset: thermal SD over 1.5 times kinetic | Failed | 0.027 (central 3) |
| P5 | Lumped onset: kinetic SD over 1.5 times thermal | Held | 9.5 (central 2) |
| P6 | Under 10 % start below 100 C (early SEI) | Failed | 36.5 %, in all nine cases |

## Stage 4 (v1.1)

1. Each of the posterior's three submodels varied alone over the same 200 draws, the other two at their posterior mean (a choice; the joint draws stay the headline); 33.2 kJ, 30 s, 500 and 100 mW/K; predictions commit a975f20.
2. The anode-electrolyte submodel, holding the SEI, carries essentially all of the variance: 0.997 of the lead's at 500 mW/K (0.89 to 1.09 for every output at both); NCM811 cathode 0.000, separator at most 0.002.
3. With it at its mean no draw starts below 100 C; varied, 37.5 % do.
4. Its central half (a parameter-space proxy for a tighter posterior, on all 57 varying parameters) narrows the lead's 95 % width only from 43.5 to 37.1 s (14.6 %); on the SEI's own parameters, 18.1 %.
5. Exploratory: the lead has two modes (starts by 122.4 C, or at 184.9 C and above) and a tighter posterior keeps both; in marginal draws the SEI's heat net of the separator's melting sets the mode.
6. Scorecard: P1 (SEI submodel over half the lead's variance) held, 0.997 (central 65 %); P2 (shares sum to 0.8 to 1.1) held, 0.998; P3 (under 5 % below 100 C) held, 0 %; P4 (over 40 % narrower) failed, 14.6 %; P5 (same ranking at 100 mW/K) held.

## Stage 5 (v1.2)

1. Against two-cell LG M50 tests of Fransson et al. (J. Power Sources 617 (2024) 234916; 9 of 16 propagated in 147 to 342 s): steel-on-steel contact 200 to 3,700 W/(m$^2$ K), nickel-strip tabs, 33.2 kJ; conduction and radiation only (no venting, ejecta or flame); predictions b4883ba.
2. In none of 5,248 runs, the brief's 4,800-run factorial among them, does either neighbour reach 255.7 C within 900 s.
3. In the central case the resolved hot spot, on the line of contact, peaks at 192 C by 41 s; the lumped neighbour at 159 to 162 C at 255 to 270 s.
4. In any run at most 226.7 C (resolved) and 180.6 C (lumped); 13 of 16 trigger cells peaked above the central case's cell 1 (548 C).
5. Exploratory: over the paper's Section 2, in the central case, the face away and the lumped neighbour heat at 0.35 to 0.52 C/s (the line of contact faster), 3.5 to 5.2 times the tests without propagation (0.1 C/s) and near those with it (0.4), but not as hot.
6. Scorecard: P1 (in 147 to 342 s) failed; P6 (30 to 90 %) failed at 0 %; P2 (lumped later or never) held; P3 to P5 and P7 not met, so failed.
7. Lacking the tests' venting, ejecta and flame, the model was expected to propagate later than they did, if at all; it never does. Conduction and radiation alone do not suffice here, and P2 holds only because nothing propagates: whether a lumped cell can be trusted in a pack stays open.

## Stage 6 (v1.2)

1. The paper's 150 C criterion on the 36 Stage 5 grid runs (predictions c9586a8): only the lumped neighbour at the central contact crosses inside the measured 147 to 342 s, in 11 of 12 runs; the hot spot crosses at 7 to 22 s; the face away and the resolved mean never reach 150 C.
2. Trigger matched to the tests (releases of 17.5 to 25.2 s from the paper's supplementary Figure 10, conditional): at 33.2 kJ cell 1 peaks at 526 to 537 C in the central case, inside the measured 164 to 832 C; at the Databank's total with ejecta, 107 kJ, at 1,424 to 1,494 C (P4 failed).
3. Matched case, 442 runs with the 200 draws: neither neighbour reaches 255.7 C (hot spot at most 227 C, lumped 179 C), as in Stage 5.
4. At 107 kJ the hot spot reaches 255.7 C in every run at 8 to 17 s, the lumped neighbour 32 to 168 s later (P7 held); exploratory, at the tests' median trigger peak (704.5 C, 45.2 kJ) only the high contact ignites (hot spot 17 s, lumped 198 to 236 s).
5. Scorecard: P1 to P6 failed, five of them foreseeable from Stage 5's records, as the predictions state; P7 held.
6. The matched trigger does not ignite the neighbour by conduction and radiation; where the hot spot ignites it does so before any test propagated, the lumped neighbour inside their window in 13 of 50 runs. Next: the ignition condition (aged SEI, internal short as an event), set up, not run.

## Stage 7 (v1.3)

1. One trigger per test (predictions 714b1fd): the energy that puts cell 1 at each test's measured maximum (9.0 to 54.3 kJ for 164 to 832 C, central case, 21.39 s release); seven ignition conditions read from 128 runs (three contacts, fresh and aged SEI) and scored against the sixteen outcomes, the central contact registered.
2. The hot spot at 255.7 C (C1) predicts 8 tests: 6 hits and 2 false alarms, 11 of 16 right, but every hit 130 to 323 s before the measured time; the lumped neighbour at 255.7 C (C2) predicts 2, both hits.
3. The lumped neighbour at the paper's 150 C (C3) and the separator's melting, 138.5 C, at the hot spot (C4) or in the lumped neighbour (C5) each predict the same 14 tests: 8 hits and 6 false alarms, 9 of 16 right; C3's hits come 43 to 260 s early.
4. An aged SEI (none left) changes no hot-spot verdict at the central contact and raises the first self-heating from 108.4 C to 181.5 to 202.1 C (a cathode reaction); the other two releases and the separator's spread change no verdict.
5. The internal short as an event (the cell's stored 65.52 kJ released over 21.39 s from the melt, a modelling choice) takes the hot spot to 1,504 to 1,584 C, about twice the hottest propagating neighbour (763 C): none of 28 runs lies in the measured 381 to 763 C, nor any at 63.36 kJ. Nothing in it is a source to a further cell; the geometry ends at the neighbour.
6. Scorecard: P1 (C1 in fewer than 9), P4 (C4 in more than 9) and P6 (no inversion) held; P2 (9 of 16, one short), P3 (1 of 8 within 60 s), P5 (raised, not lowered), P7 (C1 6 to 2) and P8 (0 of 28) failed, each as its predictions expected.
7. No criterion reproduces the tests: the whole cell's clocks predict too many (C3, C5) or too few (C2), the hot spot's come minutes early, and the event overshoots without venting or ejecta (in the Databank's nail tests the cell body kept 19 to 31 % of the energy). Exploratory: the hot spot's 255.7 C is a passing peak (262 to 307 C, then cooling), and no threshold on the trigger's peak gets more than 12 of 16 right.

## What it means for the thesis

Under DSC-trained kinetics a neighbour heated through copper busbars at 33.2 kJ starts to react where the busbar enters, before a lumped model in all 200 draws of the kinetic posterior (by 15 to 59 s in 95 % of them at the 30 s release); the uncertain kinetics, not the roll's published properties, set when. Next: an aged SEI in a resolved, two-way coupled cell with the cap and tabs.

Credit: The Battery Failure Databank is provided by the U.S. Department of Energy's National Renewable Energy Laboratory, operated by Alliance for Sustainable Energy, LLC (DOE/NREL/ALLIANCE); its notice accompanies the rows used, in inputs/databank/.