


Description

Process schematic

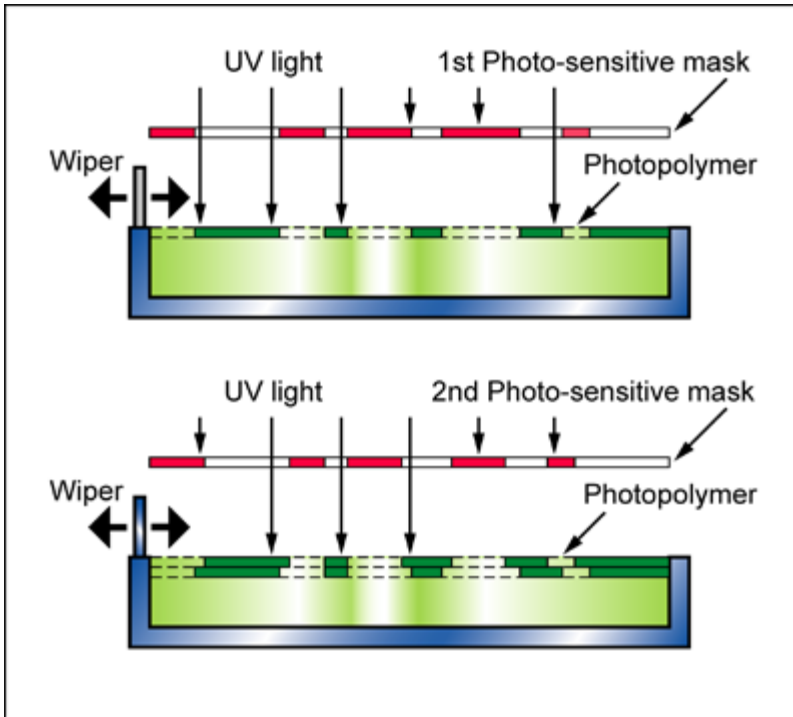

The process

SOLID GROUND CURING (SGC) is an additive manufacturing technique which differs in concept from laser-based methods. A negative image of the layer of the part to be produced is created electrostatically on a glass plate (as in a photocopier). The mask is positioned over a bath of photo-sensitive resin and the clear areas cured by exposure to UV light. The resin is wiped clear, leaving hardened areas intact. Wax is applied to the top surface to provide support to the cured resin, and solidified by chilling. The top surface is then milled back to the required thickness and the next layer of resin is applied for curing. As with other additive manufacturing processes, a CAD solid model of the part is required.

This technique is now obsolete, having been superseded by Mask Projection Stereolithography (MPSLA) which does not require chilling or milling during the building process.

Material compatibility

Polymers - thermoplastics	✓
Polymers - thermosets	✓

Shape

Circular prismatic	✓
Non-circular prismatic	✓
Flat sheet	✓
Dished sheet	✓
Solid 3-D	✓
Hollow 3-D	✓

Economic compatibility

Economic batch size (units)	1	-	10
-----------------------------	---	---	----

Physical and quality attributes

Mass range	* 0.22	-	176	lb
Range of section thickness	27.6	-	3.94e3	mil
Tolerance	3.94	-	78.7	mil
Roughness	* 3.94	-	5.91	mil


Process characteristics

Primary shaping processes	✓
Discrete	✓
Prototyping	✓

Cost model and defaults

Relative cost index (per unit)	* 1.94e3	-	4.77e3
--------------------------------	----------	---	--------

[Parameters:](#) Material Cost = 3.63USD/lb, Component Mass = 2.2lb, Batch Size = 1e3, Overhead Rate = 150USD/hr, Discount Rate = 5%, Capital Write-off Time = 5yrs, Load Factor = 0.5

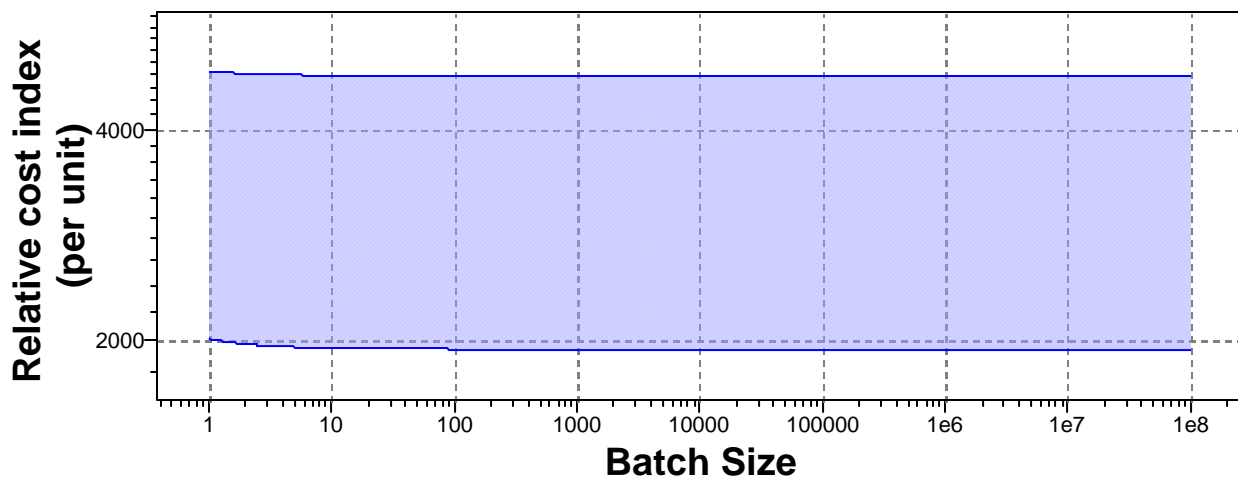

Capital Write-off Time=5yrs, Component Mass=2.2lb, Load Factor=0.5, Material Cost=3.63USD/lb, Overhead Rate=150USD/hr, Discount Rate=5%

Capital cost	5.66e5	-	7.54e5	USD
Material utilization fraction	* 0.5	-	0.7	
Production rate (units)	0.04	-	0.1	/hr
Tooling cost	* 37.7	-	94.3	USD
Tool life (units)	1	-	2	

Supporting information

Design guidelines

Complex models possible including ready assembled multi-component products.

Technical notes

The process is limited to resins that can be photo-polymerized, most based on acrylates.

Typical uses

Making prototypes and models quickly from CAD systems.

The environment

Photopolymers are thermoset materials and cannot be melted again for reuse. Care needed with environmentally hazardous solvents used to clean up models. Direct exposure to the laser beam must be avoided. The resins are volatile, requiring good ventilation.

Links

MaterialUniverse

Reference
