

Description

Process schematic

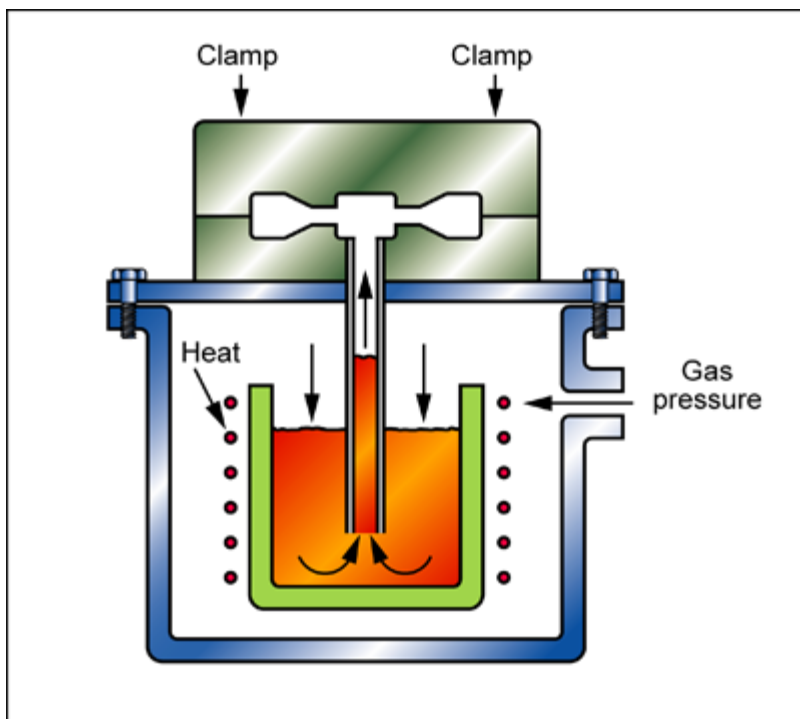


Figure caption

Low pressure die casting.

The process

In LOW PRESSURE DIE CASTING, molten metal is displaced upwards into a die by low pressure gas. The die cavity is filled slowly upwards which minimizes entrained air and gives high soundness. Such castings have better metallurgical integrity than conventional die castings, and they can be heat-treated. The process has most of the benefits of die casting without the disadvantages. The dies are made from cast iron which is comparatively cheap and easy to machine. Tool steel inserts may be used for high production runs of complex castings. Tooling costs are about half those for pressure die casting. The process is only suitable for low melting point alloys ($T_m < 950^\circ\text{C}$). Shapes are of average complexity and undercuts are possible but expensive.

Tradenames

LP die casting

Material compatibility

Metals - non-ferrous



Shape

Circular prismatic



Non-circular prismatic



Solid 3-D



Hollow 3-D



Economic compatibility

Relative tooling cost

medium

Relative equipment cost	medium
Labor intensity	medium
Economic batch size (units)	2e3 - 1e5

Physical and quality attributes

Mass range	11 - 55.1 lb
Range of section thickness	157 - 394 mil
Tolerance	15.7 - 31.5 mil
Roughness	0.0709 - 0.248 mil
Surface roughness (A=v. smooth)	B


Process characteristics

Primary shaping processes	✓
Discrete	✓

Cost model and defaults

Relative cost index (per unit)	35.2 - 79.8
--------------------------------	-------------

Parameters: Material Cost = 3.63USD/lb, Component Mass = 2.2lb, Batch Size = 1e3, Overhead Rate = 150USD/hr, Discount Rate = 5%, Capital Write-off Time = 5yrs, Load Factor = 0.5

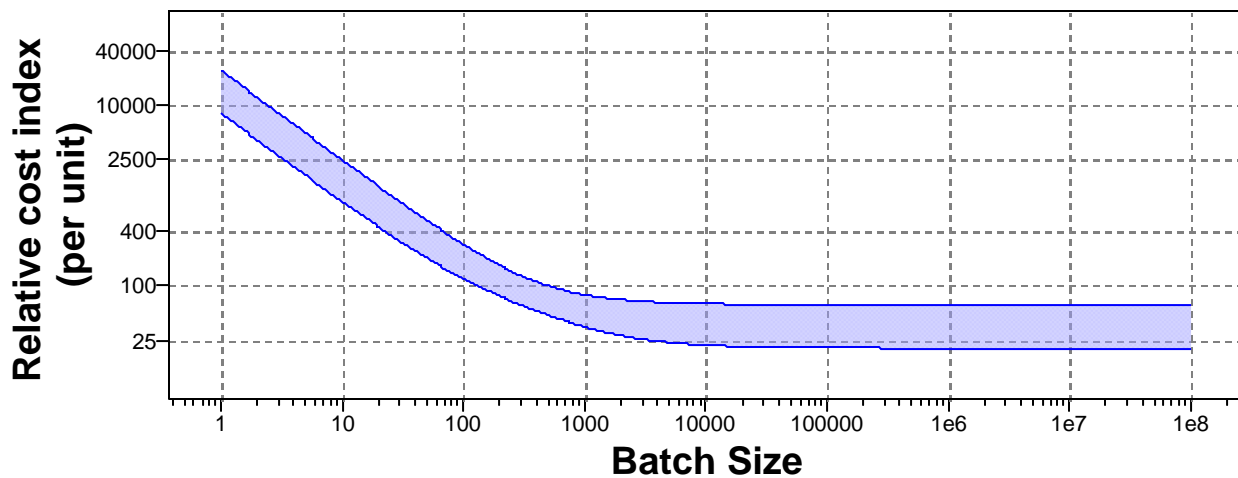

Material Cost=3.63USD/lb, Component Mass=2.2lb, Overhead Rate=150USD/hr, Capital Write-off Time=5yrs, Load Factor=0.5, Discount Rate=5%

Capital cost	1.64e4 - 1.64e5 USD
Material utilization fraction	0.8 - 0.85
Production rate (units)	3 - 15 /hr
Tooling cost	8.2e3 - 2.46e4 USD
Tool life (units)	3e4 - 1e5

Supporting information

Design guidelines

Low pressure die casting is best for castings with low surface area/volume ratio. Sand cores can be

Technical notes

The process is suitable for low melting point alloys. It is predominantly used for aluminum alloys. It gives good surface definition and better metallurgical integrity than die-casting. A general taper of 2 to 3 deg is required to allow extraction from the mold.

Typical uses

Automotive wheels and cylinder heads, gearbox and clutch covers, transmission and differential housings, electric motor stators, transformer covers and heat sinks.

The economics

Tooling cost range covers small, simple to large, complex

Links

MaterialUniverse

Reference
