


Description

Image

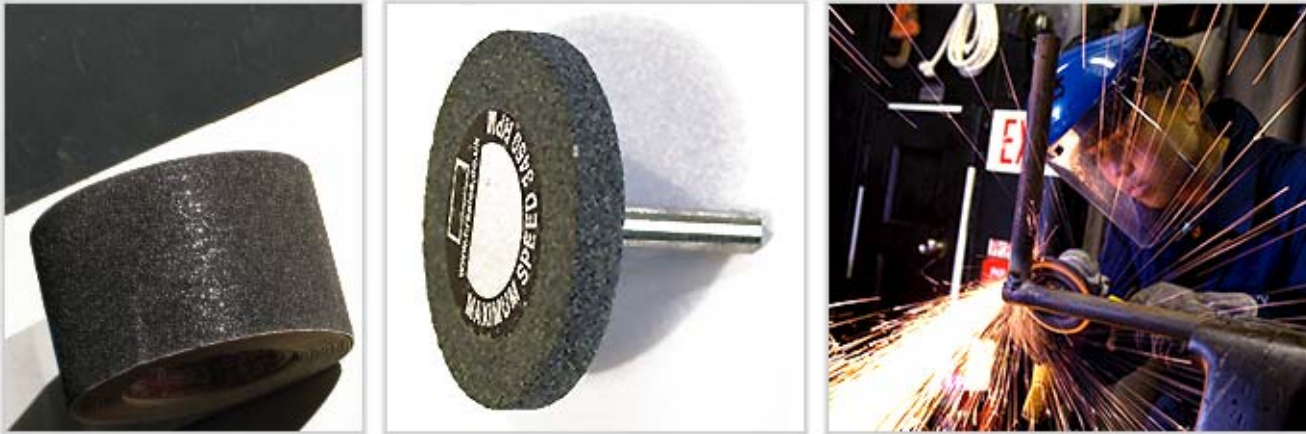

Caption

1. Samples of silicon carbide sandpaper. © Tiesse at en.wikipedia - Public domain 2. Silicon carbide grinding wheel.
3. U.S. Navy technician uses a silicon carbide sander. © U.S. Navy - Public domain

The material

Silicon carbide (SiC, carborundum), made by fusing sand and coke at 2200 C, is the grit on high quality sandpaper. It is very hard and maintains its strength to 1400C high temperature, has good thermal shock resistance, excellent abrasion resistance, but, like all ceramics, it is brittle. It has the highest corrosion resistance of all advanced ceramics.

Composition (summary)

SiC

General properties

| | | | | |
|-----------------|--------|---|------|--------------------|
| Density | 194 | - | 200 | lb/ft ³ |
| Price | * 6.59 | - | 9.41 | USD/lb |
| Date first used | 1893 | | | |

Mechanical properties

| | | | | |
|--|--------|---|-------|-----------------------|
| Young's modulus | 58 | - | 66.7 | 10 ⁶ psi |
| Shear modulus | * 26.1 | - | 28.6 | 10 ⁶ psi |
| Bulk modulus | * 26.8 | - | 29 | 10 ⁶ psi |
| Poisson's ratio | 0.16 | - | 0.18 | |
| Yield strength (elastic limit) | 58 | - | 88.5 | ksi |
| Tensile strength | 58 | - | 88.5 | ksi |
| Compressive strength | 145 | - | 761 | ksi |
| Elongation | 0 | | | % strain |
| Hardness - Vickers | 2.3e3 | - | 2.6e3 | HV |
| Fatigue strength at 10 ⁷ cycles | * 17.4 | - | 54.8 | ksi |
| Fracture toughness | 2.73 | - | 5.1 | ksi.in ^{0.5} |
| Mechanical loss coefficient (tan delta) | * 2e-5 | - | 5e-5 | |

Thermal properties

| | | | | |
|---------------------------------|----------------|---|--------|-----------------------------|
| Melting point | 3.91e3 | - | 4.53e3 | °F |
| Maximum service temperature | 2.55e3 | - | 3.09e3 | °F |
| Minimum service temperature | -458 | - | -456 | °F |
| Thermal conductor or insulator? | Good conductor | | | |
| Thermal conductivity | 46.2 | - | 75.1 | BTU.ft/h.ft ² .F |
| Specific heat capacity | 0.158 | - | 0.191 | BTU/lb.°F |
| Thermal expansion coefficient | | | | |

| | | | |
|------|---|------|------------|
| 2.22 | - | 2.67 | μstrain/°F |
|------|---|------|------------|

Electrical properties

Electrical conductor or insulator?

Poor insulator

Electrical resistivity

| | | | |
|-----|---|------|---------|
| 1e9 | - | 1e12 | μohm.cm |
|-----|---|------|---------|

Dielectric constant (relative permittivity)

| | | |
|-----|---|---|
| 6.3 | - | 9 |
|-----|---|---|

Dissipation factor (dielectric loss tangent)

| | | |
|---------|---|-------|
| * 0.001 | - | 0.005 |
|---------|---|-------|

Dielectric strength (dielectric breakdown)

| | | | |
|-------|---|-----|-------|
| * 127 | - | 254 | V/mil |
|-------|---|-----|-------|

Optical properties

Transparency

Translucent

Refractive index

| | | |
|------|---|-----|
| 2.66 | - | 2.7 |
|------|---|-----|

Processability

Moldability

| | | |
|---|---|---|
| 2 | - | 3 |
|---|---|---|

Machinability

| | | |
|---|---|---|
| 1 | - | 2 |
|---|---|---|

Eco properties

Embodied energy, primary production

| | | | |
|--------|---|--------|---------|
| 7.61e3 | - | 8.41e3 | kcal/lb |
|--------|---|--------|---------|

CO2 footprint, primary production

| | | | |
|------|---|-----|-------|
| 6.24 | - | 6.9 | lb/lb |
|------|---|-----|-------|

Recycle

✗

Supporting information**Design guidelines**

Silicon carbide and silicon nitride are two of the emerging breed of high performance technical ceramics. Their extreme corrosion resistance and high hardness makes them a good choice for mechanical components that must withstand corrosive fluids - bearings, including ball bearings, and valve and pump parts in sewage systems, for example. Their other unique feature is their ability to carry significant loads at temperatures as high as 1800 C. The main drawbacks are their low toughness, requiring careful design and flaw-free fabrication, and their high cost, which has slowed their take up. Technical ceramics are formed by the following steps. (a) Pressing, isostatic pressing, powder extrusion (for bars and tubes) or powder injection molding (for intricate, high-volume parts). (b) Green-machining in the unfired state, using standard tools. (c) Firing or "sintering" typically at 1550 - 1700 C for 12 to 20 hours; the part shrinks by about 20%. (d) Diamond grinding to achieve tighter tolerance and surface finish: +/- 10 microns is achievable. The cost of a ceramic part is greatly increased if it has to be diamond-ground. Thus design for net-shape sintering, eliminating step (d) is highly desirable. The standard tolerance for as-fired dimensions is +/- 1% or 125 microns, whichever is greater. Silicon carbide is a blue-black in color; silicon nitride is dark gray or black. Both can be polished to a very smooth, reflective surface, giving parts with a striking appearance.

Technical notes

Silicon carbide starts as a powder, is pressed (with a polymer binder) to the desired shape, then fired at a high temperature, burning off the binder and causing the powder to sinter. It is exceptionally wear and corrosion resistant. Its electrical properties can be adjusted by doping. High strength SiC fibers such as Nicalon, made by CVD processes, are used as reinforcement in ceramic and metal matrix composites.

Typical uses

Mechanical seal faces; bearings; turbocharger bearings; gas turbine rotors; wear and corrosion-resistant parts; high temperature devices, laboratory test equipment; hydraulic plungers; pistons; cylinder liners; guides and feeds; heating elements, body and aircraft armor.

Links

Reference

ProcessUniverse

Producers

