

单件分析报告 — MAT_NO 26BD04863202

生成时间: 2026-07-13 22:21:25

基本信息


- MAT_NO: 26BD04863202
- HEAT_NO: 26BD04863
- IN_MAT_NO (方坯): 26BD04863002
- SG_SIGN (牌号): SWRCH22A
- SAMPLE_LOT_NO: SCDC26051462

严重程度总览


严重 1 | 偏离 16 | 正常 35 | -无基线- 1 | -无数据- 5

化学成分雷达图

化学成分雷达 (归一化到 p05-p95)

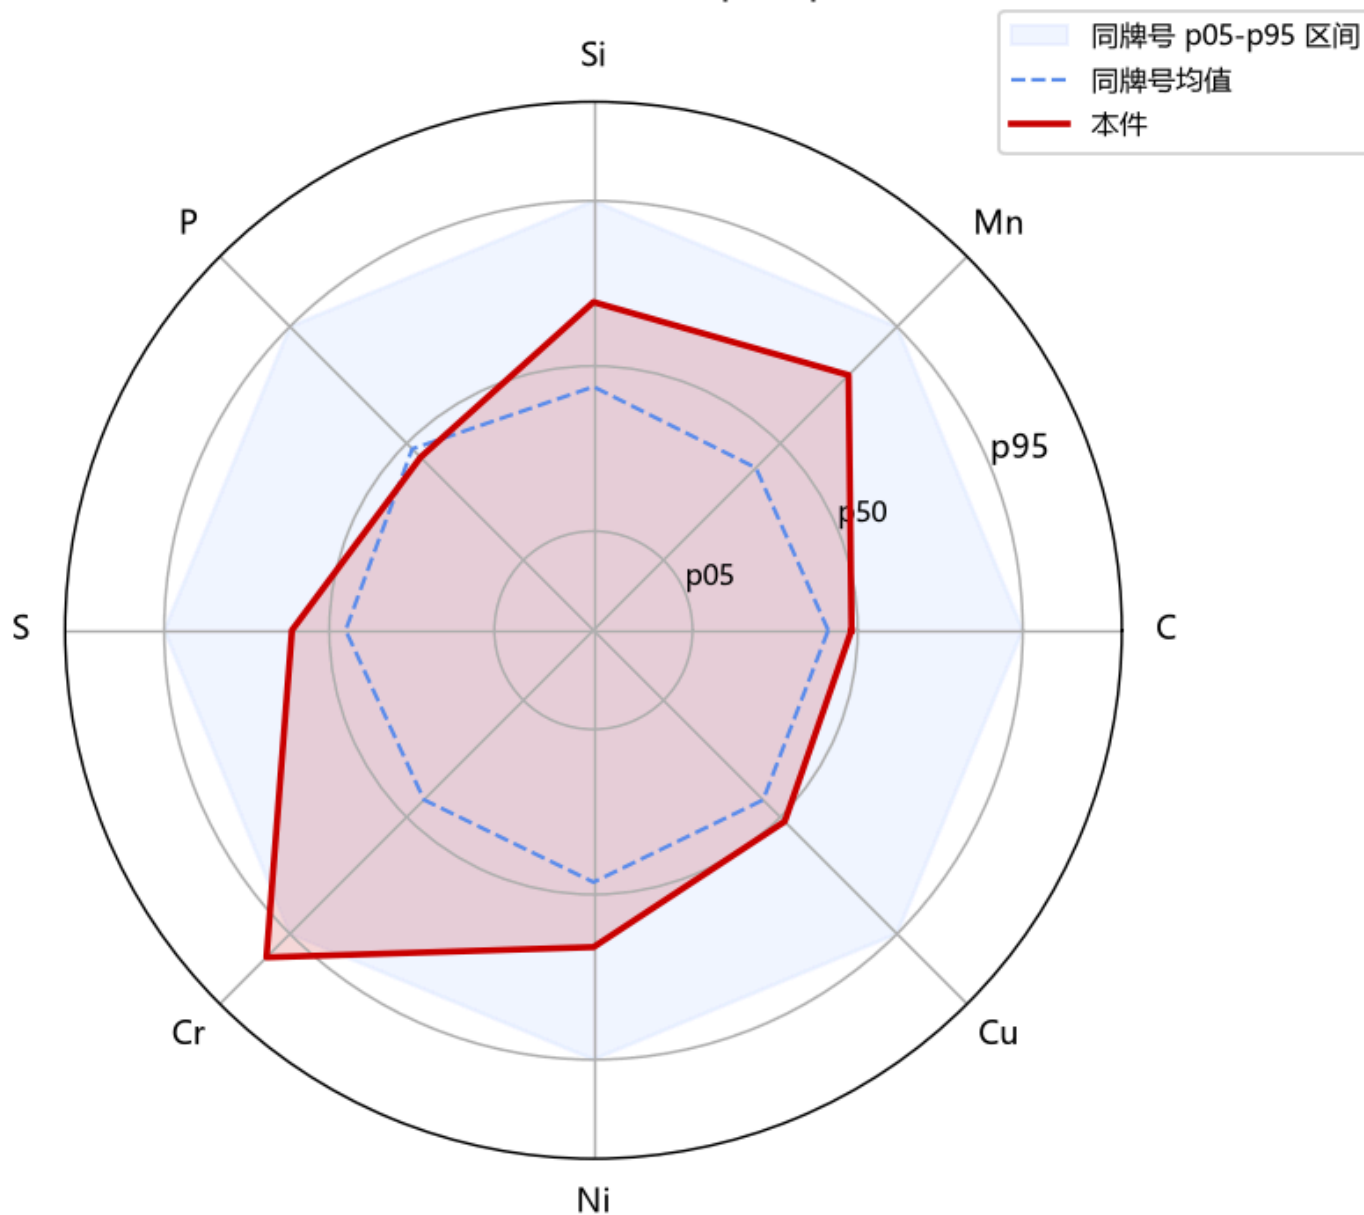

拉伸性能在整体分布中的位置

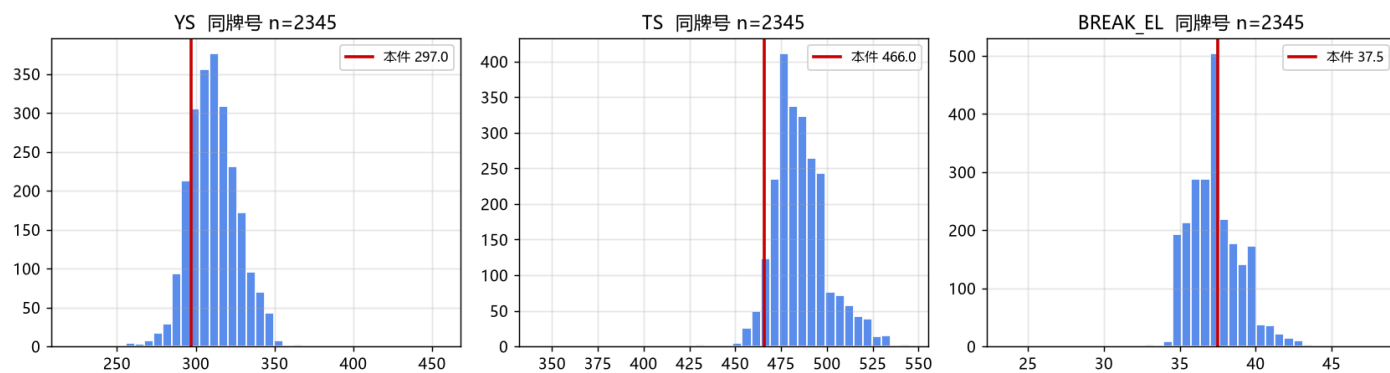

详细对比表

源	指标	实测	均值	std	p05	p95	z	评级
chemistry	La	0.001	0.000	0.000	0.00	0.00	+10.59	严重
chemistry	Ca	0.002	0.003	0.001	0.00	0.00	-1.92	偏离
chemistry	Al	0.024	0.031	0.004	0.03	0.04	-1.91	偏离
chemistry	Alt	0.024	0.031	0.004	0.03	0.04	-1.91	偏离
chemistry	Al_sol	0.022	0.030	0.004	0.02	0.04	-1.85	偏离
chemistry	Bi	0.000	0.001	0.000	0.00	0.00	-1.37	偏离
rolling	进预精轧温度(均值) (PRE_FM_TEMP)	1019.667	982.060	27.710	925.67	1016.33	+1.36	偏离
chemistry	Mn	0.798	0.766	0.024	0.73	0.81	+1.33	偏离
tensile	抗拉强度 (TS)	466.000	485.650	15.083	466.00	514.00	-1.30	偏离
heating	均热温度 (OAK_TEMP)	1073.000	1104.962	25.716	1065.00	1150.00	-1.24	偏离
chemistry	Cr	0.036	0.025	0.009	0.02	0.03	+1.15	偏离
rolling	轧制实际重量 (ROLL_ACT_WT)	2.162	2.252	0.079	2.16	2.35	-1.13	偏离
rolling	进精轧温度1(均值) (TEMP_FM_IN1)	922.000	900.880	20.169	867.67	931.67	+1.05	偏离
chemistry	Pb	0.001	0.000	0.001	0.00	0.00	+1.04	偏离
rolling	出炉温度(均值) (OUTFCE_TEMP)	974.333	984.903	10.154	970.33	1004.67	-1.04	偏离
rolling	开轧温度(均值) (BLOO_ROLL_TEMP)	974.333	985.062	10.320	970.33	1005.00	-1.04	偏离
heating	加热段温度 (HEAT_TEMP)	1022.000	1058.137	35.463	995.00	1106.00	-1.02	偏离
heating	入炉温度 (IN_FURNACE_TEMP)	54.000	142.051	93.173	33.00	308.00	-0.95	正常
chemistry	As	0.004	0.003	0.001	0.00	0.00	+0.94	正常
chemistry	Ce	0.003	0.002	0.001	0.00	0.00	+0.92	正常
rolling	入炉温度(均值) (INFCE_TEMP)	56.000	141.250	92.476	33.67	308.67	-0.92	正常
tensile	屈服强度 (YS)	297.000	311.438	15.786	289.00	338.00	-0.91	正常
chemistry	N	0.003	0.004	0.001	0.00	0.01	-0.91	正常
chemistry	Mo	0.004	0.002	0.001	0.00	0.01	+0.91	正常
chemistry	Si	0.035	0.029	0.008	0.02	0.04	+0.83	正常
chemistry	V	0.001	0.002	0.001	0.00	0.00	-0.82	正常
chemistry	Zr	0.000	0.001	0.000	0.00	0.00	-0.75	正常
chemistry	Ni	0.011	0.009	0.003	0.00	0.01	+0.63	正常
heating	总加热时间 (TOTOL_HEAT_TIME)	144.000	181.091	62.261	136.00	250.00	-0.60	正常

源	指标	实测	均值	std	p05	p95	z	评级
chemistry	S	0.004	0.003	0.001	0.00	0.00	+0.56	正常
chemistry	Sb	0.000	0.000	0.000	0.00	0.00	-0.49	正常
rolling	进减径机温度1(均值) (REDUDIA_TEMP1)	891.333	900.227	21.737	863.67	936.67	-0.41	正常
chemistry	Zn	0.001	0.001	0.001	0.00	0.00	-0.35	正常
rolling	备用字段_N4 (SPARE_ITEM_N4)	100.000	94.648	15.898	65.56	100.00	+0.34	正常
rolling	轧制时间 (ROLL_TIME)	145.000	165.258	60.669	145.00	191.00	-0.33	正常
chemistry	Cu	0.012	0.011	0.003	0.01	0.02	+0.27	正常
heating	预热段温度_001 (PRE_HEAT_TEMP)	699.000	683.968	56.741	571.00	753.00	+0.26	正常
finished	内径对角线2 (INDM_DGNL2)	6.630	6.611	0.073	6.43	6.70	+0.26	正常
chemistry	Sn	0.002	0.001	0.001	0.00	0.00	+0.26	正常
chemistry	B	0.000	0.000	0.000	0.00	0.00	+0.25	正常
chemistry	C	0.203	0.201	0.008	0.19	0.22	+0.23	正常
rolling	终轧温度1(均值) (FM_TEMP1)	856.667	837.401	83.681	613.00	917.67	+0.23	正常
finished	内径对角线1 (INDM_DGNL1)	6.450	6.466	0.078	6.38	6.66	-0.21	正常
rolling	备用字段_N3 (SPARE_ITEM_N3)	100.000	99.211	4.002	96.81	100.00	+0.20	正常
rolling	备用字段_N2 (SPARE_ITEM_N2)	100.000	99.247	3.843	96.86	100.00	+0.20	正常
chemistry	W	0.001	0.001	0.001	0.00	0.00	-0.17	正常
rolling	吐丝温度(均值) (LAYING_TEMP)	876.333	878.577	16.240	855.00	910.33	-0.14	正常
chemistry	Co	0.003	0.004	0.003	0.00	0.01	-0.13	正常
chemistry	P	0.013	0.013	0.002	0.01	0.02	-0.12	正常
tensile	断后伸长率 (BREAK_EL)	37.500	37.314	1.739	35.00	40.50	+0.11	正常
chemistry	Ti	0.002	0.002	0.002	0.00	0.00	-0.01	正常
chemistry	Nb	0.001	0.001	0.001	0.00	0.00	-0.01	正常
rolling	轧制根数 (ROLL_MAT_NUM)	1.000	1.000	0.000	1.00	1.00	-	-无 基 线-

无数据指标 (5)

强屈比 (TENSILE_RATE), 终轧速度 (WR_FIN_RL_OT_SPD), 减定径出口侧速度 (REDUDIA_OT_SPD), 出炉温度_001 (OUT_FURNACE_TEMP), 内径对角线差值 (INDM_DGNL_DIF)

拉伸试验原始记录

试批号 (SAMPLE_LOT_NO)	屈服强度 (YS)	抗拉强度 (TS)	断后伸长率 (BREAK_EL)	强屈比 (TENSILE_RATE)	判定
SCDC26051462	297.0	466.0	37.5	0.000	-