


整体数据分析报告

生成时间: 2026-07-13 22:21:49

数据规模

- 轧材总量: 8,259,019 支
- 牌号数量: 45 种
- 前 3 牌号: HRB400E, ML08Al, 30MnSi

牌号占比

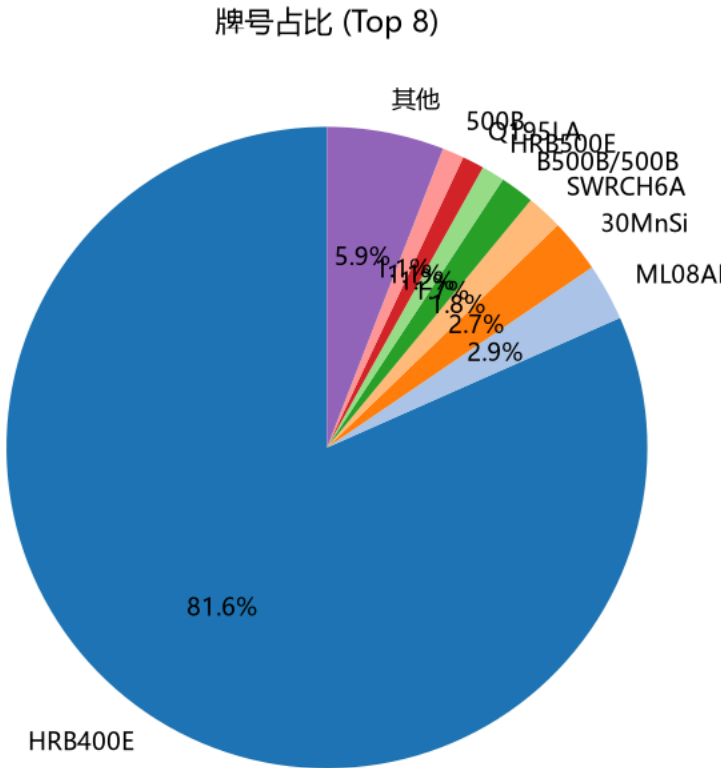

关键指标概览

拉伸性能 (mean±std, n)

牌号	屈服强度 (YS)	抗拉强度 (TS)	断后伸长率 (BREAK_EL)	强屈比 (TENSILE_RATE)
HRB400E	449.86±12.70 n=222203	613.66±25.81 n=222203	24.13±2.86 n=222203	1.36±0.05 n=222145
ML08Al	250.98±18.45 n=731	362.43±11.78 n=731	44.63±3.84 n=731	1.45±0.10 n=592
30MnSi	-	-	-	-

化学成分 (mean±std, n)

牌号	C	Mn	Si	P	S	Ceq
HRB400E	0.23±0.01 n=68324	1.33±0.05 n=68324	0.39±0.15 n=68324	0.03±0.01 n=68324	0.02±0.01 n=68324	0.47±0.01 n=68146
ML08Al	0.07±0.01 n=2591	0.36±0.02 n=2591	0.03±0.01 n=2591	0.01±0.00 n=2591	0.00±0.00 n=2591	-

牌号	C	Mn	Si	P	S	Ceq
30MnSi	0.31±0.01 n=2393	0.99±0.02 n=2393	0.84±0.09 n=2393	0.02±0.00 n=2393	0.01±0.00 n=2393	-

轧制温度 (mean±std, n)


牌号	入炉温度(均值) (INFCE_TEMP)	出炉温度(均值) (OUTFCE_TEMP)	开轧温度(均值) (BLOO_ROLL_TEMP)	进预精轧温度(均 值) (PRE_FM_TEMP)	进精轧温度1(均 值) (TEMP_FM_IN1)	进减径机温度1(均值) (REDUDIA_TEMP1)	终轧温度1(均 值) (FM_TEMP1)	吐丝温度 (LAYING_
HRB400E	615.17±260.60 n=3353162	1010.96±13.95 n=3819746	1007.28±31.10 n=6582351	987.40±153.36 n=6211083	807.77±128.42 n=6295277	883.03±34.17 n=2159474	862.10±98.52 n=5327242	893.78 n=
ML08Al	254.81±226.15 n=218462	974.36±29.21 n=231142	974.84±29.61 n=235294	988.38±43.51 n=206775	918.04±46.69 n=203777	934.69±29.69 n=205757	888.70±80.63 n=185677	916.13 n=
30MnSi	290.35±178.57 n=108660	1016.94±10.61 n=132103	1015.96±36.68 n=221138	1037.15±67.98 n=220108	893.47±144.67 n=201865	941.29±23.59 n=203934	876.38±62.50 n=206459	902.18 n=

轧制其它与加热工艺 (mean±std, n)

牌号	轧制时间 (ROLL_TIME)	轧制根数 (ROLL_MAT_NUM)	轧制实际重量 (ROLL_ACT_WT)	终轧速度 (WR_FIN_RL_OT_SPD)	减定径出口侧速度 (REDUDIA_OT_SPD)	备用字段_N2 (SPARE_ITEM_N2)	备用字段_N3 (SPARE_ITEM_N3)
HRB400E	91.37±175.68 n=6668186	1.00±0.00 n=6721736	2.43±7.74 n=6741625	18.78±13.08 n=5415937	-	99.90±2.86 n=39960	99.90±2.86 n=39946
ML08Al	145.76±79.96 n=236530	1.00±0.00 n=236858	2.32±0.08 n=236900	86.96±22.52 n=4195	-	99.11±4.96 n=136743	98.95±5.60 n=135792
30MnSi	184.89±123.14 n=222563	1.00±0.00 n=222723	2.45±0.04 n=223066	48.99±11.88 n=79433	-	99.51±2.00 n=24773	99.33±3.03 n=24767


牌号 [HRB400E]

拉伸性能分布

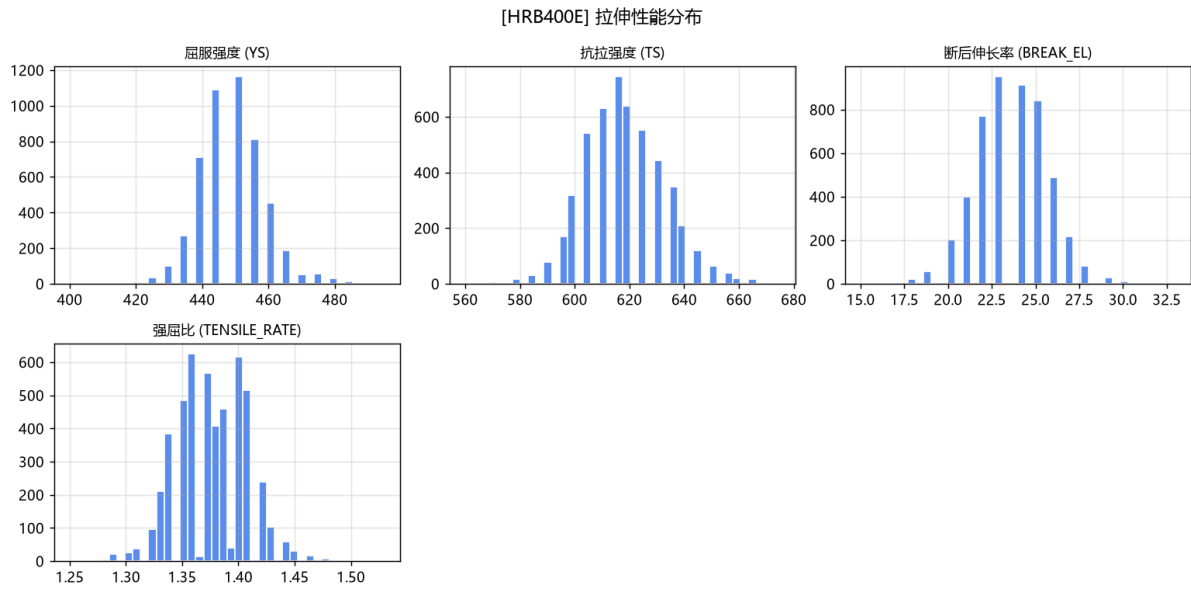


化学成分分布

[HRB400E] 化学成分分布

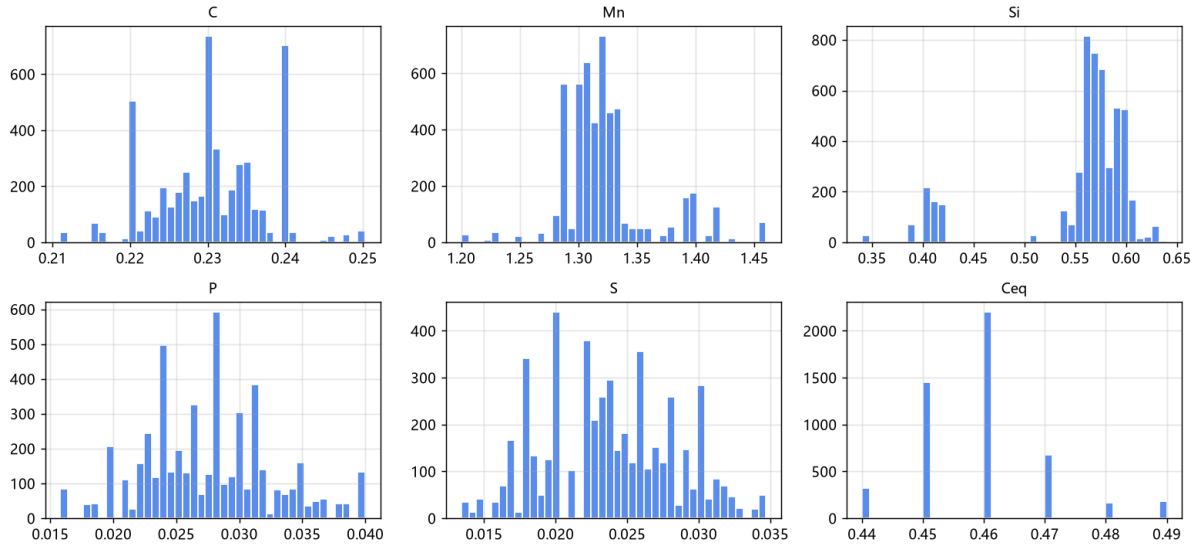


轧制工艺分布

[HRB400E] 轧制工艺分布

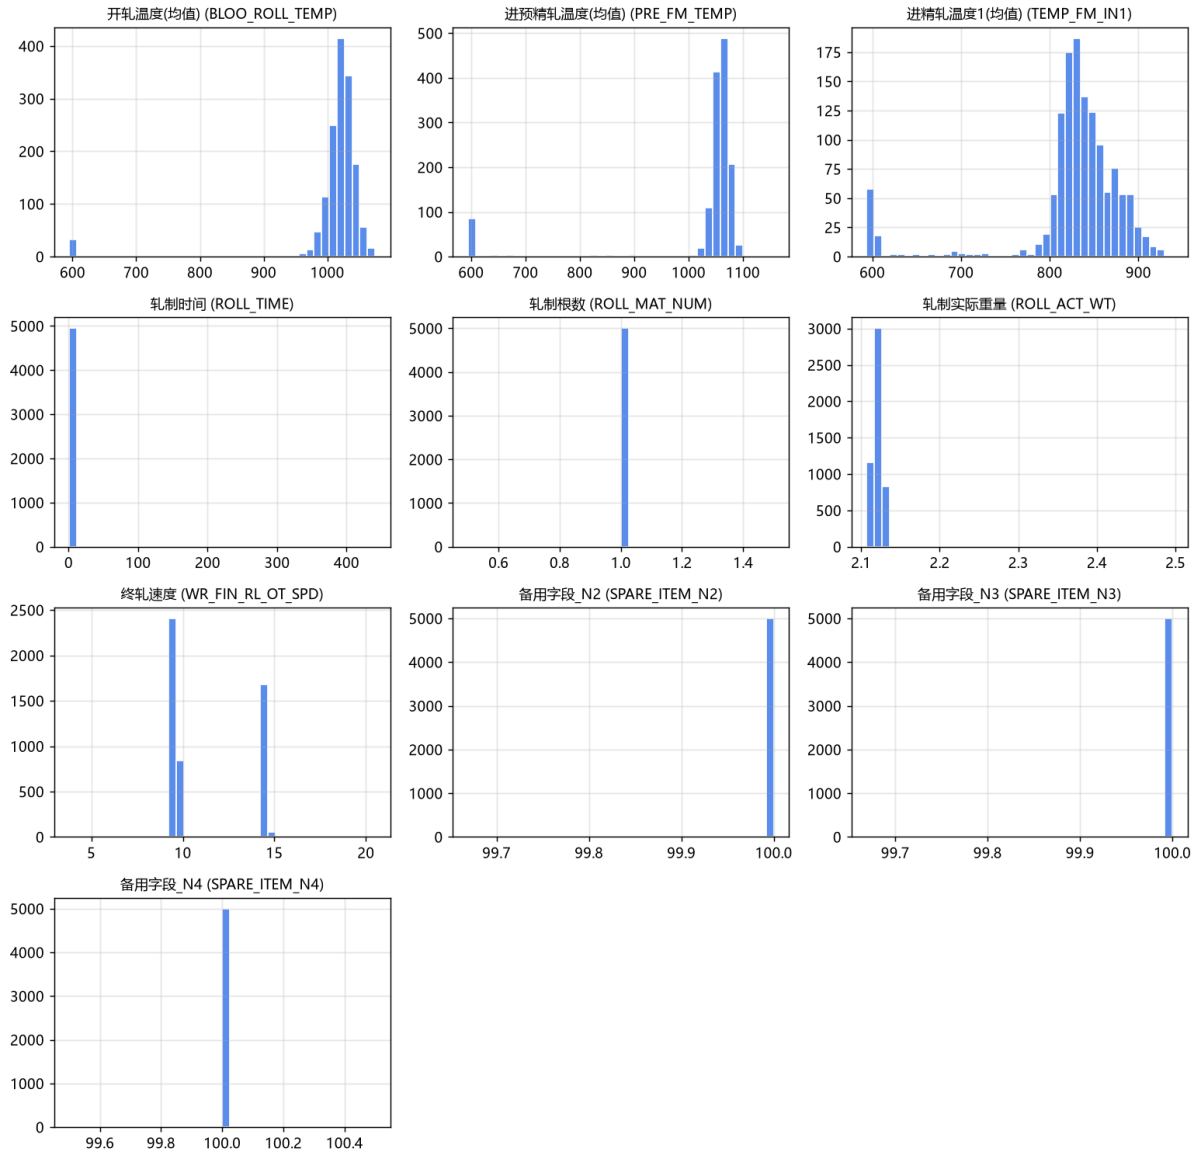


加热工艺分布

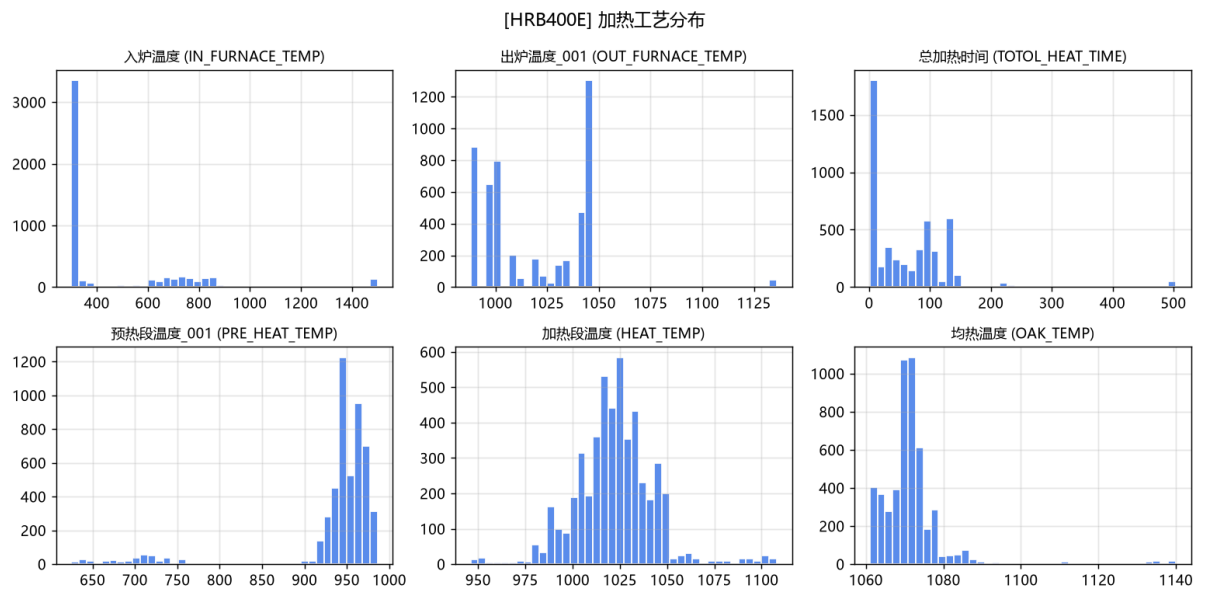


牌号 [ML08AI]

拉伸性能分布

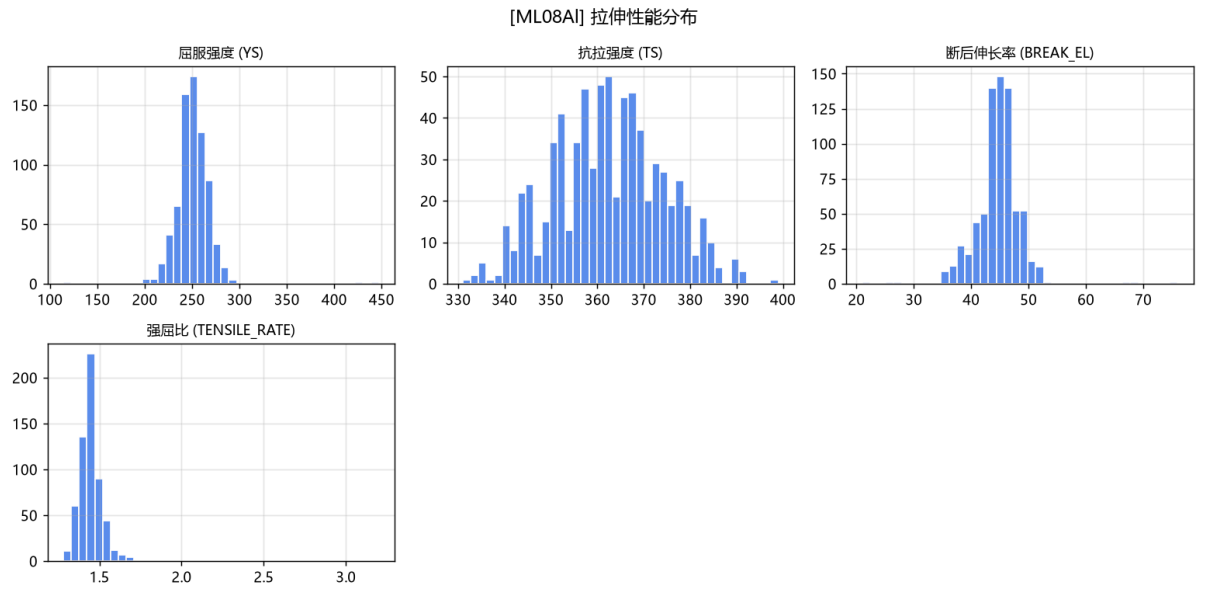


化学成分分布

[ML08AI] 化学成分分布

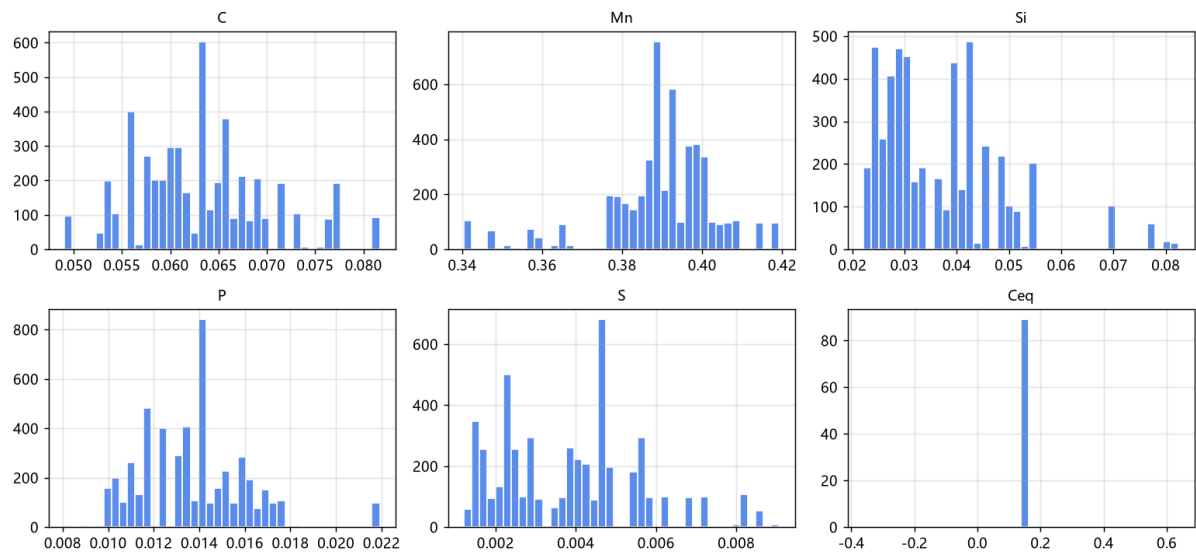


轧制工艺分布

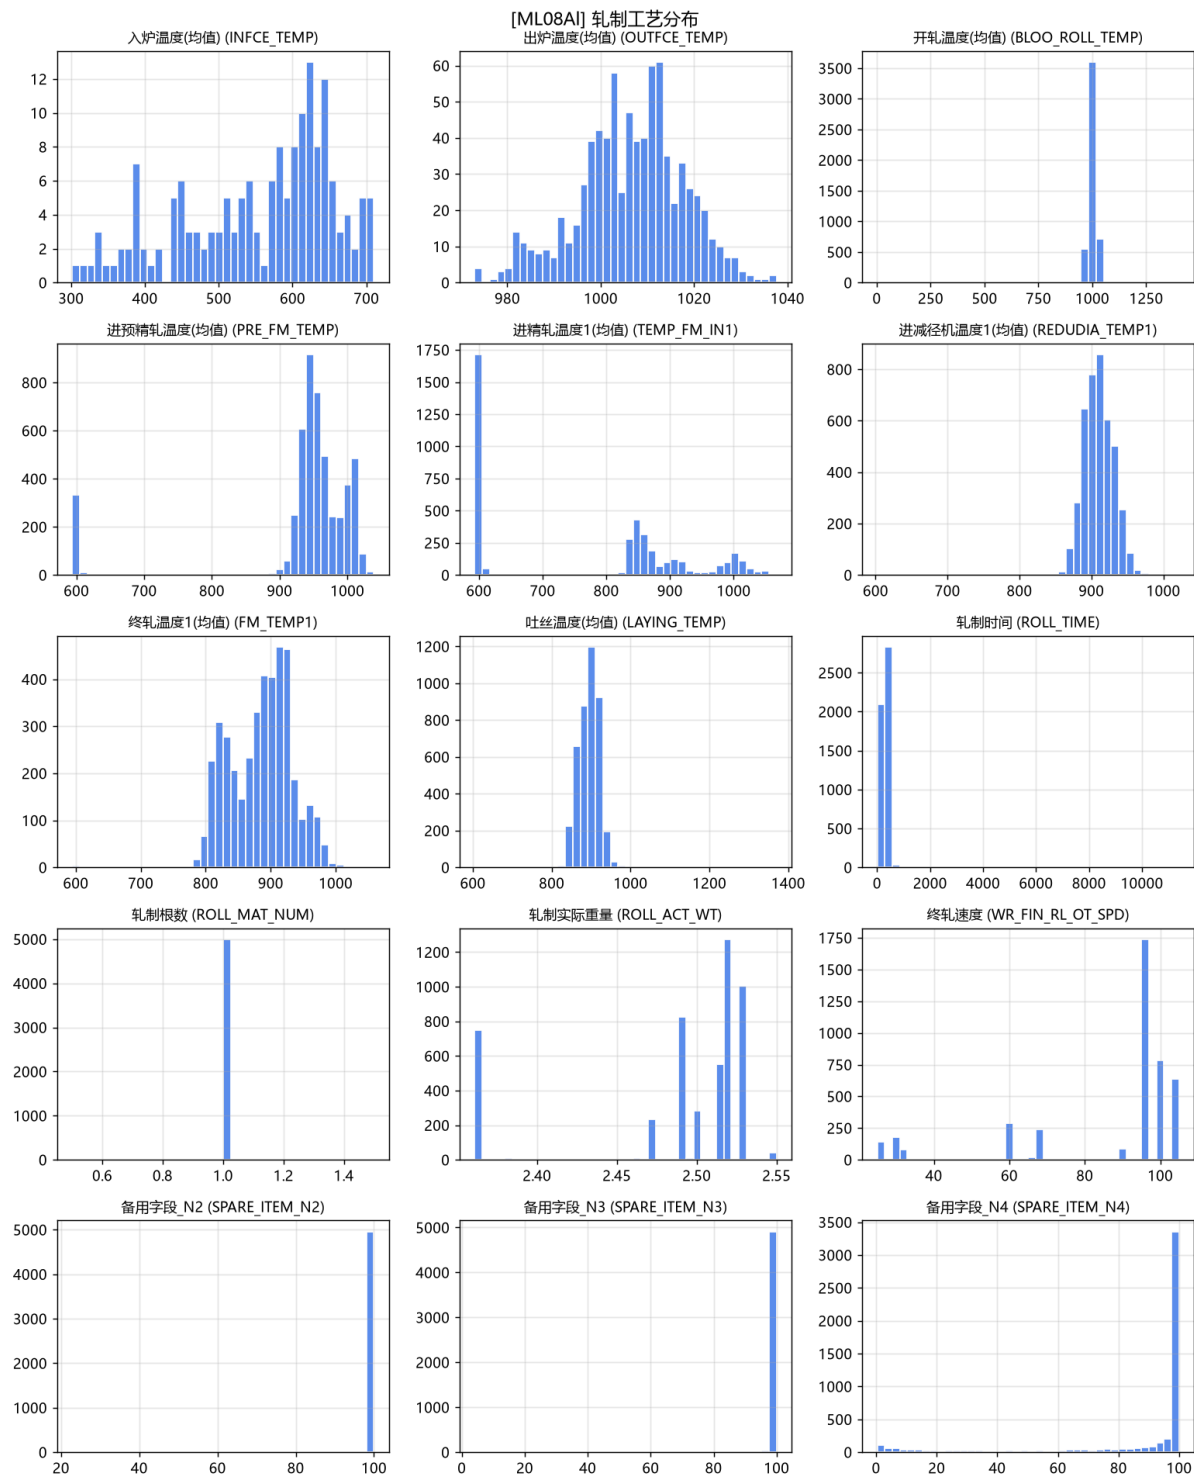

加热工艺分布


[ML08AI] 加热工艺分布

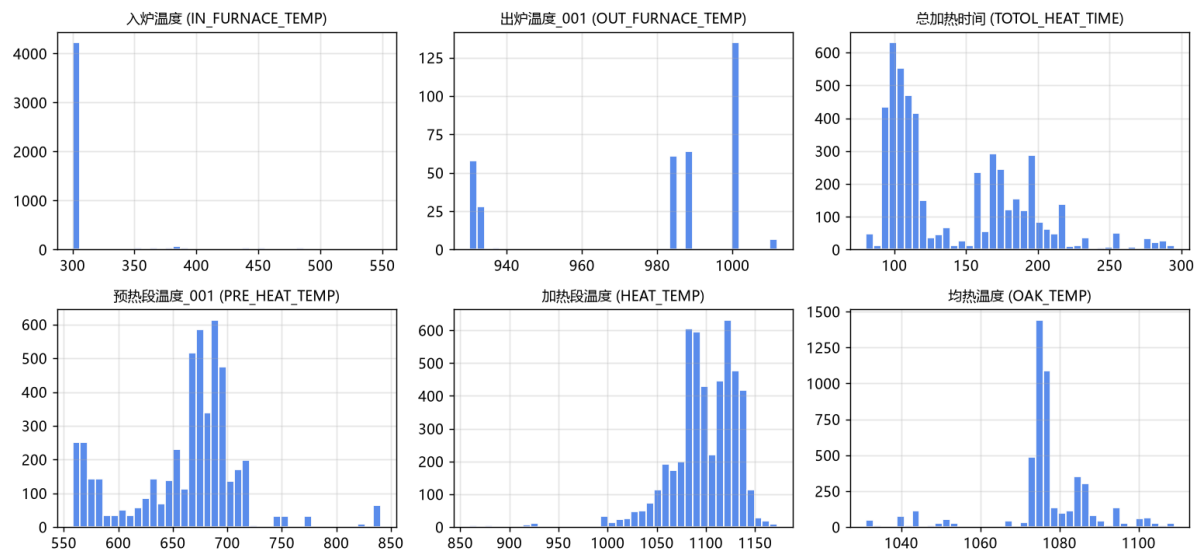


牌号 [30MnSi]

化学成分分布

[30MnSi] 化学成分分布

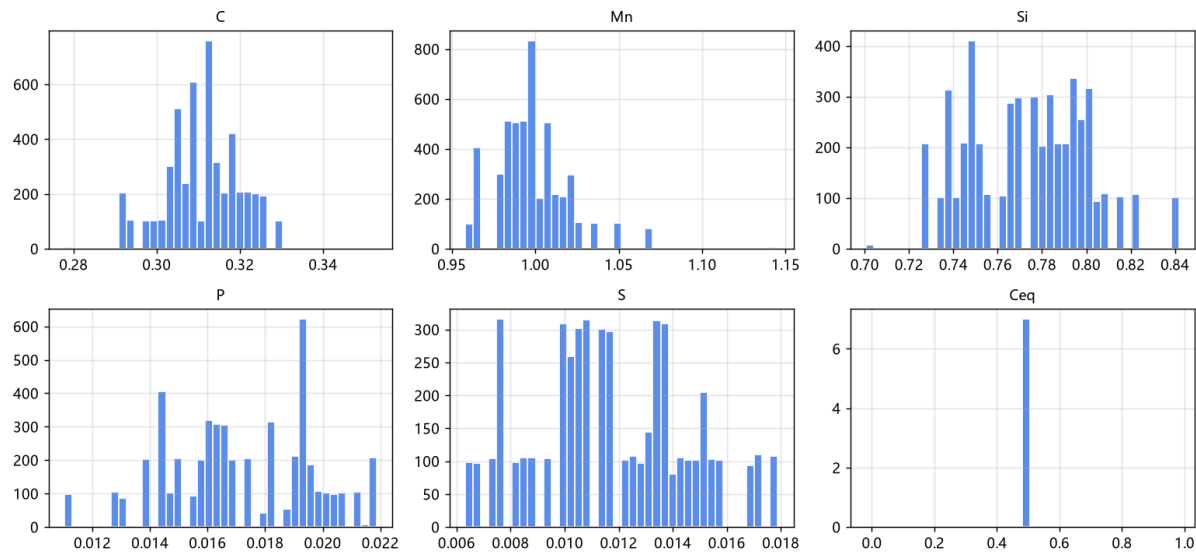

轧制工艺分布

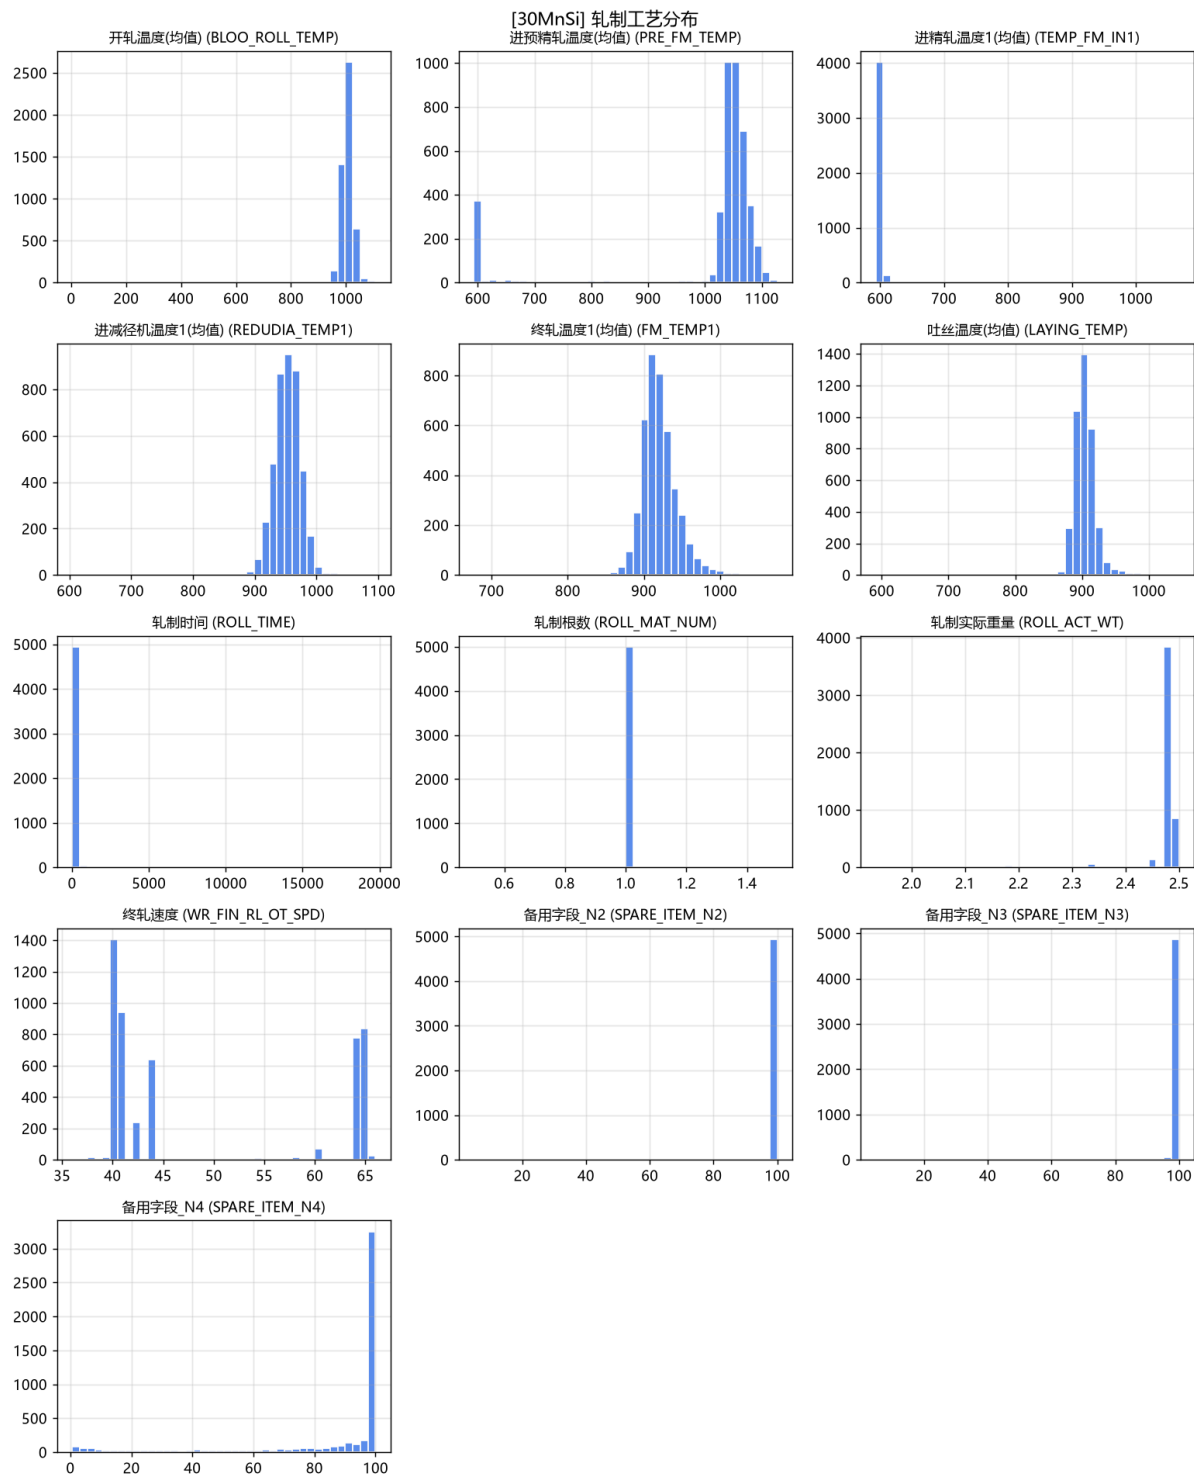

加热工艺分布

[30MnSi] 加热工艺分布

