



**ASTM D6007-22 Small Chamber Testing of
Composite Wood Products
CARB ATCM & EPA TSCA VI Program
for
Nam Huy Trading Limited Company**

General

The Shanghai Hongjun Science & Technology VN Office, performed client requested formaldehyde emission test of panel products according to general guidelines of ASTM D6007-22, **“Standard Test Method for Determining Formaldehyde Concentrations in Air from Wood Products Using a Small-Scale Chamber.”**

Test Specimen Data

The samples were selected at the manufacturing facility by manufacture. They were individually wrapped and shipped. The samples remained sealed and stored in a room maintained at $t \pm 5\%$ RH, $24 \pm 3^\circ\text{C}$ ($75 \pm 5^\circ\text{F}$) prior to testing. The formaldehyde background concentration in the air where the specimens were conditioned was documented at <0.01 ppm.

Mill Name:	Nam Huy Trading Limited Company		
Mill No.:	ES-127	Products Type:	HWPW-VC
Mfg. Date	2024.12.04	Sample Size:	247*146*18mm – 11 plies (3 PCS)
Rcvd. Date:	2024.12.05	Product/Batch ID:	04122024
Conditioning Time	6 days	Test Type	Entrusted Test

Test Method and Results

The samples were placed in the chamber (volume = 0.2 m^3) with all edges sealed with aluminum tape, and the chamber was maintained at $25 \pm 1^\circ\text{C}$ and $50 \pm 4\%$. The formaldehyde concentration of make-up air and the chamber were both measured at <0.02 ppm. After allow time for no less than three full air changes, air samples were drawn at a rate of $1\text{L}/\text{min} \pm 0.05\text{L}/\text{min}$ for 30 minutes. Emission values were determined with spectrophotometer analysis 7230G. The Formaldehyde Emissions are corrected to an emission level at standard conditions (50% RH and 77°F).

Sample No.	Small Chamber Test No.	Test Date	Chamber Q/A Ratio	Thickne ss	Total Exposed Area	Flow	Time	Temp.	RH	Formaldehyde Emission
			(m^3/h)/ m^2	mm	m^2	L/min	h	$^\circ\text{C}$	%	ppm
QT-241211-2	CB2	2024-12-11	1.172	18	0.216	4.226	2.87	24.67	53.20	0.030
Result										0.030
The ASTM D6007-22 test result MEET the §770.10 of 40 CFR Part 770 (EPA TSCA Title VI) & CARB 93120, Table1, Phase 2 limitation of 0.05ppm for HWPW-VC, HWPW-CC; 0.11ppm for MDF and 0.13ppm for t-MDF; 0.09ppm for PB.										

This testing report is responsible for the received samples only, where the sample pictures are attached in this report appendix.

TEST REPORT DUPLICATION


This test report shall not be reproduced, except in full, without the written approval of SHST.

Approved: *Phan Anh*
Date: 2024-12-11

Prepared: *Nam*
Date: 2024-12-11

Tester: *Canh*
Date: 2024-12-11

Test Report Appendix---Sample Picture

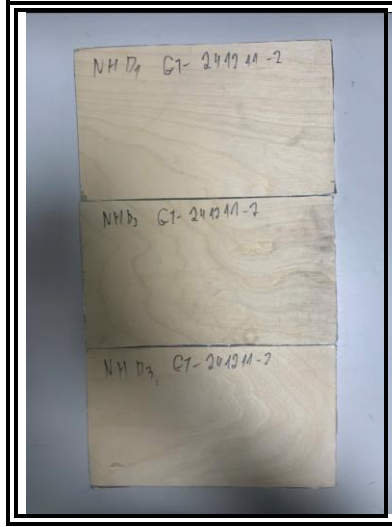

----- Report End -----