
VIEW ON THE TOP FACE 1.5:1

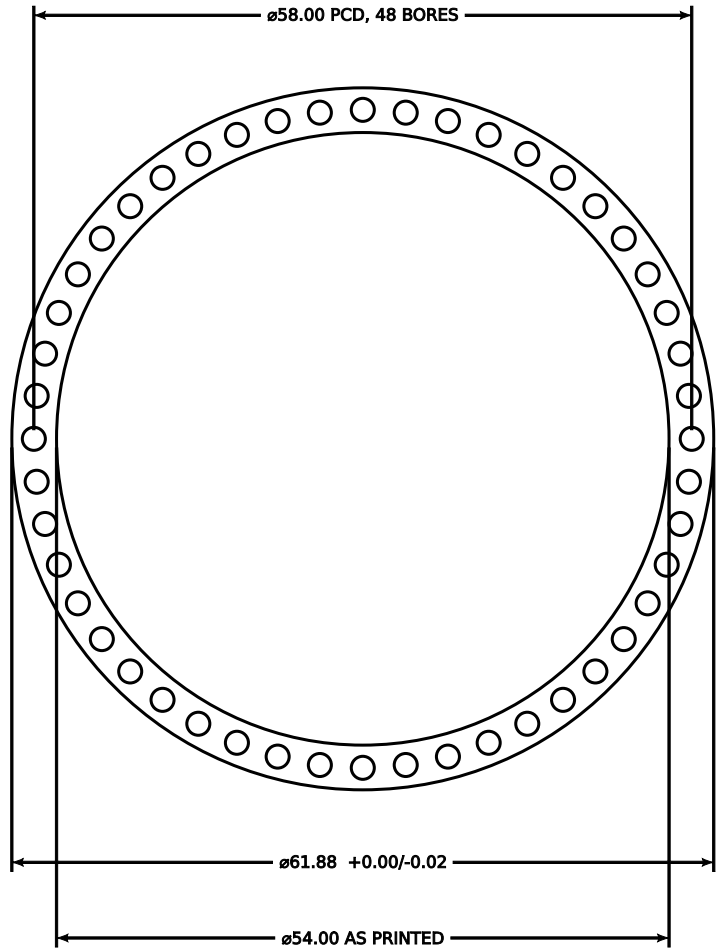

MATERIAL: PA12-GF (SLS) ONLY. STOCK: printed blank. print solid, then ream / turn.
GENERAL TOLERANCE ISO 2768-m; UNMARKED EDGES DEBURRED.
DIMENSIONS IN MM FROM THE BOTTOM FACE AND THE AXIS.
DO NOT SCALE THE DRAWING; TAKE DIMENSIONS FROM THE FIGURES.

48x ø2.03 +0.01/-0.00 THRU, EQUALLY SPACED ON THE ø58.00 PCD.
POSITION: PATTERN ø0.05 TO A AND B, BORE TO BORE ø0.07. RFS, NO MMC.
REAM TO THE MEASURED LOT: BORE = 0.02 BIN FLOOR + 0.04 (ø2.03 FOR 1.99-2.01).
A = EITHER FACE (SYMMETRIC). B = ø61.88 OUTSIDE CYLINDER.
THICKNESS 1.95 AS PRINTED; FLAT WITHIN 0.05 OVER THE FULL FACE.
DO NOT PRINT THE BORES OR THE OD. Print the blank solid and machine
both: a printed hole holds +/-0.3 at best, which cannot locate a
magnet and at the low end will not admit one.
Hold on the printed ID to turn the OD, then take the bore pattern
from the OD, so the pattern and datum B share one setup.
THE BORES LOCATE THE MAGNETS. Micrometer the lot, take the densest
0.02 bin and ream to its floor + 0.04 (2.03 shown, for 1.99-2.01):
0.010-0.025 radial clearance.
PA12-GF ONLY: unfilled PA12 or SLA resin closes the OD clearance
below 60 C. Keep the part and the magnets below 60 C at every stage.

DESIGNED BY: dial-me-spinner / hardware-as-code	magnet shim	
DATE: 2026-10-23	PA12-GF (SLS) ONLY rev A 1.5:1 THK 1.95	
SCALE: 1:0.667	DRAWING NUMBER: DMS-07A	SHEET: 1