
Baird

Author: semclass
Creation: 04/21/2026 4:23:30 PM


Sample Name: Si-100

Area 3


Live Map 1

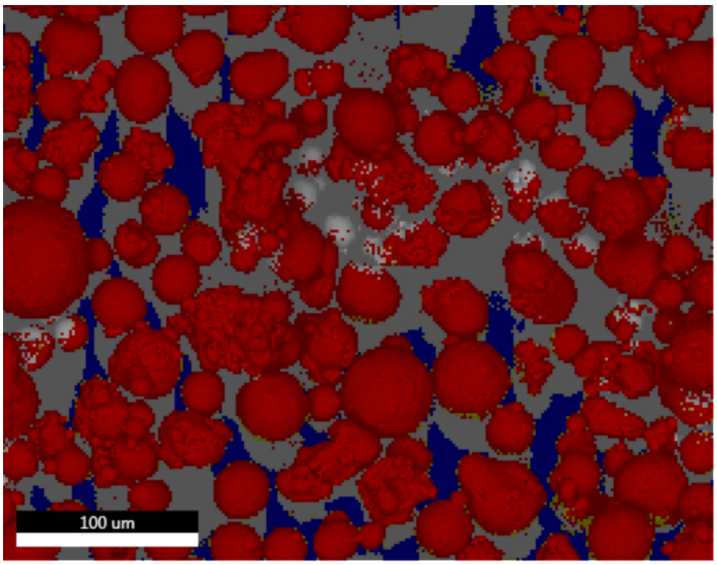

1% AlK/C K (538 Pixels)
7% C K/O K/AlK (3511 Pixels)
70% AlK (35615 Pixels)
23% Unallocated (11536 Pixels)




Notes:

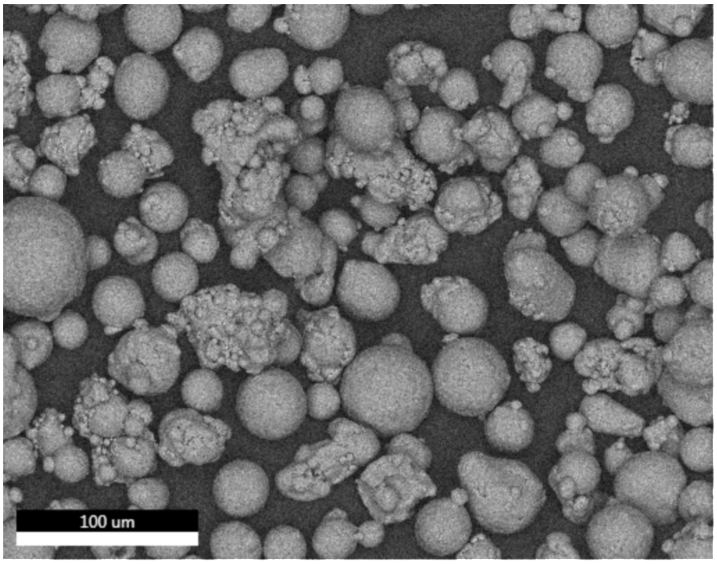

Image

ElementOverlay

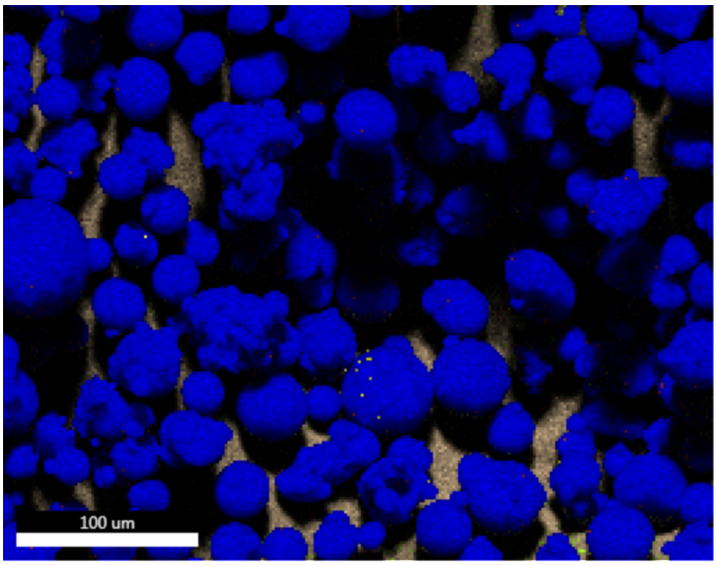


9% C K

1% O K


2% MgK

83% AlK


5% SiK

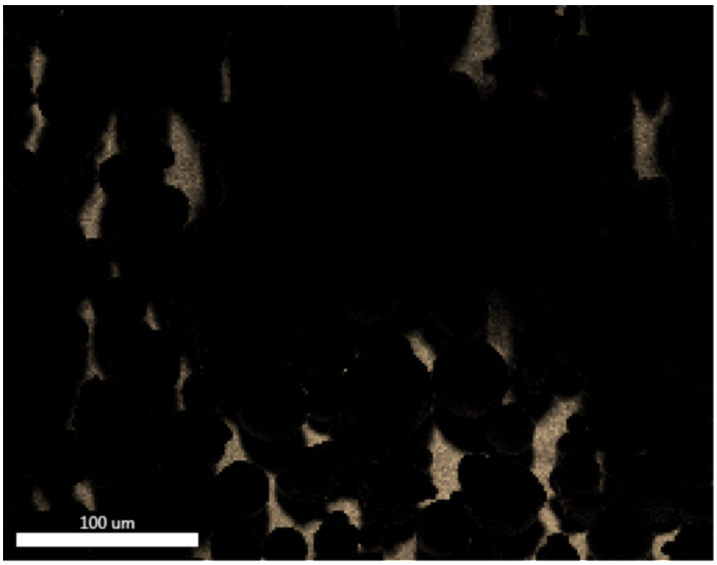


C K_ROI (107)

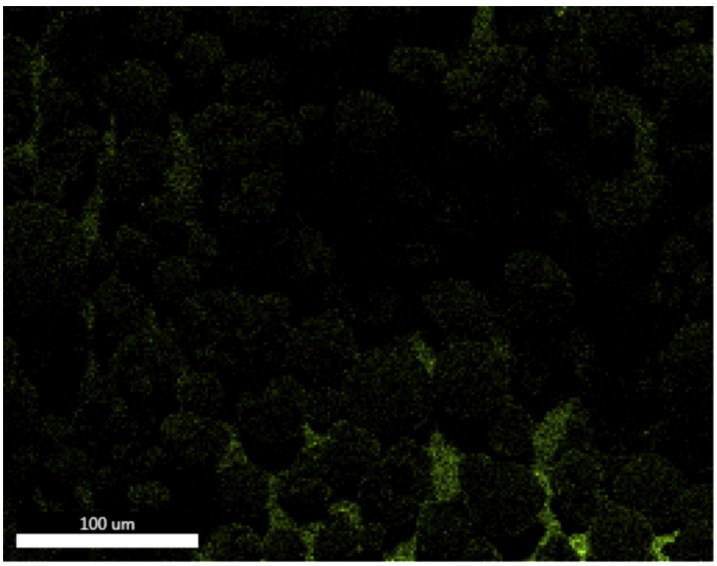


O K_ROI (29)

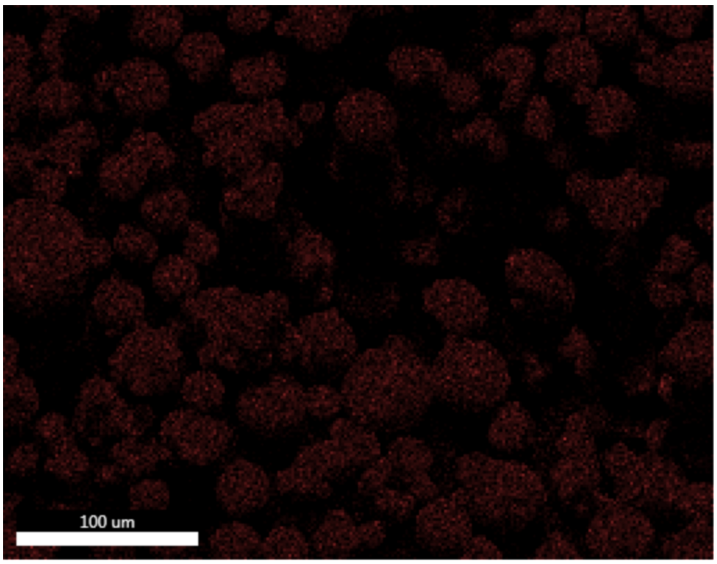

MgK_ROI (18)

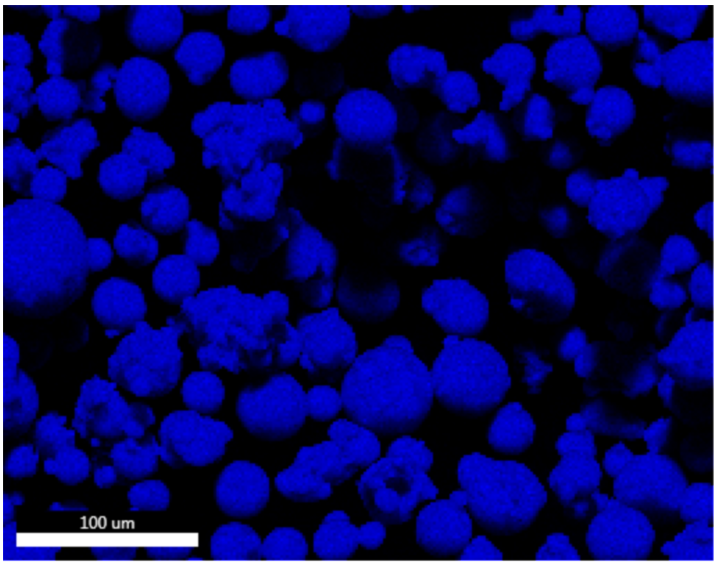


AlK_ROI (305)

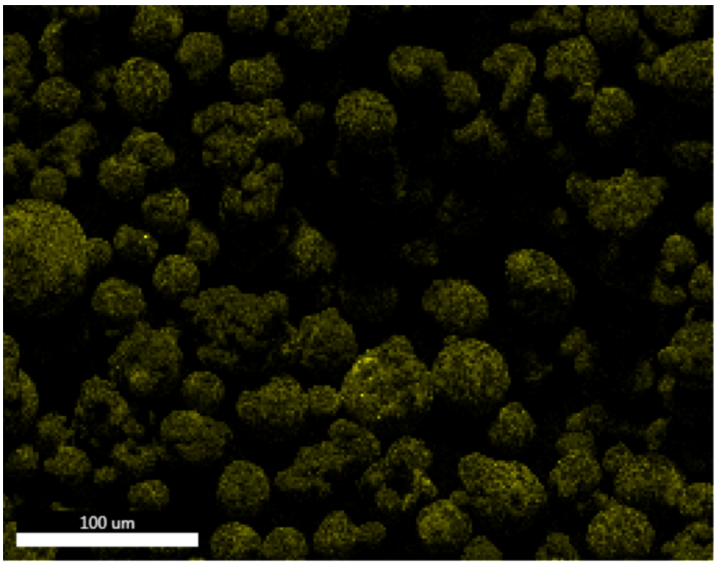

SiK_ROI (93)

kV:	15	Mag: 1001	Takeoff: 35.1	Live Time(s): 501.8	Amp Time(µs): 1.92	Resolution:(eV) 130.4

Sum Spectrum

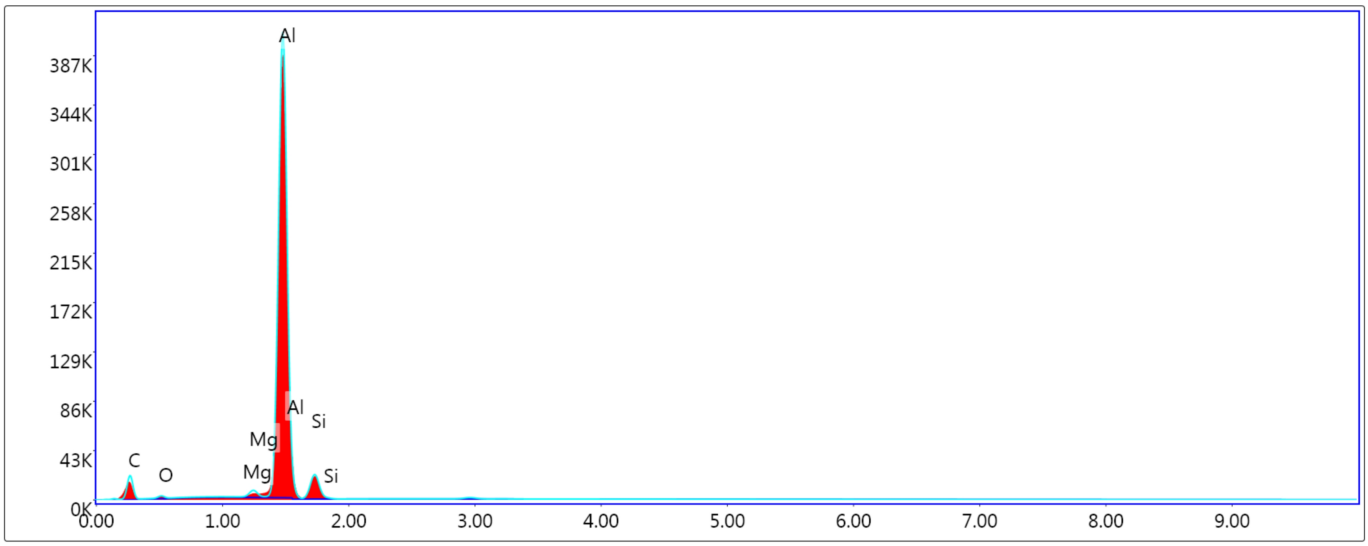


Lsec: 501.8 3.561K Cnts 0.515 keV Det: Octane Plus

eZAF Smart Quant Results

Element	Weight %	Atomic %	Net Int.	Error %	Kratio	Z	A	F
C K	34.41	53.77	460.20	10.07	0.0505	1.1096	0.1322	1.0000
O K	1.44	1.69	63.30	10.00	0.0036	1.0569	0.2360	1.0000
MgK	0.88	0.68	201.00	2.99	0.0077	0.9698	0.8873	1.0106
AlK	58.22	40.49	13171.70	1.86	0.5160	0.9327	0.9493	1.0012
SiK	5.05	3.38	712.10	5.46	0.0295	0.9519	0.6124	1.0006

kV: 15	Mag: 1001	Takeoff: 35.1	Live Time(s): 5.3	Amp Time(µs): 1.92	Resolution:(eV) 130.4

Phase: **AlK/C K**

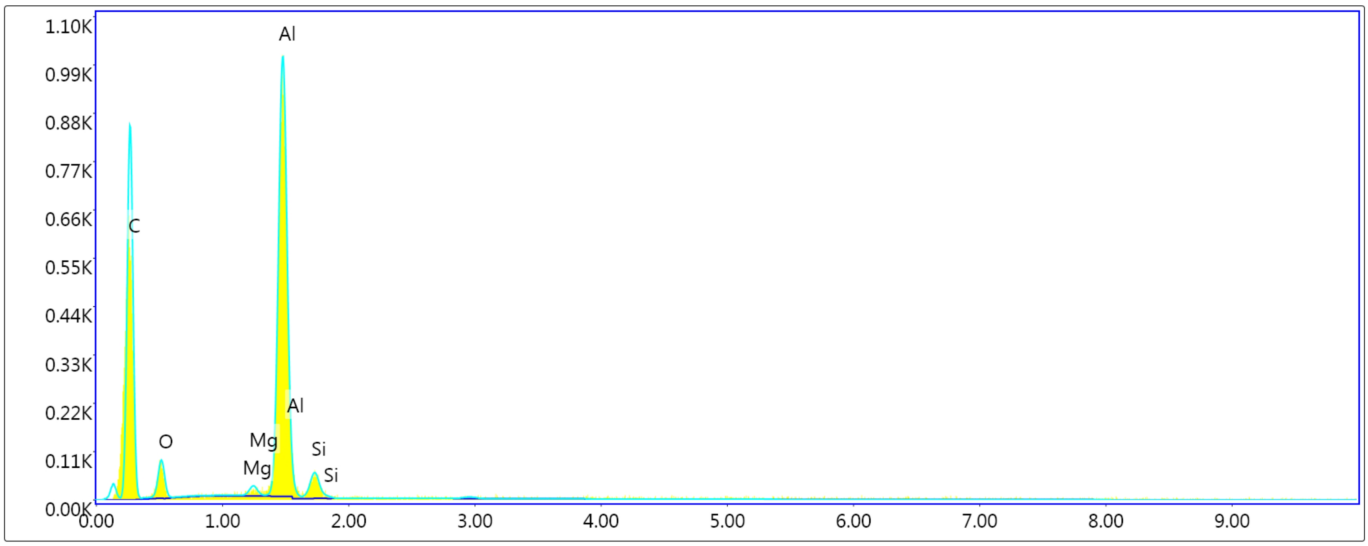


Lsec: 5.3 86 Cnts 0.515 keV Det: Octane Plus

eZAF Smart Quant Results

Element	Weight %	Atomic %	Net Int.	Error %	Kratio	Z	A	F
C K	70.58	81.89	1820.60	8.90	0.2480	1.0371	0.3388	1.0000
O K	8.20	7.14	210.20	14.44	0.0148	0.9861	0.1832	1.0000
MgK	0.52	0.30	80.40	14.59	0.0038	0.9031	0.8081	1.0077
AlK	19.55	10.10	3147.80	3.22	0.1531	0.8682	0.9007	1.0018
SiK	1.16	0.57	161.90	13.52	0.0083	0.8859	0.8111	1.0022

kV: 15	Mag: 1001	Takeoff: 35.1	Live Time(s): 34.4	Amp Time(µs): 1.92	Resolution:(eV) 130.4

Phase: **C K/O K/AlK**

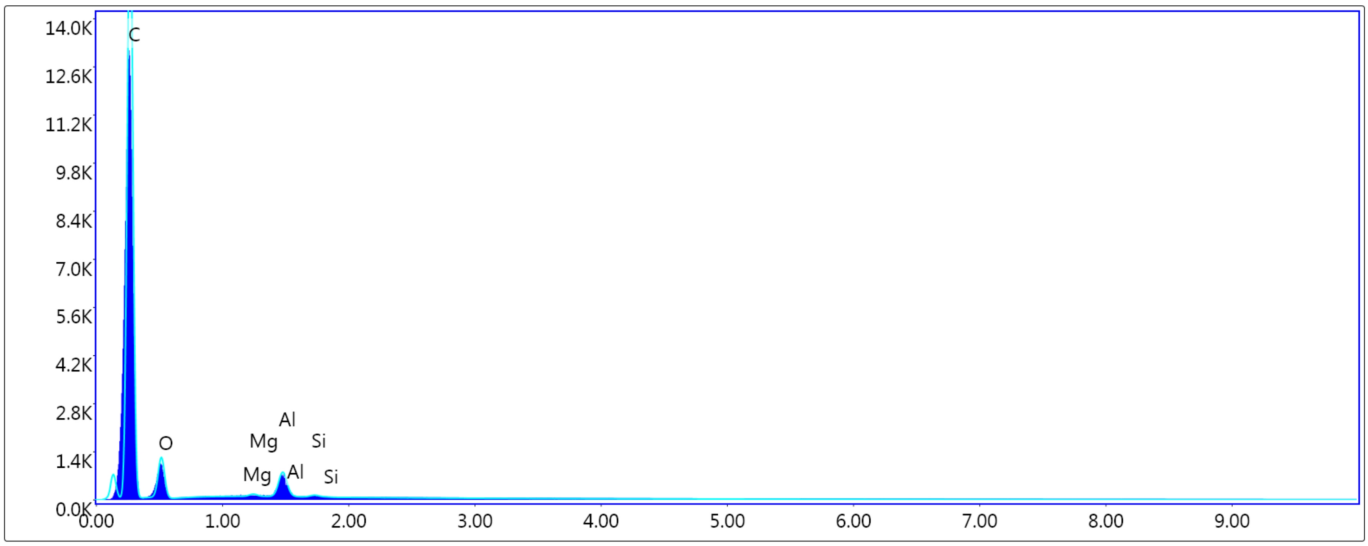


Lsec: 34.4 1.038K Cnts 0.515 keV Det: Octane Plus

eZAF Smart Quant Results

Element	Weight %	Atomic %	Net Int.	Error %	Kratio	Z	A	F
C K	83.43	87.62	5775.60	3.71	0.6492	1.0102	0.7702	1.0000
O K	14.42	11.37	412.30	11.37	0.0240	0.9598	0.1731	1.0000
MgK	0.18	0.10	31.80	17.24	0.0012	0.8781	0.7679	1.0033
AlK	1.84	0.86	339.90	4.32	0.0136	0.8440	0.8759	1.0036
SiK	0.13	0.06	24.10	27.81	0.0010	0.8611	0.9294	1.0055

kV: 15	Mag: 1001	Takeoff: 35.1	Live Time(s): 349	Amp Time(µs): 1.92	Resolution:(eV) 130.4

Phase: AlK

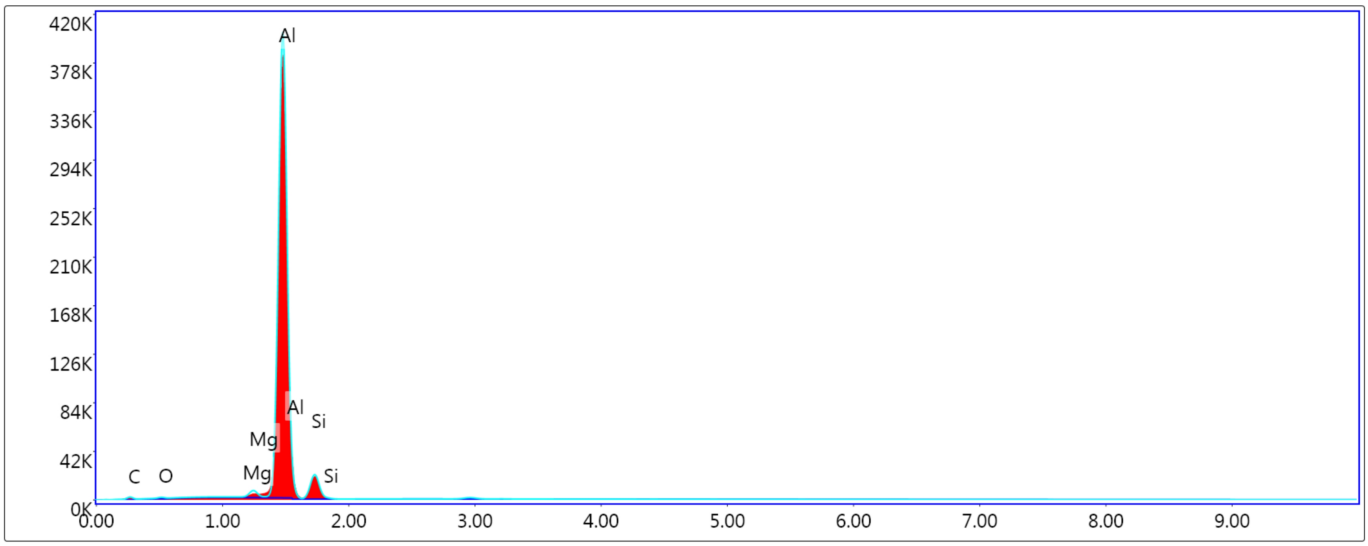


Lsec: 349.0 2.404K Cnts 0.515 keV Det: Octane Plus

eZAF Smart Quant Results

Element	Weight %	Atomic %	Net Int.	Error %	Kratio	Z	A	F
C K	6.70	13.87	61.20	11.36	0.0073	1.1676	0.0927	1.0000
O K	0.60	0.94	33.50	10.92	0.0021	1.1134	0.3048	1.0000
MgK	1.09	1.11	254.30	2.64	0.0105	1.0228	0.9319	1.0114
AlK	82.78	76.27	18771.90	1.61	0.7949	0.9837	0.9749	1.0013
SiK	8.82	7.81	1030.10	6.32	0.0461	1.0042	0.5201	1.0003

kV: 15	Mag: 1001	Takeoff: 35.1	Live Time(s): 113.1	Amp Time(µs): 1.92	Resolution:(eV) 130.4

Phase: **Unallocated**

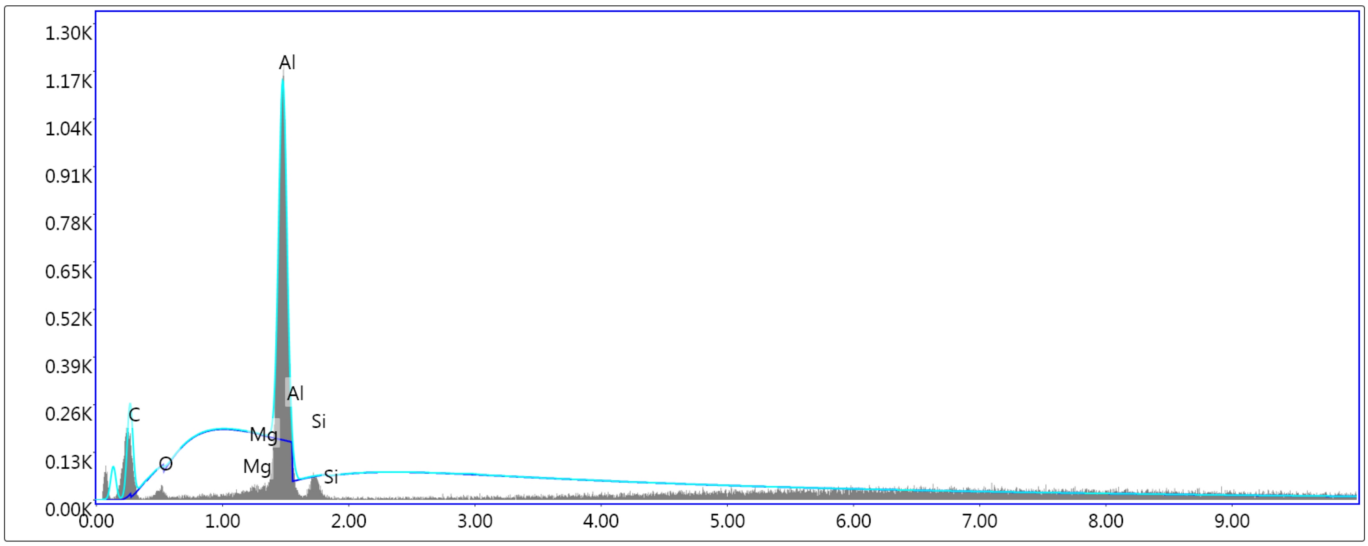

Lsec: 113.1 31 Cnts 0.515 keV Det: Octane Plus

eZAF Smart Quant Results

Element	Weight %	Atomic %	Net Int.	Error %	Kratio	Z	A	F
C K	63.34	79.51	25.20	11.51	0.1514	1.0593	0.2256	1.0000
O K	0.00	0.00	0.00	99.99	0.0000	1.0078	0.1852	1.0000
MgK	0.00	0.00	0.00	99.99	0.0000	0.9236	0.8561	1.0098
AlK	36.66	20.48	142.80	3.23	0.3063	0.8880	0.9400	1.0007
SiK	0.00	0.00	0.00	99.99	0.0000	0.9062	0.7215	1.0013