

Bayesian Optimization of Multi-Material 3D-Printed Tensegrity-Inspired Structures for Energy Absorption

Marcus E. Madsen*

Department of Mechanical Engineering,
Brigham Young University,
Provo, UT 84602, USA

Audrey K. Christiansen*

Department of Mechanical Engineering,
Brigham Young University,
Provo, UT 84602, USA

Jinkwan Han*

Department of Mechanical Engineering,
Brigham Young University,
Provo, UT 84602, USA

Jeffrey R. Hill†‡¹

Department of Mechanical Engineering,
Brigham Young University,
Provo, UT 84602, USA
email: jeff.hill@byu.edu

Sterling G. Baird†‡¹

Department of Mechanical Engineering,
Brigham Young University,
Provo, UT 84602, USA
email: sterling.baird@byu.edu

Tensegrity-inspired architectures combine rigid compression members with a continuous network of soft tension elements, yielding lightweight assemblies with tunable nonlinear responses that are attractive for energy-absorbing applications such as protective equipment, packaging, and aerospace landing structures. Multi-material fused-deposition modeling (FDM) of polylactic acid (PLA) struts and thermoplastic polyurethane (TPU) tension elements makes it possible to fabricate diverse tensegrity-inspired geometries rapidly enough to support a high-throughput experimental search, while the rate-dependent damping of TPU is itself an asset for impact mitigation. We report an experiment-driven Bayesian optimization (BO) framework in which a Gaussian-process surrogate is trained directly on physical quasi-static compression and drop-weight impact data and used to recommend the next batch of designs to print and test. The framework parameterizes a family of tensegrity-inspired unit cells over strut geometry, tension-element cross-section, connectivity topology, and unit-cell tiling, and optimizes peak transmitted force, specific energy absorption, and compaction efficiency.

Tighten abstract to 150–200 words with concrete numerical results once the experimental campaign is complete.

Keywords: tensegrity, multi-material 3D printing, Bayesian optimization, energy absorption, design of experiments

xxiii
xxiv
xxv
xxvi
xxvii
xxviii
xxix
xxx
xxxi
xxxii
xxxiii
xxxiv
xxxv
xxxvi
xxxvii
xxxviii
xxxix
xl
xli
xlii
xliii

Author order / contributions (per @me-madsen). Planned order: Marcus E. Madsen*, Audrey K. Christiansen*, Jinkwan Han*, Jeffrey R. Hill†‡, Sterling G. Baird†‡, where * = equal contribution, † = also equal contribution, and ‡ = corresponding author. Confirm affiliations and add emails for M. Madsen, A. Christiansen, and J. Han, and typeset the equal-contribution footnote per ASME JMD style.

1 Introduction

Manuscript status. At time of writing the project is at the *planned-methods* phase: the parameterized unit cell, multi-material print recipe, joint geometry, quasi-static and drop-impact protocols, and Bayesian-optimization loop described in Section 3 have been scaffolded and prototype hardware has been printed, but the closed-loop experimental campaign has not yet produced reportable results. Sections 4 and 5 therefore remain placeholders.

Tensegrity structures are assemblies of rigid compression members suspended within a continuous network of tension members; their defining property, that no two rigid bars touch, yields lightweight assemblies with remarkable strength-to-weight ratios and tunable nonlinear mechanical responses [1,2]. These properties have made tensegrity attractive across scales, from metamaterial unit cells [3–5] to compliant impact-absorbing robots developed for planetary landing [6–10]. Recent work has shown that *tensegrity-inspired* unit cells can be directly 3D-printed and exhibit load-limiting plateaus under drop-weight impact [11], opening a path toward additively manufactured architected absorbers. Throughout, we use *tensegrity-inspired* to denote printable unit cells that adopt the characteristic tensegrity motif—rigid compression members carried by a network of pretensioned soft tension elements—while relaxing the strict classical requirement that no two compression members touch and that the tension members behave as ideal inextensible cables; here the tension elements are

extruded TPU and the struts may share printed junctions.

Multi-material fused-deposition modeling (FDM) that pairs a rigid polymer such as polylactic acid (PLA) with a soft, rate-dependent elastomer such as thermoplastic polyurethane (TPU) has been used to fabricate rigid–soft architected energy absorbers on a single platform—for example, thick-panel origami metamaterials with PLA panels and TPU hinges [12] and ABS/TPU honeycombs with tunable stiff/flexible proportions [13]. The same rigid–soft co-printing capability makes it possible to rapidly fabricate diverse tensegrity-inspired geometries, which adopt a discrete-compression/continuous-tension topology rather than an origami or honeycomb one. Although extruded TPU does not behave as an idealized inextensible cable, its rate-dependent damping is a desirable property for impact-absorption applications and complements the elastic stiffness of the PLA compression members rather than competing with it.

Designing such architected absorbers is fundamentally a *design-of-experiments* problem: the configuration space spanned by strut geometry, tension-element cross-section, connectivity, and unit-cell tiling is large; each candidate must be physically printed and tested; and the relevant performance metrics—peak transmitted force, specific energy absorption (SEA), and compaction efficiency—are noisy and partially correlated. Bayesian optimization (BO) is well-matched to this regime, having driven breakthroughs from hyperparameter tuning of AlphaGo [14] to sustainable concrete [15], autonomous discovery of organic laser emitters [16], and architected materials [17–20].

1.0.1 Contributions. This paper makes the following contributions:

- (1) A parameterized family of multi-material 3D-printable tensegrity-inspired unit cells with PLA compression members and TPU tension elements that are anchored *inside* the ends

Add 1–2 sentences clearly stating the gap this paper closes vs. Pajunen et al. [11] (single fabrication condition, no closed-loop optimization) and Mo et al. [17] (multifidelity BO, but simulation-only)

¹Corresponding Author.
June 14, 2026

of each PLA strut—the strut acting as a rigid cage in which the cables meeting at a given end join before exiting through discrete outlets—a joint geometry intended to improve cyclic interface durability, to be verified by pull-out and fatigue testing.

- (2) An experiment-driven BO loop, built on BoTorch/Ax [21,22], that operates directly on physical quasi-static compression and drop-weight impact measurements, recommending the next designs to fabricate.

We need to decide whether or not to mention/include the physics-based simulations from PR #33, which seem quite reasonable at this point. If the goal is to get the best of the best, then we would want to include those simulations. In that case we would likely want to treat this as a multi-task problem, but we could run into issues with scaling. If we treat it as a featurization task, then we would likely need to move to a predefined search space or a genetic algorithm.

- (3) High-fidelity validation experiments using *pretensioned* tensegrity assemblies (true cables and measured pretension) for the Pareto-optimal designs identified by the single-stage loop above, reported separately rather than fused into the optimization.

The present study is deliberately scoped to single-cell, fixed-topology T_3 -prism specimens under *axial* quasi-static and drop-weight loading. Off-axis and combined loading, multi-hit and cyclic durability, and landing-attitude variability are outside the scope of this paper and are identified as future work (Section 5); the novelty and generality claims below are correspondingly scoped to this restricted prototype design space rather than to tensegrity-inspired absorbers in general.

The remainder of the paper is organized as follows. Section 2 reviews tensegrity mechanics, multi-material 3D printing for energy absorption, and Bayesian optimization with an emphasis on multi-objective and noise-robust acquisition functions. Section 3 introduces the design parameterization, fabrication workflow, experimental protocols, and BO loop. Section 4 reports the results of the closed-loop experimental campaign, and Section 5 discusses the implications and limitations of the approach. Section 6 concludes.

2 Background

2.1 Tensegrity-Inspired Architectures for Energy Absorption. Tensegrity prisms and their planar extensions exhibit softening–stiffening response under compression [3–5], characteristics desirable for impact mitigation because the structure can absorb a large fraction of the input energy at a controlled, sub-injurious force plateau. Santos [23] recently characterized a tensegrity energy-dissipation metamaterial reporting equivalent viscous damping on the order of $\sim 23\%$ with negligible residual strain per impact, underscoring the suitability of tensegrity-inspired architectures for repeated-impact use cases. The space program literature documents large-scale tensegrity-inspired absorbers for planetary landing [6–10] and a long history of crushable energy-absorbing landing systems [24–26]. Pajunen et al. [11] demonstrated that truncated-tetrahedral tensegrity-inspired unit cells can be directly 3D-printed and exhibit load-limiting plateaus, motivating the present focus on additively manufactured TPU/PLA composites. More recent work on dynamically loaded additively-manufactured energy-absorbing lattices [27], together with Intrigila et al.’s bistable tensegrity-like unit cell for lattice metamaterials [28] as the closest published analog, confirms that this architecture class also responds favorably under impact and quasi-static loading, although neither study employed multi-material FDM or closed-loop design optimization. Table 1 situates the present work against the three most closely related prior efforts, making explicit that the combination of a multi-material FDM tensegrity-inspired architecture with an *experiment*-driven optimization loop is, to our knowledge, not addressed by any single prior study.

2.2 Multi-Material 3D Printing of PLA/TPU Composites.

Multi-material rigid–soft FDM enables stiff/compliant combinations on a single platform with tunable energy absorption, demonstrated for thick-panel origami with PLA (or ABS/CFRP) panels and TPU hinges [12] and for ABS–TPU honeycombs [13]. Neither study is itself a tensegrity, but both establish the rigid–soft co-printing route we adopt. Ye et al. [12] introduced a *wrapping-based* strategy in which rigid cores are encapsulated by continuous soft skins, reported to reduce interface delamination under cyclic loading, something we take inspiration from in our designs. Beyond these rigid–soft demonstrations, a growing body of work confirms that genuinely tensegrity-inspired architectures can be additively manufactured and exhibit programmable mechanical response. Bauer et al. [29] showed that 3D-printed tensegrity metamaterials delocalize deformation to resist catastrophic failure, while Pajunen et al. [30] tuned acoustic bandgaps in 3D-printed tensegrity-inspired lattices through pre-strain, and Sabouni-Zawadzka et al. [31] experimentally characterized 3D-printed tensegrity-inspired metamaterials built on the simplex module. More directly relevant to impact, Almeida et al. [32] and Davami et al. [33] characterized the high-strain-rate and dynamic response of additively manufactured tensegrity-inspired structures, and Wang et al. [34] reported an integrated fabrication-and-validation workflow for tensegrity-inspired rigid–flexible metamaterials. Collectively these studies establish the additive-manufacturability, tunability, and impact relevance of the architecture class adopted here, none combining multi-material FDM with an experiment-driven optimization loop. Recent multi-material PLA/TPU sandwich and layered composites [35,36] report quantitative bounds on stiffness, strength, and energy absorption for the same PLA–TPU pair used here, while FDM PLA fatigue data [37,38] inform conservative design bounds for the rigid struts. Architected multi-material lattices with co-printed compliant skins have been explicitly designed for high specific energy absorption [39], with FDM-specific multimaterial interface adhesion (notably TPU bonded to rigid co-printed substrates) characterized in [40]; recent surveys catalogue the rapidly expanding additively manufactured polymeric energy-absorption literature [41,42].

2.3 Bayesian Optimization for Architected-Material Design.

Bayesian optimization is a sequential, model-based strategy for optimizing expensive black-box functions using a Gaussian-process surrogate [43,44]. Modern implementations such as BoTorch [21] and the Ax platform built atop it [22] support parallel batched evaluations and a wide variety of acquisition functions; recent algorithmic advances include log-EL for numerical robustness [45], noisy expected hypervolume improvement for multi-objective settings [46], input-noise-robust acquisitions [47], and evolution-guided constrained multi-objective BO for self-driving labs [48]. Mixed/categorical search spaces—needed for the planned connectivity-topology extension rather than the continuous T_3 -prism prototype studied here—have dedicated treatments in BOCS [49] and the one-hot-with-rounded-kernel construction of [50]. BO has been applied to mechanical metamaterial and structural design [17–19] and to additive manufacturing [20]. Mo et al. [17] in particular established a multifidelity BO framework for architected materials by fusing low-fidelity simulations with high-fidelity ground truth via nonlinear information-fusion priors [51]; the present work shifts the emphasis from simulation surrogates to direct experimental data, appropriate for materials whose constitutive response is difficult to calibrate from first principles.

3 Materials and Methods

3.1 Design Parameterization. We parameterize a family of tensegrity-inspired unit cells via four groups of design variables. For the working T_3 -prism prototype that defines the initial BO search space (Section 3.4), only the first two groups are active and all of their variables are *continuous*; the connectivity-topology and

Add a short paragraph on relevant TPU/PETG tensegrity search-space bounds once the Edison literature task 5ae24eaf-5b6e-45cf-9f6c-1c7fbd881738 synthesis is integrated.

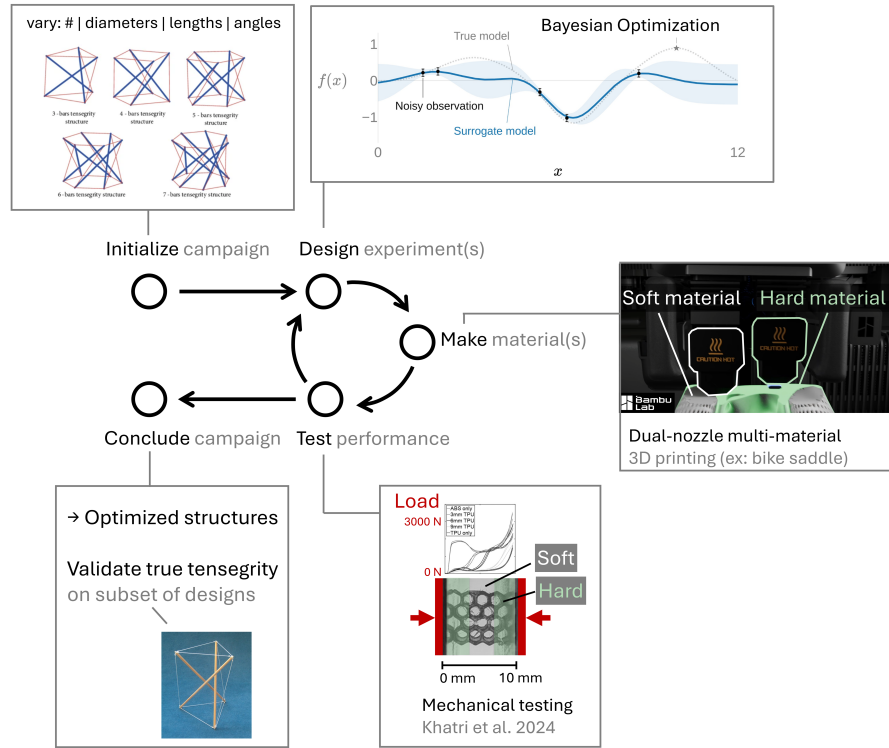


Fig. 1 Closed-loop, experiment-driven design framework. Parameterized PLA/TPU tensegrity-inspired unit cells are printed, tested under quasi-static compression and drop-weight impact, and the resulting performance data drive a Gaussian-process surrogate that recommends the next batch of designs to fabricate.

tiling groups are held fixed for this prototype and are listed here as planned extensions of the design family:

- **PLA compression members.** Strut diameter d_s and length ℓ_s , with the slenderness ratio ℓ_s/d_s bounded away from buckling-dominated regimes.
- **TPU tension elements.** Cross-sectional area A_t (or equivalent diameter d_t for circular cross-sections).
- **Connectivity topology (future extension).** Selected from a discrete set of candidate unit cells (e.g., truncated-tetrahedral, prism-based, and octahedral variants); when activated, the design vector would encode this as a categorical choice. It is held fixed at the T_3 prism for the present campaign.
- **Unit-cell tiling (future extension).** Number of cells $N_x \times N_y \times N_z$ and the orientation of each cell relative to the impact direction; held fixed at a single cell here.

3.1.1 Working prototype. The first instance of this family used to validate the fabrication and test pipeline is a three-strut (T_3) tensegrity prism scaled to a ~ 50 mm bounding box. As implemented in the BO harness, this working prototype exposes five continuous design variables—base radius R , cell height H , twist angle θ , a single strut diameter d_s , and a single cable (tendon) diameter d_t —over the ranges listed in Table 2; the cable diameter d_t is treated as a *continuous* variable on $[3.0, 5.5]$ mm rather than a discrete set. Under the prism’s D_3 symmetry all struts share one diameter and all cables share one diameter, so the present parameterization uses a single strut-diameter axis and a single cable-diameter axis (two member-diameter axes), leaving room to relax to per-orbit (saddle, top, bottom) or fully per-member diameters once the individual orbits have been characterized. The joint diameter d_j is held fixed at 7.0 mm rather than optimized: it sets the printed strut-end cage that houses the internal cable anchors (Section 3.2), so it is constrained primarily by the TPU-tendon

outlet count and the dual-nozzle clearance rather than by energy-absorption performance, and fixing it keeps the anchor geometry constant across specimens so that the five optimized variables are not confounded by joint-strength changes; relaxing d_j is deferred to a follow-on joint-design study. Figure 2 shows the parametric CAD model alongside an as-printed prototype of this working T_3 prism.

3.1.2 As-built resolution of the continuous variables. Although d_s and d_t are treated as continuous, the as-built cross-sections are discretized by the nozzle diameter, the slicer line width, and support interaction, so the effective search granularity is coarser than the nominal continuous box. The realized member diameter therefore changes in steps set by the line-width quantization rather than continuously, and the smallest CAD change that yields a reliably distinguishable as-built member is bounded below by these slicer limits; the lower TPU-tendon bound (3.0 mm) is itself a workflow-specific limit tied to the Bambu auto-support detection floor on this H2D platform rather than a fundamental geometric one. We report measured as-built diameters alongside the commanded values so that the surrogate is fitted on realized geometry, and we treat the print-to-print dimensional spread as part of the inferred observation noise (Section 3.4).

3.2 Multi-Material Fabrication. Specimens are fabricated on a multi-material FDM printer using PLA for the rigid struts and TPU for the soft tension elements. Figure 3 summarizes the end-to-end fabrication and characterization workflow, from parametric CAD through multi-material slicing, dual-extrusion printing, post-processing, and mechanical testing. Rather than wrapping the struts in a continuous TPU skin, the current design anchors the TPU tension elements *inside* the ends of each PLA strut: the cables converging at a given strut end are joined within the strut, which acts as a rigid cage housing the junction, and the individual ten-

Table 1 Positioning of this work against the most closely related prior efforts. The present study is distinguished by combining a multi-material (PLA/TPU) FDM tensegrity-inspired architecture with a closed-loop optimizer trained directly on physical measurements rather than simulations or a single fabrication condition.

Study	Architecture	Fabrication	Optimization	Ground truth
Pajunen et al. 2019 [11]	Truncated-tetrahedral tensegrity-inspired	Single-material 3D print	None (single condition)	Experiment (drop impact)
Intrigila et al. 2022 [28]	Bistable tensegrity-like lattice unit cell	Single-material 3D print	None	Experiment (quasi-static/impact)
Mo et al. 2023 [17]	Architected lattices	— (simulation)	Multifidelity BO	Simulation (+ sparse high-fid.)
This work	Tensegrity-inspired T_3 prism (PLA/TPU)	Multi-material FDM (PLA + TPU)	Experiment-driven BO (SAASBO/qNEHVI)	Physical experiment

Table 2 Design variables for the T_3 -prism Sobol initialization batch, as implemented in the BO harness (single-iteration $n = 9$ Sobol set). The joint diameter is held fixed at the t3-prism.scad default; all specimens are printed in the vertical orientation and packed 3×3 on a single Bambu Lab H2D plate.

Design variable	Symbol	Units	Range
Base radius	R	mm	25–40
Cell height	H	mm	60–110
Twist angle	θ	deg	40–80
Strut (PLA) diameter	d_s	mm	6.0–12.0
Cable (TPU) diameter	d_t	mm	3.0–5.5
Joint diameter (fixed)	d_j	mm	7.0

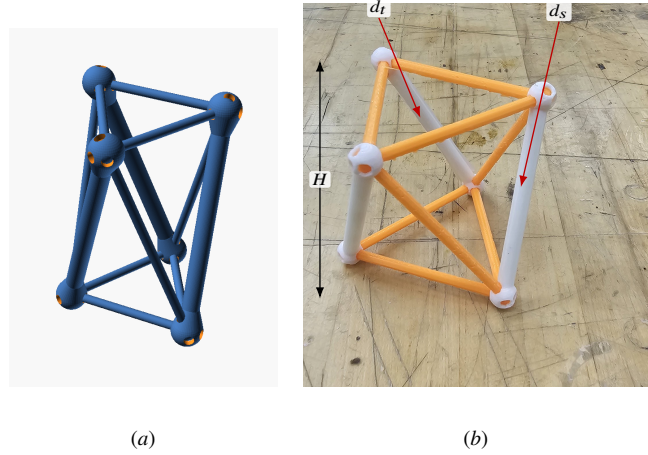


Fig. 2 Working T_3 -prism prototype. (a) Parametric OpenSCAD model whose base radius R , cell height H , twist angle θ , strut diameter d_s , and cable diameter d_t are the design variables of Table 2. (b) A representative dual-material print from the PR #35 print history (rigid PLA struts, here in white; tendon members in orange), with callouts marking the strut diameter d_s , a tendon (cable) diameter d_t , and the cell height H ; the inter-plate twist θ is the relative rotation of the top and bottom node triangles, and the base radius R sets their circumradius.

dons then exit through discrete outlets. This keeps the soft–rigid interface in internal, compression-dominated pockets rather than at an exposed overmolded surface. This construction effectively inverts the material roles of Ye et al.’s soft-skin-over-rigid-core wrapping [12]: here a soft TPU core is captured within a rigid PLA shell, so we cite that work only as a multi-material co-printing precedent rather than as validation of the present junction.

3.2.1 Print platform and joint geometry. The working platform is a Bambu Lab H2D printer, which permits a single rigid–soft build without filament swaps. Strut endpoints are tied to cables through parametric joint geometries developed and ranked through a five-design OpenSCAD study (anchor-bulb, dovetail, TPU-sleeve overmold, eyelet-loop, and TPU-rebar variants); the working prototype uses a dovetail joint (Design B) with an anchor-bulb backup (Design A) for sensitivity studies, with a captive TPU core routed inside the PLA shell to keep the soft tendon protected from layer-line failure at the strut-to-cable transition. The full five-design comparison and the selected junction are detailed in the Supplementary Information.

3.2.2 Supports for soft members. Because near-vertical TPU tendons are otherwise unsupported during printing, the slicer profile combines a tensegrity-specific Bambu Studio recipe (support threshold angle dropped from 40° to 10° , support material matched to the rigid extruder) with manually generated narrowing pillars that ray-cast against the printable mesh underside, producing TPU-safe coverage of vertical members without slicer-side painting. Full workflow details are provided in the Supplementary Information.

3.3 Experimental Characterization. Each printed specimen is subjected to two physical tests:

3.3.1 Quasi-static compression. A uniaxial load–displacement curve is recorded on a benchtop electromechanical load frame (BYU CB 123 Instron) following best-practice combinations of ASTM D638, ASTM D412, ASTM E111,

ASTM F2971, and ISO/ASTM 52900/52921 adapted to architected polymer cells. Because expected cell stiffnesses fall in the ~ 5 – 30 g force range, the default 5 kN load cell is over-ranged and is being replaced by a 100–500 N cell for the first campaign. Reported metrics are

$$\text{SEA} = \frac{1}{m} \int_0^{\delta_d} F(\delta) d\delta, \quad \eta_c = \frac{\int_0^{\delta_d} F(\delta) d\delta}{F_{\max} \delta_d}, \quad (1)$$

where m is the specimen mass, δ_d is the densification displacement, $F_{\max}$ is the peak transmitted force, and η_c is the compaction efficiency. To keep these metrics objective and reproducible, the densification displacement δ_d is taken as the displacement at which the energy-absorption efficiency–displacement curve reaches its maximum ($d\eta/d\delta = 0$), and $F_{\max}$ is the maximum force recorded within the integration window $[0, \delta_d]$ rather than a global or post-densification peak. These energy-absorption-diagram definitions of densification displacement and compaction (energy-absorption) efficiency follow the canonical cellular-solid treatments of Gibson and Ashby [52], Avalle et al. [53], Tan et al. [54], and Michailidis et al. [55].

3.3.2 Drop-weight impact. Following Pajunen et al. [11], specimens are subjected to drop-weight impact tests with instrumented load cells; we report the peak transmitted force and the

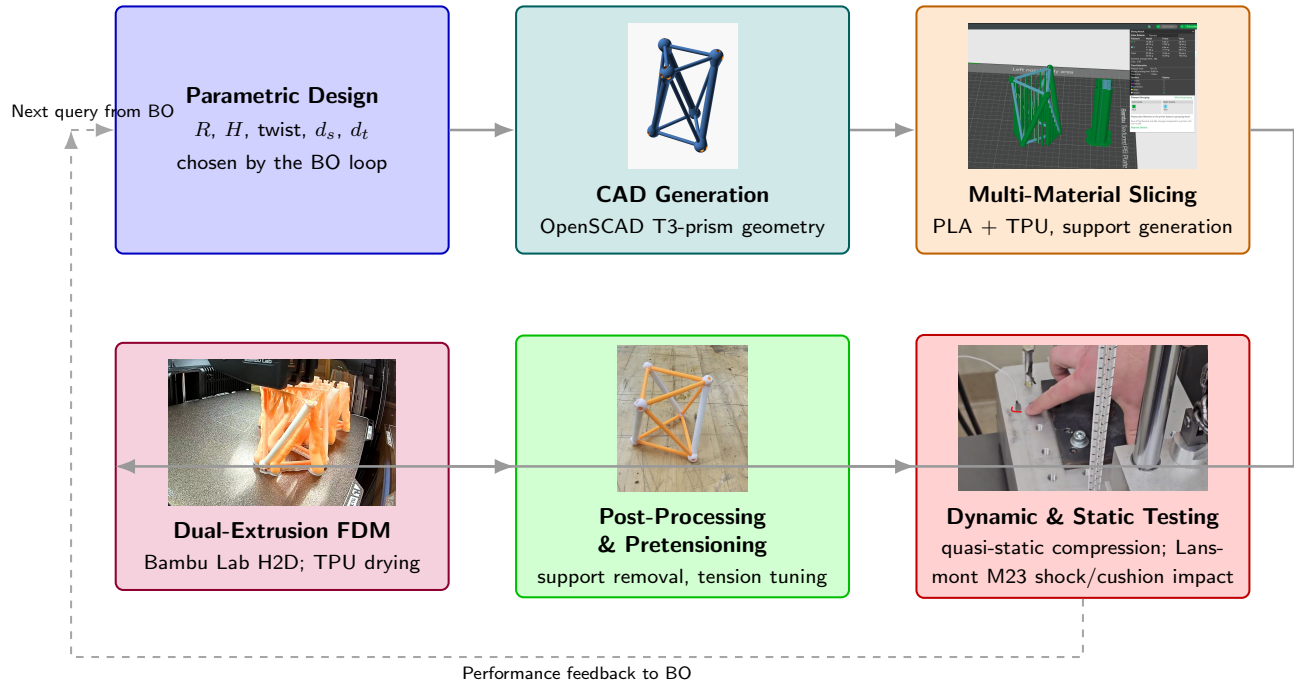


Fig. 3 Fabrication and characterization workflow for the multi-material tensegrity-inspired unit cells: design parameters drive parametric CAD, slicing with manually generated TPU supports, a single multi-material print on the Bambu Lab H2D, post-processing and inspection, and mechanical testing. Node photographs are representative artifacts drawn from the project's build history: the OpenSCAD T_3 -prism render (CAD), the dual-nozzle Bambu Studio slice with PLA on the left extruder and TPU on the right (slicing), an in-progress H2D print of the prism batch (FDM), an as-printed specimen (post-processing), and the bungee-assisted drop-tower base plate with accelerometer (testing).

Table 3 Multi-material print parameters on the Bambu Lab H2D. Cells marked *TBD* are pending confirmation; the reporting structure follows the methods section of Ye et al. [12].


Parameter	PLA (rigid struts)	TPU (soft tendons)
Nozzle temperature (°C)	<i>TBD</i>	<i>TBD</i>
Bed temperature (°C)		<i>TBD</i>
Layer height (mm)		<i>TBD</i>
Print speed (mm/min)	<i>TBD</i>	<i>TBD</i>
Infill (%)	<i>TBD</i>	<i>TBD</i>
Build-plate type	Textured PEI	
Build orientation	Vertical	
Supports	Off in slicer; manual narrowing pillars	

energy-absorption plateau characteristics. Figure 4 illustrates the mechanism-oriented presentation we adopt for these processed deceleration traces, linking features of the measured signal to the structural events that produce them. The primary fixture is a bungee-assisted laboratory drop tower in which the base accelerates downward faster than $1g$; because unconstrained specimens lift off the base during descent by design of the rig, the protocol constrains the specimen top through light tethers (capping upward travel) and registers the base via transfer tape or V-block features so that loading-direction compliance is not altered. A higher-fidelity replicate campaign on a Lansmont M23 shock/cushion tester (per ASTM D1596) with synchronized Polytec QTEC laser vibrometry is planned for selected Pareto-optimal designs. Slip resistance and traction at the specimen-floor interface—governed by the tip geometry rather than the internal lattice—follow the test methodology of ISO 11334-4 [56] for walking-aid tips and are out of scope for the present axial-impact study.

3.3.3 Per-modality objectives. Five complementary data streams (triaxial accelerometer, high-speed video, shaker transfer function, slug-firing gas gun, and Polytec QTEC laser-Doppler vibrometer) each contribute a distinct raw observable; the mapping from each stream to BO-ready scalar objectives (SEA, VEA, $F_{\max}$, cushion-curve intercept, Gibson–Ashby relative density [52]) is defined in five companion briefs and consolidated in a cross-modality synthesis.

3.4 Experiment-Driven Bayesian Optimization Loop. The optimization loop maintains a Gaussian-process (GP) surrogate over the design space defined in Section 3.1. After each round of physical experiments, the GP is updated and an acquisition function is maximized to recommend the next batch of designs to fabricate. The primary reported campaign is posed as a *constrained multi-objective* problem: simultaneously maximize specific energy absorption (SEA) and compaction efficiency η_c subject to an upper bound on peak transmitted force $F_{\max} \leq F^*$, where F^* is fixed from the rigid-control drop response so that admissible designs must out-cushion the uncushioned baseline. Implementation uses BoTorch [21] with noisy Expected Hypervolume Improvement (qNEHVI) [46] as the acquisition function; the hypervolume reference point is anchored at the rigid-control (SEA, η_c) pair so that improvement is measured against the no-absorber baseline. A single-objective log-Expected-Improvement (LogEI) run [45] on SEA (with the same force constraint) is retained only as a baseline for quantifying the benefit of the multi-objective formulation. The input-noise-robust acquisition of Daulton et al. [47] and the evolution-guided constrained variant of Low et al. [48] are held in reserve as a contingency, to be adopted only if between-print variability is found to dominate the objective signal; they are not part of the default reported loop. The working T_3 -prism search space is fully continuous (the five variables of Table 2), so no categorical encoding is required for the present campaign; the mixed-

EXAMPLE (mock-up, synthetic data): mechanism-oriented drop-test figure

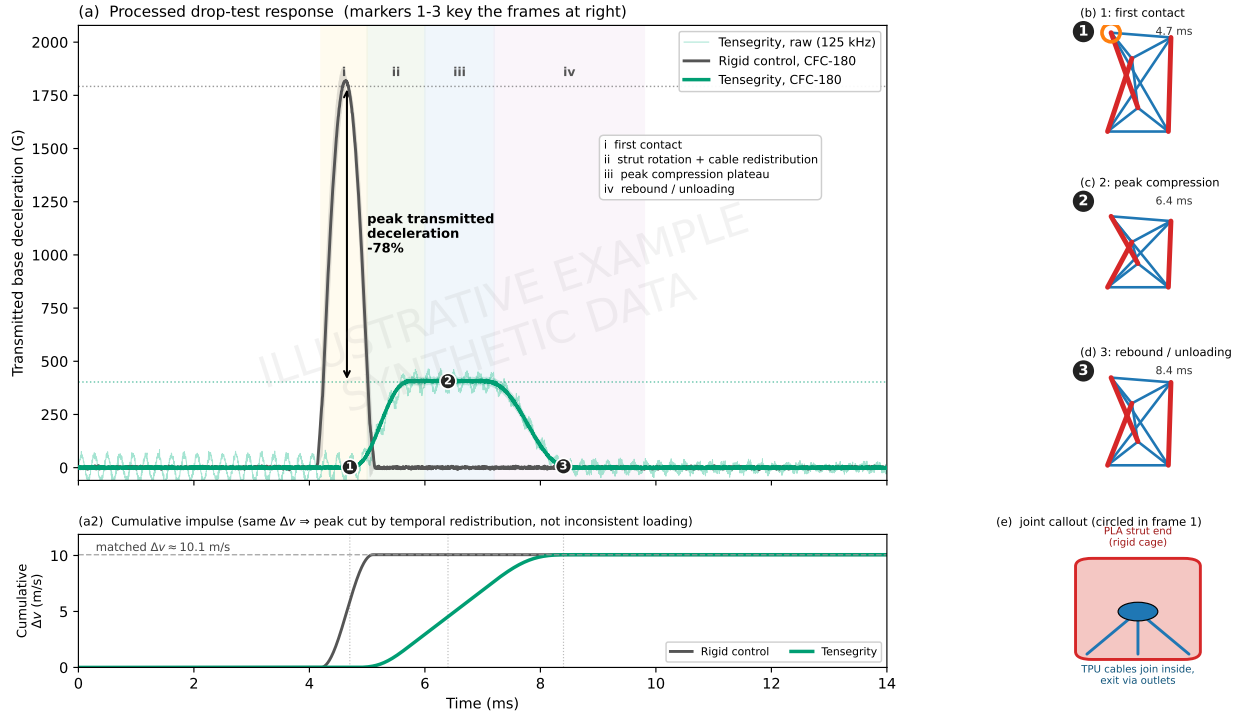

Synthetic illustration. In a real figure: transmitted base deceleration of a rigid control vs. T3-prism tensegrity, both SAE J211 CFC-180 filtered (125 kHz raw shown faint), zero-phase (filtfilt), time-aligned on the CH4 first-contact index. Curves are the mean of $n=5$ replicates; bands are ± 1 s.d. Frames 1-3 are high-speed/DIC stills at markers 1-3; (e) shows the internal cable-anchor joint that spreads the impulse.

Fig. 4 Illustrative example (synthetic data). Template for the mechanism-oriented drop-test figures planned for the Results: (a) processed deceleration response of a rigid control vs. a tensegrity specimen (SAE J211 CFC-180 filtered [57]), with event-based phase shading and numbered markers keyed to the schematic frames (b)–(d); (a2) cumulative-impulse subpanel showing the two traces transfer the same mass-normalized Δv , so the lower tensegrity peak reflects temporal redistribution rather than inconsistent loading; (e) the internal-anchor joint load path. Curves are synthetic and impulse-consistent (control anchored to the documented ~ 1792 G CFC-180 peak; tensegrity shoulder scaled to the same impulse), pending real high-rate channels and camera frames. Generated by `scripts/figures/mechanistic_data_figure_example.py`.

search-space constructions of [50] and the BOCS combinatorial baseline [49] are noted as the route for the future connectivity-topology categorical (Section 3.1) rather than as part of the current loop.

The GP surrogate uses a Matérn-5/2 kernel with automatic relevance determination (ARD), i.e. a separate length scale per input dimension, so that per-variable sensitivities can be read directly from the fitted length scales. Inputs are normalized to the unit cube and outputs are standardized; observation noise is *inferred* by the model (a learned homoscedastic noise level) rather than fixed a priori. The campaign budget is an $n = 9$ Sobol initialization batch (Table 2) followed by $T = 10$ sequential optimization batches of $q = 5$ prints each, i.e. $9+50 = 59$ specimens in total. Random seeds for the Sobol generator and the acquisition optimizer are recorded per batch so that each recommendation is reproducible.

3.4.1 Implementation status. The campaign harness is built on the Ax platform [22]. The working T_3 -prism search space is the five-variable continuous box of Table 2; Ax's HierarchicalSearchSpace machinery is reserved for the planned topology/tiling extensions (Section 3.1) and is not exercised by the current continuous-only prototype. The first physical batch consists of $n = 9$ specimens generated by a Sobol sequence over these five variables and printed in a single 3×3 plate layout. For this ~ 5 – 6 variable space the default acquisition pairing is sparse axis-aligned subspace BO (SAASBO) [58] with qNEHVI. We retain SAASBO even though the dimensionality is modest because its strong priors on length scales tend to improve uncertainty quantification and

predictive accuracy at the small sample sizes typical of physical campaigns, not only in high-dimensional settings; to make this an empirical rather than asserted choice, the reported campaign benchmarks SAASBO against a standard single-task GP baseline with the same Matérn-5/2 ARD kernel (retrospective leave-one-out calibration and predictive accuracy on the accumulated data). Escalation to trust-region BO (TuRBO) [59] is planned only if larger per-member-diameter tilings push the design space well beyond this regime. The campaign code and recommended batches will be archived at a Zenodo-minted DOI mirroring the GitHub repository.

Once the campaign produces model data, the fitted surrogate is audited with the leave-one-out cross-validation and parameter-sensitivity diagnostics of Figs. 5 and 6.

The previous BO-loop schematic here was redundant with the overview figure (Fig. 1); per review it is replaced with surrogate-diagnostic figures. Figs. 5–9 are currently *illustrative examples* produced by a real Ax/BoTorch loop on synthetic objective values (`scripts/figures/ax_placeholder_figures_example.py`); replace the synthetic `evaluate()` with measured outcomes once the campaign runs.

3.5 Metal-Analog Validation. To test whether the rankings learned on the printed PLA/TPU specimens generalize beyond the as-printed polymer system, a final validation campaign reproduces a subset of the T_3 -prism designs as *metal analogs* built from hollow aluminum rods (compression members) and stainless-steel threaded cables (tension members), using the same R , H , θ , and member-diameter parameterization. Rather than fabricating only the top-ranked geometries, we deliberately span the pre-

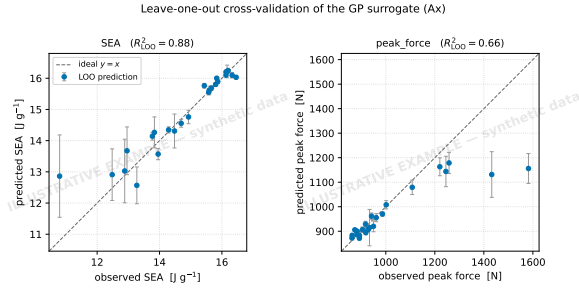


Fig. 5 Illustrative example (synthetic data). Leave-one-out cross-validation of the Gaussian-process surrogate—predicted vs. observed specific energy absorption (SEA) and peak transmitted force, with model error bars and R^2_{LOO} —obtained from a real Ax/BoTorch run on synthetic objective values. To be regenerated from campaign data.

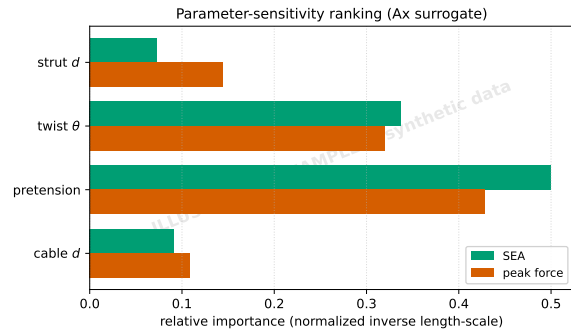


Fig. 6 Illustrative example (synthetic data). Parameter-sensitivity ranking (model length-scale-based importances per objective; cf. SAASBO inverse length-scales or Sobol indices) of the design variables in Table 2, from the same Ax/BoTorch run as Fig. 5.

dicted performance range: a few designs the surrogate predicts to be *worst*-performing, a few *mediocre*, and a few *best*-performing are each built in both material systems. Comparing the measured ordering of the PLA/TPU specimens against their hollow-aluminum/stainless-steel counterparts tests whether both systems preserve the same rank ordering of energy-absorption performance, which would indicate that the optimization transfers across material systems rather than overfitting to the printed polymers. We treat this as a *stringent, exploratory* transfer test rather than a presumed one-to-one validation: the deformation modes, joint compliance, friction, pretension behavior, and strain-rate sensitivity all differ between the PLA/TPU and aluminum/steel systems, so agreement is not expected a priori. The rank-preservation criterion is fixed in advance as the Spearman rank-correlation coefficient ρ_s between the two material systems' orderings of the primary metric (SEA), with peak transmitted force reported as a secondary ranking; ρ_s near unity would support cross-system transfer of the learned design ranking. Table 4 reports the planned rank-ordering comparison and Fig. 7 shows the assembled metal-analog and printed-polymer specimens for each performance tier.

Populate Table 4 with measured metrics and ranks once the metal-analog validation specimens (hollow Al rods + stainless-steel threaded cables) and their PLA/TPU equivalents have been built and tested.

Figure metal-validation: Assembled validation specimens for each predicted performance tier (worst / mediocre / best), shown as printed PLA/TPU builds alongside their hollow-aluminum-rod and stainless-steel-threaded-cable metal analogs, with callouts marking the aluminum compression members, the threaded steel tension cables, and the strut-end cable anchors. Photographs to be added once the specimens are fabricated.

Table 4 Placeholder (data pending). Planned rank-ordering validation: representative T_3 -prism designs predicted to be *worst*-, *mid*-, and *best*-performing, each fabricated as a printed PLA/TPU specimen and as a hollow-aluminum-rod / stainless-steel-cable metal analog. Entries record the measured performance metric (e.g. SEA or peak transmitted force) and the resulting rank within each material system; agreement of the two rankings indicates the optimization transfers across material systems.

Predicted tier	Design ID	PLA/TPU (rank)	Al/SS (rank)
Worst	<i>D-w1</i>	—	—
Worst	<i>D-w2</i>	—	—
Mediocre	<i>D-m1</i>	—	—
Mediocre	<i>D-m2</i>	—	—
Best	<i>D-b1</i>	—	—
Best	<i>D-b2</i>	—	—

Figure placeholder: Assembled validation specimens for each predicted performance tier (worst / mediocre / best), shown as printed PLA/TPU builds alongside their hollow-aluminum-rod and stainless-steel-threaded-cable metal analogs, with callouts marking the aluminum compression members, the threaded steel tension cables, and the strut-end cable anchors. Photographs to be added once the specimens are fabricated.

Fig. 7 Placeholder. Assembled validation specimens for each predicted performance tier (worst / mediocre / best), shown as printed PLA/TPU builds alongside their hollow-aluminum-rod and stainless-steel-threaded-cable metal analogs, with callouts marking the aluminum compression members, the threaded steel tension cables, and the strut-end cable anchors. Photographs to be added once the specimens are fabricated.

4 Results

Populate Results section once the experimental campaign produces data. Suggested subsections follow.

4.1 Convergence of the BO Loop. Figure 8 illustrates the intended convergence comparison.

4.2 Pareto-Optimal Designs. Figure 9 shows the form the Pareto-front presentation will take.

4.3 Reproducibility Across Print Replicates.

Table 5 Placeholder. Mean and CV of SEA, peak force, and compaction efficiency across n replicate prints for the top- k designs.

Column A	Column B	Column C
(table contents pending)		

Table repeatability: Mean and CV of SEA, peak force, and compaction efficiency across n replicate prints for the top- k designs.

5 Discussion

Populate Discussion section once Results are in. Anchor against the gaps identified in Section 1 and the prior work cited in Section 2.

Topics to address:

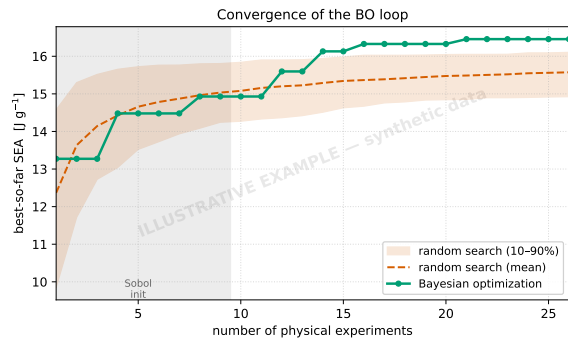


Fig. 8 Illustrative example (synthetic data). Best-so-far SEA vs. number of physical experiments for the Ax/BoTorch loop against an independent random-search baseline; the shaded region is the $n = 9$ Sobol initialization. Generated on synthetic objective values; to be replaced with campaign results (with confidence intervals over random seeds, and Pareto hypervolume for the multi-objective runs).

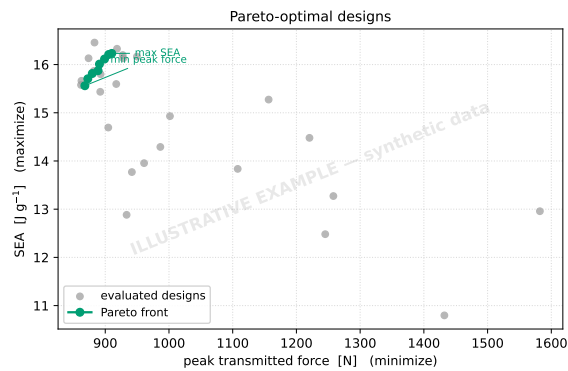


Fig. 9 Illustrative example (synthetic data). Pareto front in (peak transmitted force, SEA) space with all evaluated designs, from the Ax/BoTorch loop on synthetic objective values; representative geometries to be annotated once campaign data are available.

- Comparison to the simulation-driven multifidelity framework of Mo et al. [17] and the single-condition fabrication study of Pajunen et al. [11].
- Practical considerations: TPU–PLA interface durability under cyclic loading; sensitivity of optimal designs to print parameters (extrusion temperature, layer height); transferability to TPU/PETG or other high-temperature thermoplastics.
- Path forward toward integrated tread+latte structures, miniaturization to crutch-tip envelopes (from the Edison crutch-tip synthesis), and field testing. Long-term crutch use is associated with substantial upper-extremity overuse injury and ground-reaction-force impulses [60–64]; existing spring-loaded [65,66] and polymer-damped [67] tip designs reduce loading rate but not peak transmitted force, leaving an open design opportunity that an architected tensegrity-inspired insert is well-positioned to address. Recent open-source 3D-printed crutch work [68] and expert evaluations of orthopaedic caps [69] suggest a plausible translation path; adjacent footwear and orthotic lattice studies [70–72] provide additional transferable design heuristics.

5.0.1 Limitations..

6 Conclusions

We have presented an experiment-driven Bayesian-optimization framework for designing multi-material 3D-printed tensegrity-inspired energy absorbers using PLA struts and TPU tension elements. The framework parameterizes a family of unit cells, fabricates each candidate on a single multi-material FDM platform with TPU tendons anchored inside the PLA strut ends, characterizes the response under quasi-static compression and drop-weight impact, and updates a Gaussian-process surrogate [21] that recommends the next batch of designs. The approach is broadly applicable to architected absorbers whose constitutive response is difficult to calibrate from first principles and where physical experiments—rather than simulations—are the natural ground truth.

Acknowledgment

This work was supported by the Brigham Young University Mentored Research Grant program. The authors thank the undergraduate researchers who carried out the multi-material printing and impact testing, and the graduate co-mentor who supported day-to-day operations.

Funding Data

- Brigham Young University Mentored Research Grant ().

Conflict of Interest

The authors declare no conflict of interest.

Pending TODOs and figure/table placeholders

- Tighten abstract to 150–200 words with concrete numerical results once the experimental campaign is complete. 1
- Author order / contributions (per @me-madsen). Planned order: Marcus E. Madsen*, Audrey K. Christiansen*, Jinkwan Han*, Jeffrey R. Hill†‡, Sterling G. Baird†‡, where * = equal contribution, † = also equal contribution, and ‡ = corresponding author. Confirm affiliations and add emails for M. Madsen, A. Christiansen, and J. Han, and typeset the equal-contribution footnote per ASME JMD style. 1
- Manuscript status. At time of writing the project is at the *planned-methods* phase: the parameterized unit cell, multi-material print recipe, joint geometry, quasi-static and drop-impact protocols, and Bayesian-optimization loop described in Section 3 have been scaffolded and prototype hardware has been printed, but the closed-loop experimental campaign has not yet produced reportable results. Sections 4 and 5 therefore remain placeholders. 1
- Add 1–2 sentences clearly stating the gap this paper closes vs. Pajunen et al. [11] (single fabrication condition, no closed-loop optimization) and Mo et al. [17] (multifidelity BO, but simulation-only). 1
- We need to decide whether or not to mention/include the physics-based simulations from PR #33, which seem quite reasonable at this point. If the goal is to get the best of the best, then we would want to include those simulations. In that case we would likely want to treat this as a multi-task problem, but we could run into issues with scaling. If we treat it as a featurization task, then we would likely need to move to a predefined search space or a genetic algorithm. 2
- Eventually switch this overview figure to a vertical orientation; it is currently reproduced from the MRG proposal (figures/overview-updated.png). 2

516	■ Add a short paragraph on relevant TPU/PETG tensegrity search-space bounds once the Edison literature task 5ae24eaf-5b6e-45cf-9f6c-1c7fbd881738 synthesis is integrated.	2	■ Figure metal-validation: Assembled validation specimens for each predicted performance tier (worst / mediocre / best), shown as printed PLA/TPU builds alongside their hollow-aluminum-rod and stainless-steel-threaded-cable metal analogs, with callouts marking the aluminum compression members, the threaded steel tension cables, and the strut-end cable anchors. Photographs to be added once the specimens are fabricated.	580
517				581
518				582
519				583
520	■ Specify exact manufacturing-feasibility constraints once finalized; the connectivity-topology categorical encoding is deferred until that variable is activated beyond the T_3 prism.	3		584
521				585
522				586
523				587
524	■ Cite the heterogeneous-parameters Edison LITERATURE_HIGH brief (5191cf4d) on D_3 -symmetric vs. fully-per-member parameterization.	3	■ Populate Results section once the experimental campaign produces data. Suggested subsections follow.	588
525				589
526				590
527	■ The cable-diameter lower bound (3.0 mm) is set by the Bambu auto-support detection floor; add the remaining manufacturing-feasibility constraints once finalized.	3	■ Plot best-so-far performance vs. number of physical experiments for each acquisition function, with confidence intervals over random seeds.	591
528				592
529				593
530	■ Quantitatively verify the internal-anchoring junction strength against the PR #39 / PR #35 joint pull-out studies before making any cyclic-durability claim.	3	■ Show 3–5 representative geometries from along the Pareto front trading SEA against peak transmitted force.	594
531				595
532				596
533	■ Document slicer profile (layer height, infill, print speed, nozzle temperatures, retraction settings) and validation prints used to characterize PLA-TPU interface strength.	4	■ Report between-print variability (CV) for top-ranked designs; informs the choice of input-noise-robust acquisition.	597
534				598
535				599
536	■ Cite the joint-design Phase-3 CAD review (Edison ANALYSIS 19e0c868) and the Phase-4 vision review (e9a1f4cc) once both are integrated into the references.	4	■ Table repeatability: Mean and CV of SEA, peak force, and compaction efficiency across n replicate prints for the top- k designs.	600
537				601
538				602
539	■ @achris0520 to confirm the exact PLA and TPU print parameters (nozzle and bed temperatures, layer height, print speeds, infill) used on the Bambu Lab H2D; only the build-plate type, vertical orientation, and support strategy are currently established.	4	■ Populate Discussion section once Results are in. Anchor against the gaps identified in Section 1 and the prior work cited in Section 2.	603
540				604
541				605
542				606
543				607
544	■ Cite the Instron-stiffness Edison LITERATURE_HIGH brief (9f68e71e) once the entry is added to references.bib.	4	■ Identify limitations: design space size relative to experimental budget; reliance on a single fabrication platform; metric selection (axial impact only).	608
545				609
546				610
547	■ Cite the drop-test protocol document (PR #67) and the drop-test Edison LITERATURE_HIGH brief (653d7d39) once integrated.	4	■ Two-sentence quantitative summary of the headline outcome (e.g., improvement in SEA over baselines within N rounds; identification of a Pareto-optimal geometry validated by replicate prints).	611
548				612
549				613
550	■ Cite the M23 + QTec equipment brief (Edison LITERATURE_HIGH 1a0f4a70) once integrated.	5	■ Confirm exact grant numbers and acknowledge any NASA/Utah-Space-Grant-Consortium support per acknowledgment-text guidelines.	614
551				615
552	■ Cite the per-modality objective-function briefs (Edison LITERATURE_HIGH cfd30f3e, 7d6b43bf, 31126ee7, 9d74ab2e, f40e41a7) and the ANALYSIS synthesis (789de8ab) once references.bib entries are added from PR #60.	5	■ award number	616
553				617
554				618
555				
556				
557	■ Specify the exact test fixtures, load-cell ranges, sampling rate, DAQ, drop heights, and the protocol for averaging replicate prints.	5		
558				
559				
560	■ Confirm the final budget ($T = 10$ batches of $q = 5$) against printer throughput once the campaign is underway.	5		
561				
562				
563	■ Insert the Zenodo DOI and release version for the campaign code once the repository snapshot is published; cite the BO scaffolding (PR #30), the T_3 -prism Sobol batch (PR #35), and the heterogeneous-parameter Edison brief (5191cf4d) once those branches land in main.	6		
564				
565				
566				
567				
568	■ The previous BO-loop schematic here was redundant with the overview figure (Fig. 1); per review it is replaced with surrogate-diagnostic figures. Figs. 5–9 are currently <i>illustrative examples</i> produced by a real Ax/BoTorch loop on synthetic objective values (scripts/figures/ax_placeholder_figures_example.py); replace the synthetic evaluate() with measured outcomes once the campaign runs.	6		
569				
570				
571				
572				
573				
574				
575				
576	■ Populate Table 4 with measured metrics and ranks once the metal-analog validation specimens (hollow Al rods + stainless-steel threaded cables) and their PLA/TPU equivalents have been built and tested.	7		
577				
578				
579				
			References	619
			[1] Skelton, R. E. and de Oliveira, M. C., 2009, <i>Tensegrity Systems</i> , Springer, New York.	620
			[2] Sultan, C., 2009, “Tensegrity: 60 Years of Art, Science, and Engineering,” <i>Advances in Applied Mechanics</i> , 43 , pp. 69–145.	621
			[3] Amendola, A., Carpentieri, G., de Oliveira, M. C., Skelton, R. E., and Fraternali, F., 2014, “Experimental Investigation of the Softening–Stiffening Response of Tensegrity Prisms under Compressive Loading,” <i>Composite Structures</i> , 117 , pp. 234–243.	622
			[4] Zhang, Q., Zhang, D., Dobah, Y., Scarpa, F., Fraternali, F., and Skelton, R. E., 2018, “Tensegrity Cell Mechanical Metamaterial with Metal Rubber,” <i>Applied Physics Letters</i> , 113 (3), p. 031906.	623
			[5] Fraternali, F., Carpentieri, G., and Amendola, A., 2015, “Tensegrity Ring Structures for Impact Protection,” <i>International Journal of Solids and Structures</i> , 65–66 , pp. 232–243.	624
			[6] Agogino, A. K., SunSpiral, V., and Atkinson, D., 2018, “Super Ball Bot — Structures for Planetary Landing and Exploration,” NASA Ames Research Center, https://www.nasa.gov/general/super-ball-bot/	625
			[7] Caluwaerts, K., Agogino, A. M., and SunSpiral, V., 2014, “SUPERball: Exploring Tensegrities for Planetary Probes,” <i>Proceedings of the 12th International Symposium on Artificial Intelligence, Robotics and Automation in Space (i-SAIRAS)</i>	626
			[8] Sabelhaus, A. P., Bruce, J., Caluwaerts, K., Manovi, P., Firoozi, R. F., Dobi, S., Agogino, A. M., and SunSpiral, V., 2015, “System Design and Locomotion of SUPERball, an Untethered Tensegrity Robot,” <i>2015 IEEE International Conference on Robotics and Automation (ICRA)</i> , pp. 2867–2873, doi: 10.1109/ICRA.2015.7139590.	627
			[9] Vespignani, M., Friesen, J. M., SunSpiral, V., and Bruce, J., 2018, “Design of SUPERball v2, a Compliant Tensegrity Robot for Absorbing Large Impacts,” , pp. 2865–2871.	628
			[10] Deitrich, N., Baldonado, K. M., Khan, A., Cook, J., and Rizzo, L., 2022, “A Rideshare Tensegrity Rover Concept to Explore Titan’s Lands and Oceans,” <i>AIAA SciTech Forum</i> , NASA Langley Research Center / Ames Research Center.	629

- [11] Pajunen, K., Johannis, P., Pal, R. K., Rimoli, J. J., and Daraio, C., 2019, "Design and Impact Response of 3D-Printable Tensegrity-Inspired Structures," *Materials & Design*, **182**, p. 107966.
- [12] Ye, H., Liu, Q., Cheng, J., Li, H., Jian, B., Wang, R., Sun, Z., Lu, Y., and Ge, Q., 2023, "Multimaterial 3D Printed Self-Locking Thick-Panel Origami Metamaterials," *Nature Communications*, **14**, p. 1607.
- [13] Khatri, N. R. and Egan, P. F., 2024, "Energy Absorption of 3D Printed ABS and TPU Multimaterial Honeycomb Structures," *3D Printing and Additive Manufacturing*, **11**, pp. e840–e850.
- [14] Silver, D., Huang, A., Maddison, C. J., Guez, A., Sifre, L., van den Driessche, G., Schrittwieser, J., Antonoglou, I., Panneershelvam, V., Lanctot, M., et al., 2016, "Mastering the Game of Go with Deep Neural Networks and Tree Search," *Nature*, **529**(7587), pp. 484–489.
- [15] Ament, S., Witte, A., Garg, N., and Kusuma, J., 2023, "Sustainable Concrete via Bayesian Optimization," *arXiv preprint arXiv:2310.18288*, NeurIPS 2023 Workshop on Adaptive Experimental Design and Active Learning in the Real World.
- [16] Strieth-Kalthoff, F., Hao, H., Rathore, V., Derasp, J., Gaudin, T., Angello, N. H., Seifrid, M., Trushina, E., Guy, M., Liu, J., et al., 2024, "Delocalized, Asynchronous, Closed-Loop Discovery of Organic Laser Emitters," *Science*, **384**(6697), p. eadk9227.
- [17] Mo, C., Perdikaris, P., and Raney, J. R., 2023, "Accelerated Design of Architected Materials with Multifidelity Bayesian Optimization," *Journal of Engineering Mechanics*, **149**(6), p. 04023028.
- [18] Wang, Y. et al., 2022, "Bayesian Optimization for the Design of Mechanical Metamaterials," *Journal of the Mechanics and Physics of Solids*, **159**, p. 104734.
- [19] Lee, S. et al., 2023, "Bayesian Optimization for Structural Design Problems," *Structural and Multidisciplinary Optimization*, **66**(2), p. 47.
- [20] Zhang, M., Parnell, A., Brabazon, A., and Benavoli, A., 2021, "Bayesian Optimisation for Sequential Experimental Design with Applications in Additive Manufacturing," *arXiv preprint arXiv:2107.12809*.
- [21] Balandat, M., Karrer, B., Jiang, D. R., Daulton, S., Letham, B., Wilson, A. G., and Bakshy, E., 2020, "BoTorch: A Framework for Efficient Monte-Carlo Bayesian Optimization," *Advances in Neural Information Processing Systems 33 (NeurIPS 2020)*, <https://arxiv.org/abs/1910.06403>
- [22] Olson, M., Santorella, E., Tiao, L. C., Cakmak, S., Garrard, M., Daulton, S., Lin, Z. J., Ament, S., Beckerman, B., Onofrey, E., Igusti, P., Lara, C., Letham, B., Cardoso, C., Shen, S. S., Lin, A. C., Grange, M., Kashtelyan, E., Eriksson, D., Balandat, M., and Bakshy, E., 2025, "Ax: A Platform for Adaptive Experimentation," *Proceedings of the Fourth International Conference on Automated Machine Learning*, L. Akoglu, C. Doerr, J. N. van Rijn, R. Garnett, and J. R. Gardner, eds., Proceedings of Machine Learning Research, Vol. 293, PMLR, pp. 21/1–25, <https://proceedings.mlr.press/v293/olson25a.html>
- [23] Santos, F. A., 2023, "Toward a novel energy-dissipation metamaterial with tensegrity architecture," *Advanced Materials*, May 2023.
- [24] Cloutier, G. J., 1966, "Landing Impact Energy Absorption Using Anisotropic Crushable Materials," *Journal of Spacecraft and Rockets*, **3**(12), pp. 1755–1761.
- [25] Adams, D. S., 2004, "Mars Exploration Rover Airbag Landing Loads Testing and Analysis," *45th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conference*, doi: 10.2514/6.2004-1795.
- [26] Jackson, K. E., Fasanella, E. L., and Polanco, M. A., 2014, "Simulating the Response of a Composite Honeycomb Energy Absorber: I. Dynamic Crushing of Components and Multiterrain Impacts," *Journal of Aerospace Engineering*, **27**(3), pp. 424–436.
- [27] Davami, K., Mohsenizadeh, M., Munther, M., Palma, T., Beheshti, A., and Momeni, K., 2019, "Dynamic energy absorption characteristics of additively-manufactured shape-recovering lattice structures," doi: 10.1088/2053-1591/aaf78c, <https://doi.org/10.1088/2053-1591/aaf78c>
- [28] Intrigila, C., Micheletti, A., Nodargi, N. A., Artioli, E., and Bisegna, P., 2022, "Fabrication and experimental characterisation of a bistable tensegrity-like unit for lattice metamaterials," *Additive Manufacturing*, **57**, p. 102946.
- [29] Bauer, J., Kraus, J. A., Crook, C., Rimoli, J. J., and Valdevit, L., 2021, "Tensegrity Metamaterials: Toward Failure-Resistant Engineering Systems through Delocalized Deformation," *Advanced Materials*, **33**(10), p. 2005647.
- [30] Pajunen, K., Celli, P., and Daraio, C., 2021, "Prestrain-induced bandgap tuning in 3D-printed tensegrity-inspired lattice structures," *Extreme Mechanics Letters*, **44**, p. 101236.
- [31] Sabouni-Zawadzka, A. A., Gilewski, W., and Zawadzki, A., 2024, "Experimental investigations on mechanical properties of 3D-printed tensegrity-inspired metamaterials based on 4-strut simplex module," *Archives of Civil Engineering*, **70**(2), pp. 343–357.
- [32] Almeida, N., Gullede, B., Park, J., Momeni, K., Tajyar, A., Davami, K., and Beck, S., 2025, "High strain rate response of 3D-printable tensegrity-inspired structures," *International Journal of Solids and Structures*, **322**, p. 113590.
- [33] Davami, K., Rowe, R., Gullede, B., Park, J., Beheshti, A., Palazotto, A., Tavangarian, F., and Beck, S., 2025, "Dynamic analysis of additively manufactured tensegrity structures," *International Journal of Impact Engineering*, **198**, p. 105208.
- [34] Wang, Z., Zhang, M., Sun, J., Wen, Q., and Chu, J., 2026, "Integrated fabrication and validation of tensegrity-inspired rigid-flexible mechanical metamaterials," *Additive Manufacturing*, **118**, p. 105107.
- [35] Arifvianto, B., Satiti, B. E., Salim, U. A., Suyitno, Nuryanti, A., and Mahardika, M., 2022, "Mechanical properties of the fff sandwich-structured parts made of pla/tpu multi-material," *Progress in Additive Manufacturing*, **7**:1213-1223, Apr 2022.
- [36] Ruwais, A. and Naveed, N., 2025, "Mechanical performance of layered pla-tpu composites using multi-material additive manufacturing," *Unknown journal*, 2025.
- [37] Ezech, O. H. and Susmel, L., 2018, "On the fatigue strength of 3d-printed polylactide (pla)," *Procedia structural integrity*, **9**:29-36, Jan 2018.
- [38] Vanaei, H. R., Shirinbayan, M., Vanaei, S., Fitoussi, J., Khelladi, S., and Tcharkhtchi, A., 2021, "Multi-scale damage analysis and fatigue behavior of pla manufactured by fused deposition modeling (fdm)," *Rapid Prototyping Journal*, **27**:371-378, Jan 2021.
- [39] Yavas, D., Liu, Q., Zhang, Z., and Wu, D., 2022, "Design and fabrication of architected multi-material lattices with tunable stiffness, strength, and energy absorption," *Materials & Design*, **217**:110613, May 2022.
- [40] Caminero, M. A., Chacón, J. M., García-Plaza, E., Núñez, P. J., Reverte, J. M., and Becar, J. P., 2019, "Additive Manufacturing of PLA-Based Composites Using Fused Filament Fabrication: Effect of Graphene Nanoplatelet Reinforcement on Mechanical Properties, Dimensional Accuracy and Texture," *Polymers*, **11**(5), p. 799.
- [41] Bustihan, A. and Botiz, I., 2026, "Recent advances in additively manufactured polymeric structures for mechanical energy absorption," *Polymers*, **18**:1019, Apr 2026.
- [42] Liu, J., Seidu, R., Hu, L., Cheng, C., Yan, S., Yang, L., and xiang Jiang, S., 2026, "Three-dimensional printed lattice structures for next generation of wearable technology," *Fashion and Textiles*, Mar 2026.
- [43] Shahriari, B., Swersky, K., Wang, Z., Adams, R. P., and de Freitas, N., 2016, "Taking the Human Out of the Loop: A Review of Bayesian Optimization," *Proceedings of the IEEE*, **104**(1), pp. 148–175.
- [44] Frazier, P. I., 2018, "A Tutorial on Bayesian Optimization," *arXiv preprint arXiv:1807.02811*.
- [45] Ament, S., Daulton, S., Eriksson, D., Balandat, M., and Bakshy, E., 2023, "Unexpected Improvements to Expected Improvement for Bayesian Optimization," *Advances in Neural Information Processing Systems*, Vol. 36, doi: 10.52202/075280-0904.
- [46] Daulton, S., Balandat, M., and Bakshy, E., 2021, "Parallel Bayesian Optimization of Multiple Noisy Objectives with Expected Hypervolume Improvement," *Advances in Neural Information Processing Systems*, Vol. 34, pp. 2187–2200, <https://arxiv.org/abs/2105.08195>
- [47] Daulton, S., Cakmak, S., Balandat, M., Osborne, M. A., Zhou, E., and Bakshy, E., 2022, "Robust Multi-Objective Bayesian Optimization Under Input Noise," *Proceedings of the 39th International Conference on Machine Learning*, Proceedings of Machine Learning Research, Vol. 162, pp. 4831–4866, <https://arxiv.org/abs/2202.07549>
- [48] Low, A. K. Y., Mekki-Berrada, F., Ostudin, A., Xie, J., Vissol-Gaudin, E., Lim, Y.-F., Gupta, A., Li, Q., Ong, Y. S., Khan, S. A., and Hippalgaonkar, K., 2024, "Evolution-guided Bayesian Optimization for Constrained Multi-Objective Optimization in Self-Driving Labs," *npj Computational Materials*, **10**, pp. 1–11.
- [49] Baptista, R. and Poloczek, M., 2018, "Bayesian Optimization of Combinatorial Structures," *Proceedings of the 35th International Conference on Machine Learning (ICML)*, pp. 462–471, <https://proceedings.mlr.press/v80/baptista18a.html>
- [50] Garrido-Merchán, E. C. and Hernández-Lobato, D., 2020, "Dealing with Categorical and Integer-Valued Variables in Bayesian Optimization with Gaussian Processes," *Neurocomputing*, Vol. 380, pp. 20–35, doi: 10.1016/j.neucom.2019.11.004.
- [51] Perdikaris, P., Raissi, M., Damianou, A., Lawrence, N. D., and Karniadakis, G. E., 2017, "Nonlinear Information Fusion Algorithms for Data-Efficient Multi-Fidelity Modelling," *Proceedings of the Royal Society A*, **473**(2198), p. 20160751.
- [52] Gibson, L. J. and Ashby, M. F., 1997, *Cellular Solids: Structure and Properties*, 2nd ed., Cambridge Solid State Science Series, Cambridge University Press.
- [53] Avallé, M., Belingardi, G., and Montanini, R., 2001, "Characterization of polymeric structural foams under compressive impact loading by means of energy-absorption diagram," *International Journal of Impact Engineering*, **25**(5), pp. 455–472.
- [54] Tan, P. J., Reid, S. R., Harrigan, J. J., Zou, Z., and Li, S., 2005, "Dynamic compressive strength properties of aluminium foams. Part I—experimental data and observations," *Journal of the Mechanics and Physics of Solids*, **53**(10), pp. 2174–2205.
- [55] Michailidis, N., Stergioudi, F., Tsouknidas, A., and Pavlidou, E., 2011, "Establishment of process parameter optimization for the manufacturing of aluminium foams and the determination of their mechanical properties," *Materials Science and Engineering: B*, **176**(1), pp. 19–25.
- [56] International Organization for Standardization, 1999, "ISO 11334-4:1999 Assistive products for walking manipulated by one arm — Requirements and test methods — Part 4: Walking sticks with three or more legs," Standard, International Organization for Standardization, <https://www.iso.org/standard/27298.html>
- [57] SAE International, 2022, "Instrumentation for Impact Test—Part 1: Electronic Instrumentation," Surface Vehicle Recommended Practice J211/1_202208, doi: 10.4271/J211/1_202208.
- [58] Eriksson, D. and Jankowiak, M., 2021, "High-Dimensional Bayesian Optimization with Sparse Axis-Aligned Subspaces," *Proceedings of the Thirty-Seventh Conference on Uncertainty in Artificial Intelligence (UAI)*, Proceedings of Machine Learning Research, Vol. 161, pp. 493–503, <https://proceedings.mlr.press/v161/eriksson21a.html>
- [59] Eriksson, D., Pearce, M., Gardner, J. R., Turner, R. D., and Poloczek, M., 2019, "Scalable Global Optimization via Local Bayesian Optimization," *Advances in*

- Neural Information Processing Systems 32 (NeurIPS 2019), pp. 5496–5507, <https://arxiv.org/abs/1910.01739>
- [60] Requejo, P. S., Wahl, D. P., Bontrager, E. L., Newsam, C. J., Gronley, J. K., Mulroy, S. J., and Perry, J., 2005, “Upper extremity kinetics during lofstrand crutch-assisted gait,” *Medical engineering & physics*, 27 1:19-29, Jan 2005.
 - [61] Rasouli, F. and Reed, K. B., 2020, “Walking assistance using crutches: a state of the art review,” *Journal of Biomechanics*, 98:109489, Jan 2020.
 - [62] Manocha, R. H. K., MacGillivray, M. K., Eshraghi, M., and Sawatzky, B. J., 2021, “Injuries associated with crutch use: a narrative review,” *PM&R*, 13:1176-1192, Dec 2021.
 - [63] da Silva, D. B.-B. and Fachin-Martins, E., 2022, “Pain mapping and health-related conditions in relation to forearm crutch usage: a cross-sectional study,” *Assistive Technology*, 34:334-340, Oct 2022.
 - [64] Dozono, K., Hachisuka, A., Wada, F., and Hachisuka, K., 2015, “Peripheral neuropathies in nonparetic upper extremities of stroke patients induced by excessive use of a walking device,” *Journal of stroke and cerebrovascular diseases : the official journal of National Stroke Association*, 24 8:1841-7, Aug 2015.
 - [65] Segura, A. and Piazza, S. J., 2007, “Mechanics of ambulation with standard and spring-loaded crutches,” *Archives of physical medicine and rehabilitation*, 88 9:1159-63, Sep 2007.
 - [66] Zhang, Y., Liu, G., Xie, S., and Liger, A., 2011, “Biomechanical evaluation of an innovative spring-loaded axillary crutch design,” *Assistive Technology*, 23:225-231, Dec 2011.
 - [67] MacGillivray, M. K., Manocha, R. H., and Sawatzky, B., 2016, “The influence of a polymer damper on swing-through crutch gait biomechanics,” *Medical engineering & physics*, 38 3:275-9, Mar 2016.
 - [68] Mottaghi, M., Woods, M. C., Danier, L., So, A., Reeves, J. M., and Pearce, J. M., 2025, “Open-source 3d printable forearm crutch,” *PLOS ONE*, Nov 2025.
 - [69] Stasiak-Cieślak, B. and Malawko, P., 2025, “Expert evaluation of attachments (caps) for orthopaedic equipment dedicated to pedestrian road users,” *Open Engineering*, Jan 2025.
 - [70] Wang, H.-Y., Wu, L., Qi, J., null, J.-T. D., and Wang, Y., 2025, “Porous lattice structure optimization in 3d printed insole design,” *Journal of Fiber Bioengineering and Informatics*, 18:29-39, Jun 2025.
 - [71] Zhang, J., Lu, S., Lin, Y., Wang, Y., Yi, X., and Fang, W., 2024, “Pressure-reducing design of 3d-printed diabetic shoe midsole utilizing auxetic lattice structure,” *Applied Sciences*, 14:5291, Jun 2024.
 - [72] Janarthanan, A. K. K. and Vaidhyanathan, B., 2024, “Additive manufacturing of smart footwear components for healthcare applications,” *Micromachines*, 16:30, Dec 2024.

List of Figures

1	Closed-loop, experiment-driven design framework. Parameterized PLA/TPU tensegrity-inspired unit cells are printed, tested under quasi-static compression and drop-weight impact, and the resulting performance data drive a Gaussian-process surrogate that recommends the next batch of designs to fabricate.	3
2	Working T_3 -prism prototype. (a) Parametric OpenSCAD model whose base radius R , cell height H , twist angle θ , strut diameter d_s , and cable diameter d_t are the design variables of Table 2. (b) A representative dual-material print from the PR #35 print history (rigid PLA struts, here in white; tendon members in orange), with callouts marking the strut diameter d_s , a tendon (cable) diameter d_t , and the cell height H ; the inter-plate twist θ is the relative rotation of the top and bottom node triangles, and the base radius R sets their circumradius.	4
3	Fabrication and characterization workflow for the multi-material tensegrity-inspired unit cells: design parameters drive parametric CAD, slicing with manually generated TPU supports, a single multi-material print on the Bambu Lab H2D, post-processing and inspection, and mechanical testing. Node photographs are representative artifacts drawn from the project's build history: the OpenSCAD T_3 -prism render (CAD), the dual-nozzle Bambu Studio slice with PLA on the left extruder and TPU on the right (slicing), an in-progress H2D print of the prism batch (FDM), an as-printed specimen (post-processing), and the bungee-assisted drop-tower base plate with accelerometer (testing).	5
4	<i>Illustrative example (synthetic data)</i> . Template for the mechanism-oriented drop-test figures planned for the Results: (a) processed deceleration response of a rigid control vs. a tensegrity specimen (SAE J211 CFC-180 filtered [57]), with event-based phase shading and numbered markers keyed to the schematic frames (b)–(d); (a2) cumulative-impulse subpanel showing the two traces transfer the same mass-normalized Δv , so the lower tensegrity peak reflects temporal redistribution rather than inconsistent loading; (e) the internal-anchor joint load path. Curves are synthetic and impulse-consistent (control anchored to the documented ~ 1792 G CFC-180 peak; tensegrity shoulder scaled to the same impulse), pending real high-rate channels and camera frames. Generated by <code>scripts/figures/mechanistic_data_figure_example.py</code>	6
5	<i>Illustrative example (synthetic data)</i> . Leave-one-out cross-validation of the Gaussian-process surrogate—predicted vs. observed specific energy absorption (SEA) and peak transmitted force, with model error bars and R^2_{LOO} —obtained from a real Ax/BoTorch run on synthetic objective values. To be regenerated from campaign data.	7
6	<i>Illustrative example (synthetic data)</i> . Parameter-sensitivity ranking (model length-scale-based importances per objective; cf. SAASBO inverse length-scales or Sobol indices) of the design variables in Table 2, from the same Ax/BoTorch run as Fig. 5.	7
7	<i>Placeholder</i> . Assembled validation specimens for each predicted performance tier (worst / mediocre / best), shown as printed PLA/TPU builds alongside their hollow-aluminum-rod and stainless-steel-threaded-cable metal analogs, with callouts marking the aluminum compression members, the threaded steel tension cables, and the strut-end cable anchors. Photographs to be added once the specimens are fabricated.	7
8	<i>Illustrative example (synthetic data)</i> . Best-so-far SEA vs. number of physical experiments for the Ax/BoTorch loop against an independent random-search baseline; the shaded region is the $n = 9$ Sobol initialization. Generated on synthetic objective values; to be replaced with campaign results (with confidence intervals over random seeds, and Pareto hypervolume for the multi-objective runs).	8
9	<i>Illustrative example (synthetic data)</i> . Pareto front in (peak transmitted force, SEA) space with all evaluated designs, from the Ax/BoTorch loop on synthetic objective values; representative geometries to be annotated once campaign data are available.	8

List of Tables

1	Positioning of this work against the most closely related prior efforts. The present study is distinguished by combining a multi-material (PLA/TPU) FDM tensegrity-inspired architecture with a closed-loop optimizer trained directly on physical measurements rather than simulations or a single fabrication condition.	4
2	Design variables for the T_3 -prism Sobol initialization batch, as implemented in the BO harness (single-iteration $n = 9$ Sobol set). The joint diameter is held fixed at the <code>t3-prism.scad</code> default; all specimens are printed in the vertical orientation and packed 3×3 on a single Bambu Lab H2D plate.	4
3	Multi-material print parameters on the Bambu Lab H2D. Cells marked <i>TBD</i> are pending confirmation; the reporting structure follows the methods section of Ye et al. [12].	5
4	<i>Placeholder (data pending)</i> . Planned rank-ordering validation: representative T_3 -prism designs predicted to be worst-, mid-, and best-performing, each fabricated as a printed PLA/TPU specimen and as a hollow-aluminum-rod / stainless-steel-cable metal analog. Entries record the measured performance metric (e.g. SEA or peak transmitted force) and the resulting rank within each material system; agreement of the two rankings indicates the optimization transfers across material systems.	7
5	<i>Placeholder</i> . Mean and CV of SEA, peak force, and compaction efficiency across n replicate prints for the top- k designs.	7