

Master thesis: documentation of task 2.2

Vinayak Gholap

1 Tasks performed

1. Implement a material model for the coupled problem
2. Extend the application code incorporating the conclusions drawn from the previous tasks
3. Implement a segregated iterative solver from the literature [3] to solve the coupled saddle point system
4. Examine material behaviour at high mechanical loads for material instability

2 Kinematics

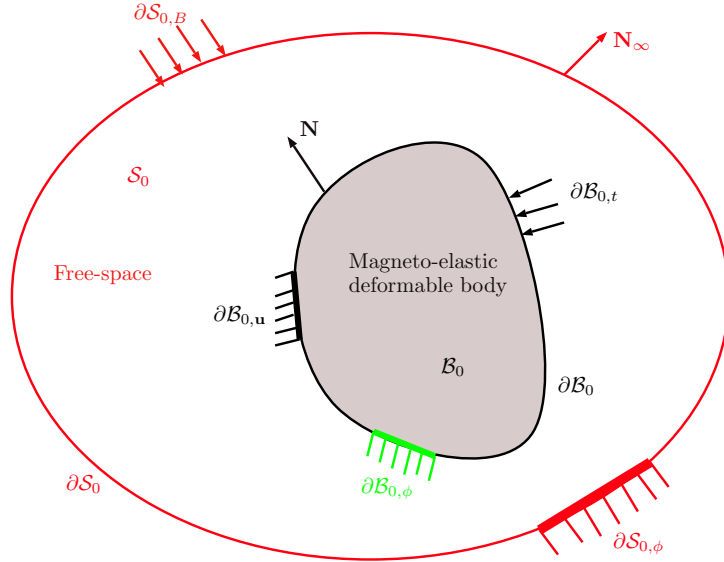


Figure 1: Domain definition: Deformable magneto-elastic solid \mathcal{B}_0 immersed in an electromagnetically permeable free space (\mathcal{S}_0).

We consider a compressible magneto-elastic deformable solid \mathcal{B}_0 with a boundary $\partial\mathcal{B}_0$ in a reference state of no stress and no deformations. In this state, the free space surrounding the deformable solid is denoted as \mathcal{S}_0 with the topologically constant/fixed boundary $\partial\mathcal{S}_0$. We denote the entire domain containing the magneto-elastic and the surrounding free space domain as $\mathcal{D}_0 := \mathcal{B}_0 \cup \mathcal{S}_0$. On application of a combined static mechanical and magnetic load, the body deforms and occupies the current state \mathcal{B}_t with boundary $\partial\mathcal{B}_t$. In the current configuration the free space is denoted as \mathcal{S}_t , the free space boundary due to fixed constraints stays constant with $\partial\mathcal{S}_0 = \partial\mathcal{S}_t$ and the entire domain is denoted as $\mathcal{D}_t := \mathcal{B}_t \cup \mathcal{S}_t$. Any point in the deformed/current configuration $\mathbf{x} \in \overline{\mathcal{D}_t}$ is identified by a one-to-one non-linear deformation map φ to $\mathbf{X} \in \overline{\mathcal{D}_0}$ as $\mathbf{x} := \varphi(\mathbf{X})$. We define the associated deformation gradient relative to reference configuration \mathcal{D}_0 as $\mathbf{F} := \nabla_0 \varphi$ and its determinant $J := \det \mathbf{F} > 0$ to ensure that φ remains invertible and it also avoid the material self-penetration. Here, the gradient w.r.t. \mathcal{D}_0 is denoted as ∇_0 and that w.r.t. \mathcal{D}_t is denoted as ∇ . \mathbf{N} describes the unit outward normal to $\partial\mathcal{B}_0$ and \mathbf{N}_∞ describes the unit outward normal to the boundary $\partial\mathcal{S}_0$. We denote the portion of boundary $\partial\mathcal{B}_{0,u}$ as the boundary with prescribed deformations and $\partial\mathcal{B}_{0,t}$ as the boundary with prescribed mechanical

traction load. The portion $\partial\mathcal{B}_{0,\phi}$ denotes the boundary with prescribed magnetic scalar-valued potential. We assume the boundary $\partial\mathcal{S}_{0,\mathbf{u}} = \partial\mathcal{S}_0$ to be prescribed with homogeneous Dirichlet boundary condition for the deformations (fixing the free space boundary topology). We apply a prescribed magnetic scalar-valued potential $\bar{\phi}$ on the portion $\partial\mathcal{S}_{0,\phi}$ to generate a magnetic vector field \mathbb{H} in \mathcal{D}_0 . Let the associated referential magnetic induction vector be \mathbb{B} and the magnetization vector be \mathbb{M} .

We proceed with the assumption that there exists no free electric currents and thus, no electric fields in the complete computational domain. As already explained in detail in Task 1, due to the magnetic vector fields such as \mathbb{H} which is discontinuous over boundaries and material interfaces, for the purpose of finite element modelling we proceed with a magnetic scalar potential formulation. We assume a fictitious quantity ϕ and define the curl-free magnetic field \mathbb{H} as [8, 10]

$$\mathbb{H} := -\nabla_0\phi \text{ in } \mathcal{D}_0. \quad (1)$$

The continuity condition associated with potential ϕ is

$$[[\phi]] = 0 \text{ on } \partial\mathcal{B}_0, \quad (2)$$

and the Dirichlet and Neumann boundary conditions are

$$\phi = \bar{\phi} \text{ on } \partial\mathcal{S}_{0,\phi}, \quad \mathbb{B}_\infty \cdot \mathbf{N}_\infty = 0 \text{ on } \partial\mathcal{S}_{0,\mathbb{B}}, \quad (3)$$

where \mathbb{B}_∞ is the prescribed magnetic induction on the far-field boundary.

3 Constitutive material model for coupled problem

The material response is characterised by a Helmholtz free energy density function. For the considered magneto-elastic material, in addition to the dependence on the deformation gradient \mathbf{F} and the Jacobian J (as already seen in quasi-static finite strain compressible elasticity, Task 2.1), the free energy density function now also depends on the referential magnetic vector field. The strain energy function (S.E.F.) is given as:

$$\Psi = \Psi(J, \mathbf{F}, \mathbb{H}) = \Psi(J, \mathbf{C}, \mathbb{H}). \quad (4)$$

Using the symmetry argument from the definition of the right Cauchy-Green deformation tensor $\mathbf{C} := \mathbf{F}^T \cdot \mathbf{F}$, the dependence of \mathbf{F} is simplified to a dependence on \mathbf{C} . The isotropic hyperelastic material response when \mathbf{C} is used to describe the S.E.F. is given by the constitutive relation as

$$\mathbf{S} = 2 \frac{\partial \Psi(J, \mathbf{C}, \mathbb{H})}{\partial \mathbf{C}}. \quad (5)$$

The referential magnetic induction vector field \mathbb{B} is modelled in terms of the referential magnetic vector field \mathbb{H} , taking \mathbb{H} as the independent field

$$\mathbb{B} = \mathbb{B}(\mathbb{H}), \quad (6)$$

which is termed as the alternative formulation in [2]. With \mathbb{H} chosen as the independent field, its components can be chosen to satisfy the vector equation $\text{Curl}\mathbb{H} = \mathbf{0}$ and then the resulting \mathbb{B} has to satisfy the scalar equation $\text{Div}\mathbb{B} = 0$. This alternative formulation does not put restrictions on the admissible class of constitutive laws (which arise if one were to proceed with \mathbb{B} as the independent field) and also avoids the complexities of a vector-valued magnetic field from the finite element modelling aspects. The fundamental constitutive equation that relates the magnetic quantities \mathbb{B} , \mathbb{H} and the magnetization vector \mathbb{M} is given as [2, 4]

$$J^{-1} \mathbf{C} \cdot \mathbb{B} = \mu_0 [\mathbb{H} + \mathbb{M}]. \quad (7)$$

The magnetization vector field exists only in the solid magneto-elastic material and vanishes in the free space. \mathbb{B} is given by another constitutive relation as [2]:

$$\mathbb{B} = -\frac{\partial \Psi(J, \mathbf{C}, \mathbb{H})}{\partial \mathbb{H}}. \quad (8)$$

The S.E.F corresponding to a compressible coupled magneto-elastic Neo-Hookean material is given as:

$$\Psi(J, \mathbf{C}, \mathbb{H}) = \frac{\mu}{2} [\mathbf{C} : \mathbf{I} - \mathbf{I} : \mathbf{I} - 2 \ln J] + \frac{\lambda}{2} (\ln J)^2 - \frac{\mu_0 \mu_r}{2} [J \mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}], \quad (9)$$

$$= \Psi_0^{\text{elas}}(\mathbf{C}) + \mu_r M_0(J, \mathbf{C}, \mathbb{H}), \quad (10)$$

$$\text{with } M_0(J, \mathbf{C}, \mathbb{H}) := -\frac{\mu_0}{2} [J \mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}], \quad (11)$$

where μ and ν are the Lamé parameters, $\mu_0 = 4\pi \times 10^{-7} \text{ Hm}^{-1}$ is the free space (vacuum) magnetic permeability and μ_r is the relative magnetic permeability of the magneto-elastic material ($\mu_r = 1$ represents the free space material). The term highlighted in red takes into account the energy stored in the body due to applied external magnetic load \mathbb{H} and the response of the coupled interaction between the displacement field and the magnetic field. The term $\Psi_0^{\text{elas}}(\mathbf{C})$ describes the purely elastic response of the material and the term $M_0(J, \mathbf{C}, \mathbb{H})$ describes the total energy per unit volume stored in the magnetic fields in the free space [2]. The constant $\mu_r > 1$ represents a magnetisable material such as the membrane.

The second Piola-Kirchhoff stress \mathbf{S} for the considered S.E.F. as stated in Equation (11) is derived below.

$$\begin{aligned} \mathbf{S} &= 2 \frac{\partial \Psi(J, \mathbf{C}, \mathbb{H})}{\partial \mathbf{C}} \\ &= 2 \left[\frac{\mu}{2} \left\{ \frac{\partial [\mathbf{C} : \mathbf{I}]}{\partial \mathbf{C}} - 2 \frac{\partial \ln J}{\partial \mathbf{C}} \right\} + \frac{\lambda}{2} \frac{\partial (\ln J)^2}{\partial \mathbf{C}} - \frac{\mu_0 \mu_r}{2} \frac{\partial [J \mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}]}{\partial \mathbf{C}} \right] \end{aligned}$$

Side calculation 1:

$$\begin{aligned} \frac{\partial [\mathbf{C} : \mathbf{I}]}{\partial \mathbf{C}} &= \mathbf{I} \\ \frac{\partial \ln J}{\partial \mathbf{C}} &= \frac{1}{J} \frac{\partial J}{\partial \mathbf{C}} \\ \frac{\partial (\ln J)^2}{\partial \mathbf{C}} &= 2 \ln J \frac{\partial \ln J}{\partial \mathbf{C}} \\ \frac{\partial J}{\partial \mathbf{C}} &= \frac{1}{2} J \mathbf{C}^{-1} \quad \text{c.f. [see 7, page 46 Equation (3.124)]} \end{aligned}$$

$$\mathbf{S} = \mu \mathbf{I} - \mu \mathbf{C}^{-1} + \lambda \ln J \mathbf{C}^{-1} - \mu_0 \mu_r \frac{\partial [J \mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}]}{\partial \mathbf{C}}$$

Side calculation 2: Note $\mathbf{C} := \mathbf{F}^T \cdot \mathbf{F}$ is symmetric $\implies \mathbf{C}^{-1}$ is also symmetric

$$\begin{aligned} \frac{\partial [J \mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}]}{\partial \mathbf{C}} &= \frac{\partial [J C_{IJ}^{-1} H_I H_J]}{\partial C_{KL}} \mathbf{E}_K \otimes \mathbf{E}_L \\ &= C_{IJ}^{-1} H_I H_J \frac{\partial J}{\partial C_{KL}} \mathbf{E}_K \otimes \mathbf{E}_L + J H_I H_J \frac{\partial C_{IJ}^{-1}}{\partial C_{KL}} \mathbf{E}_K \otimes \mathbf{E}_L \\ &= C_{IJ}^{-1} H_I H_J \frac{J}{2} C_{KL}^{-1} \mathbf{E}_K \otimes \mathbf{E}_L + J H_I H_J \frac{\partial C_{IJ}^{-1}}{\partial C_{KL}} \mathbf{E}_K \otimes \mathbf{E}_L \end{aligned}$$

c.f. [see 7, page 519]:

$$\frac{\partial C_{IJ}^{-1}}{\partial C_{KL}} = -\frac{1}{2}[C_{IK}^{-1} C_{LJ}^{-1} + C_{IL}^{-1} C_{KJ}^{-1}]$$

$$\begin{aligned} \frac{\partial [J\mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}]}{\partial \mathbf{C}} &= \frac{J}{2} C_{IJ}^{-1} H_I H_J C_{KL}^{-1} \mathbf{E}_K \otimes \mathbf{E}_L + \frac{-J}{2} [C_{IK}^{-1} C_{LJ}^{-1} H_I H_J + C_{IL}^{-1} C_{KJ}^{-1} H_I H_J] \mathbf{E}_K \otimes \mathbf{E}_L \\ &= \frac{J}{2} C_{IJ}^{-1} H_I H_J C_{KL}^{-1} \mathbf{E}_K \otimes \mathbf{E}_L - \frac{J}{2} [C_{KI}^{-1} H_I C_{LJ}^{-1} H_J + C_{LI}^{-1} H_I C_{KJ}^{-1} H_J] \mathbf{E}_K \otimes \mathbf{E}_L \\ &= \frac{J}{2} C_{IJ}^{-1} H_I H_J C_{KL}^{-1} \mathbf{E}_K \otimes \mathbf{E}_L - J[C_{KI}^{-1} H_I C_{LJ}^{-1} H_J]^{sym} \mathbf{E}_K \otimes \mathbf{E}_L \\ &= \frac{J}{2} [\mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}] \mathbf{C}^{-1} - J[(\mathbf{C}^{-1} \cdot \mathbb{H}) \otimes (\mathbf{C}^{-1} \cdot \mathbb{H})]^{sym} \end{aligned}$$

$$\mathbf{S} = \mu \mathbf{I} - [\mu - \lambda \ln J] \mathbf{C}^{-1} - \frac{\mu_0 \mu_r}{2} J [\mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}] \mathbf{C}^{-1} + \mu_0 \mu_r J [(\mathbf{C}^{-1} \cdot \mathbb{H}) \otimes (\mathbf{C}^{-1} \cdot \mathbb{H})]^{sym}$$

(12)

The referential magnetic induction vector field is given as:

$$\begin{aligned} \mathbb{B} &= -\frac{\partial \Psi(J, \mathbf{C}, \mathbb{H})}{\partial \mathbb{H}} \\ &= \frac{\mu_0 \mu_r}{2} \frac{\partial [J \mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}]}{\partial \mathbb{H}} \\ &= \frac{\mu_0 \mu_r}{2} \frac{\partial [J C_{IJ}^{-1} H_I H_J]}{\partial H_K} \mathbf{E}_K \\ &= \frac{\mu_0 \mu_r}{2} \left[J C_{IJ}^{-1} \frac{\partial H_I}{\partial H_K} H_J + J C_{IJ}^{-1} H_I \frac{\partial H_J}{\partial H_K} \right] \mathbf{E}_K \\ &= \frac{\mu_0 \mu_r}{2} [J C_{IJ}^{-1} \delta_{IK} H_J + J C_{IJ}^{-1} H_I \delta_{JK}] \mathbf{E}_K \\ &= \frac{\mu_0 \mu_r}{2} [J C_{JI}^{-1} \delta_{IK} H_J + J C_{IJ}^{-1} \delta_{JK} H_I] \mathbf{E}_K \\ &= \frac{\mu_0 \mu_r}{2} [J C_{JK}^{-1} H_J + J C_{IK}^{-1} H_I] \mathbf{E}_K \\ &= \frac{\mu_0 \mu_r}{2} [J C_{KJ}^{-1} H_J + J C_{KI}^{-1} H_I] \mathbf{E}_K \end{aligned}$$

$$\mathbb{B} = \mu_0 \mu_r J [\mathbf{C}^{-1} \cdot \mathbb{H}]$$

(13)

The referential material elasticity tangent \mathfrak{C} is defined as

$$\mathfrak{C} := 2 \frac{\partial \mathbf{S}(J, \mathbf{C}, \mathbb{H})}{\partial \mathbf{C}} = 4 \frac{\partial^2 \Psi(J, \mathbf{C}, \mathbb{H})}{\partial \mathbf{C} \otimes \partial \mathbf{C}}.$$

(14)

Using the result of Equation (12), \mathfrak{C} is derived as follows.

$$\begin{aligned}
\mathfrak{C} &= 2 \frac{\partial \mathbf{S}}{\partial \mathbf{C}} \\
&= 2 \frac{\partial S_{KL}}{\partial C_{MN}} \mathbf{E}_K \otimes \mathbf{E}_L \otimes \mathbf{E}_M \otimes \mathbf{E}_N \\
&= 2 \left\{ -\mathbf{C}^{-1} \otimes \frac{\partial [\mu - \lambda \ln J]}{\partial \mathbf{C}} - [\mu - \lambda \ln J] \frac{\partial \mathbf{C}^{-1}}{\partial \mathbf{C}} - \frac{\mu_0 \mu_r}{2} [\mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}] \mathbf{C}^{-1} \otimes \frac{\partial J}{\partial \mathbf{C}} \right\} \\
&\quad + 2 \left\{ -\frac{\mu_0 \mu_r}{2} J \mathbf{C}^{-1} \otimes \frac{\partial [\mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}]}{\partial \mathbf{C}} - \frac{\mu_0 \mu_r}{2} J [\mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}] \frac{\partial \mathbf{C}^{-1}}{\partial \mathbf{C}} \right\} \\
&\quad + 2 \left\{ \mu_0 \mu_r [(\mathbf{C}^{-1} \cdot \mathbb{H}) \otimes (\mathbf{C}^{-1} \cdot \mathbb{H})]^{sym} \otimes \frac{\partial J}{\partial \mathbf{C}} + \mu_0 \mu_r J \frac{\partial [(\mathbf{C}^{-1} \cdot \mathbb{H}) \otimes (\mathbf{C}^{-1} \cdot \mathbb{H})]^{sym}}{\partial \mathbf{C}} \right\} \\
&= 2 \left\{ C_{KL}^{-1} \frac{\lambda}{J} \frac{\partial J}{\partial C_{MN}} - [\mu - \lambda \ln J] \left\{ \frac{-1}{2} (C_{KM}^{-1} C_{NL}^{-1} + C_{KN}^{-1} C_{ML}^{-1}) \right\} \right\} \mathbf{E}_K \otimes \mathbf{E}_L \otimes \mathbf{E}_M \otimes \mathbf{E}_N \\
&\quad + 2 \left\{ -\frac{\mu_0 \mu_r}{2} [C_{IJ}^{-1} H_I H_J] C_{KL}^{-1} \frac{1}{2} J C_{MN}^{-1} - \frac{\mu_0 \mu_r}{2} J C_{KL}^{-1} \frac{\partial [C_{IJ}^{-1} H_I H_J]}{\partial C_{MN}} \right\} \mathbf{E}_K \otimes \mathbf{E}_L \otimes \mathbf{E}_M \otimes \mathbf{E}_N \\
&\quad + 2 \left\{ -\frac{\mu_0 \mu_r}{2} J [C_{IJ}^{-1} H_I H_J] \left\{ \frac{-1}{2} (C_{KM}^{-1} C_{NL}^{-1} + C_{KN}^{-1} C_{ML}^{-1}) \right\} \right\} \mathbf{E}_K \otimes \mathbf{E}_L \otimes \mathbf{E}_M \otimes \mathbf{E}_N \\
&\quad + 2 \left\{ \mu_0 \mu_r [C_{KI}^{-1} H_I C_{LJ}^{-1} H_J]^{sym} \frac{1}{2} J C_{MN}^{-1} + \mu_0 \mu_r J \frac{\partial [C_{KI}^{-1} H_I C_{LJ}^{-1} H_J]^{sym}}{\partial C_{MN}} \right\} \mathbf{E}_K \otimes \mathbf{E}_L \otimes \mathbf{E}_M \otimes \mathbf{E}_N \\
&= \lambda C_{KL}^{-1} C_{MN}^{-1} + [\mu - \lambda \ln J] (C_{KM}^{-1} C_{NL}^{-1} + C_{KN}^{-1} C_{ML}^{-1}) - \frac{\mu_0 \mu_r}{2} J [C_{IJ}^{-1} H_I H_J] C_{KL}^{-1} C_{MN}^{-1} \\
&\quad - \mu_0 \mu_r J C_{KL}^{-1} \frac{\partial [C_{IJ}^{-1} H_I H_J]}{\partial C_{MN}} + \frac{\mu_0 \mu_r}{2} J [C_{IJ}^{-1} H_I H_J] (C_{KM}^{-1} C_{NL}^{-1} + C_{KN}^{-1} C_{ML}^{-1}) \\
&\quad + \mu_0 \mu_r J [C_{KI}^{-1} H_I C_{LJ}^{-1} H_J]^{sym} C_{MN}^{-1} + 2 \mu_0 \mu_r J \frac{\partial [C_{KI}^{-1} H_I C_{LJ}^{-1} H_J]^{sym}}{\partial C_{MN}} \mathbf{E}_K \otimes \mathbf{E}_L \otimes \mathbf{E}_M \otimes \mathbf{E}_N
\end{aligned}$$

Side calculation 1:

$$\begin{aligned}
\frac{\partial [C_{IJ}^{-1} H_I H_J]}{\partial C_{MN}} &= H_I H_J \frac{\partial C_{IJ}^{-1}}{\partial C_{MN}} \\
&= \frac{-1}{2} H_I H_J [C_{IM}^{-1} C_{NJ}^{-1} + C_{IN}^{-1} C_{MJ}^{-1}] \\
&= \frac{-1}{2} [C_{MI}^{-1} H_I C_{NJ}^{-1} H_J + C_{NI}^{-1} H_I C_{MJ}^{-1} H_J] \\
&= -[C_{MI}^{-1} H_I C_{NJ}^{-1} H_J]^{sym} \\
&= -[(\mathbf{C}^{-1} \cdot \mathbb{H}) \otimes (\mathbf{C}^{-1} \cdot \mathbb{H})]^{sym}
\end{aligned}$$

Side calculation 2:

$$\begin{aligned}
\frac{\partial [C_{KI}^{-1} H_I C_{LJ}^{-1} H_J]^{sym}}{\partial C_{MN}} &= \frac{1}{2} \frac{\partial [C_{KI}^{-1} H_I C_{LJ}^{-1} H_J + C_{LI}^{-1} H_I C_{KJ}^{-1} H_J]}{\partial C_{MN}} \\
&= \frac{1}{2} \frac{\partial C_{KI}^{-1}}{\partial C_{MN}} H_I C_{LJ}^{-1} H_J + \frac{1}{2} C_{KI}^{-1} H_I \frac{\partial C_{LJ}^{-1}}{\partial C_{MN}} H_J \\
&\quad + \frac{1}{2} \frac{\partial C_{LI}^{-1}}{\partial C_{MN}} H_I C_{KJ}^{-1} H_J + \frac{1}{2} C_{LI}^{-1} H_I \frac{\partial C_{KJ}^{-1}}{\partial C_{MN}} H_J \\
&= \frac{1}{2} \frac{-1}{2} [C_{KM}^{-1} C_{NI}^{-1} + C_{KN}^{-1} C_{MI}^{-1}] H_I C_{LJ}^{-1} H_J \\
&\quad + \frac{1}{2} \frac{-1}{2} C_{KI}^{-1} H_I [C_{LM}^{-1} C_{NJ}^{-1} + C_{LN}^{-1} C_{MJ}^{-1}] H_J \\
&\quad + \frac{1}{2} \frac{-1}{2} [C_{LM}^{-1} C_{NI}^{-1} + C_{LN}^{-1} C_{MI}^{-1}] H_I C_{KJ}^{-1} H_J \\
&\quad + \frac{1}{2} \frac{-1}{2} C_{LI}^{-1} H_I [C_{KM}^{-1} C_{NJ}^{-1} + C_{KN}^{-1} C_{MJ}^{-1}] H_J \\
&= -\frac{1}{4} [C_{KM}^{-1} C_{NI}^{-1} H_I C_{LJ}^{-1} H_J + C_{KN}^{-1} C_{MI}^{-1} H_I C_{LJ}^{-1} H_J] \\
&\quad - \frac{1}{4} [C_{KI}^{-1} H_I C_{LM}^{-1} C_{NJ}^{-1} H_J + C_{KI}^{-1} H_I C_{LN}^{-1} C_{MJ}^{-1} H_J] \\
&\quad - \frac{1}{4} [C_{LM}^{-1} C_{NI}^{-1} H_I C_{KJ}^{-1} H_J + C_{LN}^{-1} C_{MI}^{-1} H_I C_{KJ}^{-1} H_J] \\
&\quad - \frac{1}{4} [C_{LI}^{-1} H_I C_{KM}^{-1} C_{NJ}^{-1} H_J + C_{LI}^{-1} H_I C_{KN}^{-1} C_{MJ}^{-1} H_J] \\
&= -\mathbb{X} - \mathbb{Y}
\end{aligned}$$

The tensors

$$\begin{aligned}
\mathbb{X} &:= \frac{1}{4} [C_{KI}^{-1} H_I C_{LM}^{-1} C_{NJ}^{-1} H_J + C_{KI}^{-1} H_I C_{LN}^{-1} C_{MJ}^{-1} H_J + C_{LI}^{-1} H_I C_{KM}^{-1} C_{NJ}^{-1} H_J + C_{LI}^{-1} H_I C_{KN}^{-1} C_{MJ}^{-1} H_J] \\
\mathbb{Y} &:= \frac{1}{4} [C_{KM}^{-1} C_{NI}^{-1} H_I C_{LJ}^{-1} H_J + C_{KN}^{-1} C_{MI}^{-1} H_I C_{LJ}^{-1} H_J + C_{LM}^{-1} C_{NI}^{-1} H_I C_{KJ}^{-1} H_J + C_{LN}^{-1} C_{MI}^{-1} H_I C_{KJ}^{-1} H_J]
\end{aligned}$$

with indices $\mathbf{E}_K \otimes \mathbf{E}_L \otimes \mathbf{E}_M \otimes \mathbf{E}_N$ are both symmetric rank-4 tensors such that for given symmetric rank-2 tensors $\mathbf{M}, \mathbf{N}, \mathbf{P}, \mathbf{Q}$, we have:

$$\begin{aligned}
\mathbf{N} &= \mathbb{X} : \mathbf{M}, \\
\mathbf{Q} &= \mathbb{Y} : \mathbf{P}.
\end{aligned}$$

$$\begin{aligned}
\mathfrak{C} &= \lambda \mathbf{C}^{-1} \otimes \mathbf{C}^{-1} - 2[\mu - \lambda \ln J] \frac{\partial \mathbf{C}^{-1}}{\partial \mathbf{C}} \\
&\quad - \frac{\mu_0 \mu_r}{2} J [\mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}] (\mathbf{C}^{-1} \otimes \mathbf{C}^{-1}) + \mu_0 \mu_r J (\mathbf{C}^{-1} \otimes [(\mathbf{C}^{-1} \cdot \mathbb{H}) \otimes (\mathbf{C}^{-1} \cdot \mathbb{H})]^{sym}) \\
&\quad - \mu_0 \mu_r J [\mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}] \frac{\partial \mathbf{C}^{-1}}{\partial \mathbf{C}} + \mu_0 \mu_r J ([(\mathbf{C}^{-1} \cdot \mathbb{H}) \otimes (\mathbf{C}^{-1} \cdot \mathbb{H})]^{sym} \otimes \mathbf{C}^{-1}) \\
&\quad - 2\mu_0 \mu_r J (\mathbb{X} + \mathbb{Y})
\end{aligned}$$

For given symmetric rank 2 tensors \mathbf{A} and \mathbf{B} , we know: $\mathbf{A} \otimes \mathbf{B} = \mathbf{B} \otimes \mathbf{A}$.

$$\begin{aligned}
\mathfrak{C} &= \lambda \mathbf{C}^{-1} \otimes \mathbf{C}^{-1} - 2[\mu - \lambda \ln J] \frac{\partial \mathbf{C}^{-1}}{\partial \mathbf{C}} \\
&\quad - \frac{\mu_0 \mu_r}{2} J [\mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}] (\mathbf{C}^{-1} \otimes \mathbf{C}^{-1}) - \mu_0 \mu_r J [\mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}] \frac{\partial \mathbf{C}^{-1}}{\partial \mathbf{C}} \\
&\quad + 2\mu_0 \mu_r J (\mathbf{C}^{-1} \cdot \mathbb{H}) \otimes (\mathbf{C}^{-1} \cdot \mathbb{H})^{sym} \otimes \mathbf{C}^{-1} - 2\mu_0 \mu_r J (\mathbb{X} + \mathbb{Y})
\end{aligned} \tag{15}$$

The fourth-order referential material elasticity tensor possess both major and minor symmetries, i.e. $\mathfrak{C} = C_{KLMN} = C_{MKNL} = C_{KLN M} = C_{LKM N}$.

4 Problem set up

4.1 Set up for the magnetic field \mathbb{H}

Following the results obtained in Task 1 and Task 2.1, the problem set up for the coupled magneto-elasticity problem is updated in view of modelling the instabilities arising in the torus membrane. Same geometry of the axisymmetric torus membrane immersed in free space is used as in the Task 1 and Task 2.1.

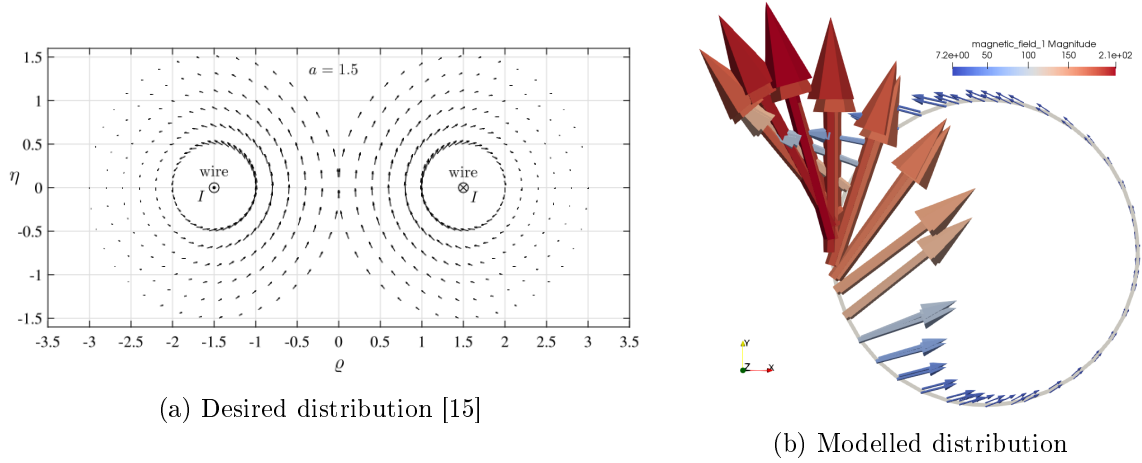


Figure 2: Resulting magnetic field in torus membrane

In Task 1 of the thesis (a purely magneto-static problem), we considered a rectangular permanent magnet placed at the center and along the axis of symmetry to generate a circulating magnetic field \mathbb{H} in \mathcal{D}_0 . A linearly varying potential function was applied to this permanent magnet region, c.f. Figure 3a. The dimension of this rectangular permanent magnet region and the potential difference per unit length to be applied were taken as user input parameters. It was observed in the results for Task 1 that the size of the magnet and the potential applied influenced the resulting magnetic field generated in the domain. A small study for this was also carried out and presented in Task 1. The important finding of this study was that the direction of the resulting magnetic field in the torus membrane did not change irrespective of increasing the magnet size and the applied potential value. The resulting magnetic field, c.f. Figure 2b, in the torus membrane on the left section (in close proximity to the permanent magnet and axis of symmetry) was comparatively high in magnitude than on the other sections of the membrane. The orientation of this large magnetic field on the left section was the same as that observed on the right section. The orientation of the magnetic field did not meet the desired result as observed in Figure 2a from [15]. The main reason for this discrepancy was the different modelling approach taken by us to generate the magnetic field compared to the approach taken in [15]. In [15], a thin current carrying wire placed along the centre line of the torus membrane was considered to generate the field \mathbb{H} . This approach is not possible from the perspective of finite element modelling and thus we had employed a permanent magnet region to generate a similar effect.

Due to such a concentrated magnetic field on one section of the membrane, modelling of instabilities arising from the coupled mechanical and magnetic static loading would not be possible. The instability behaviour of our interest is witnessed at large mechanical loads and under an uniformly distributed magnetic field of large magnitude [15, 17]. Thus, to generate a uni-

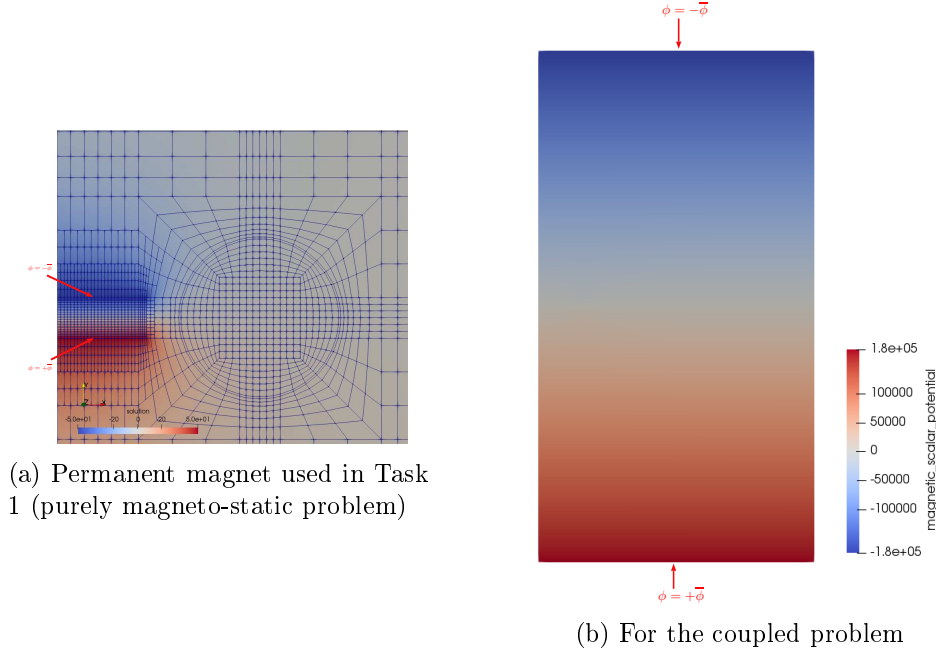


Figure 3: Applied potential difference per unit length

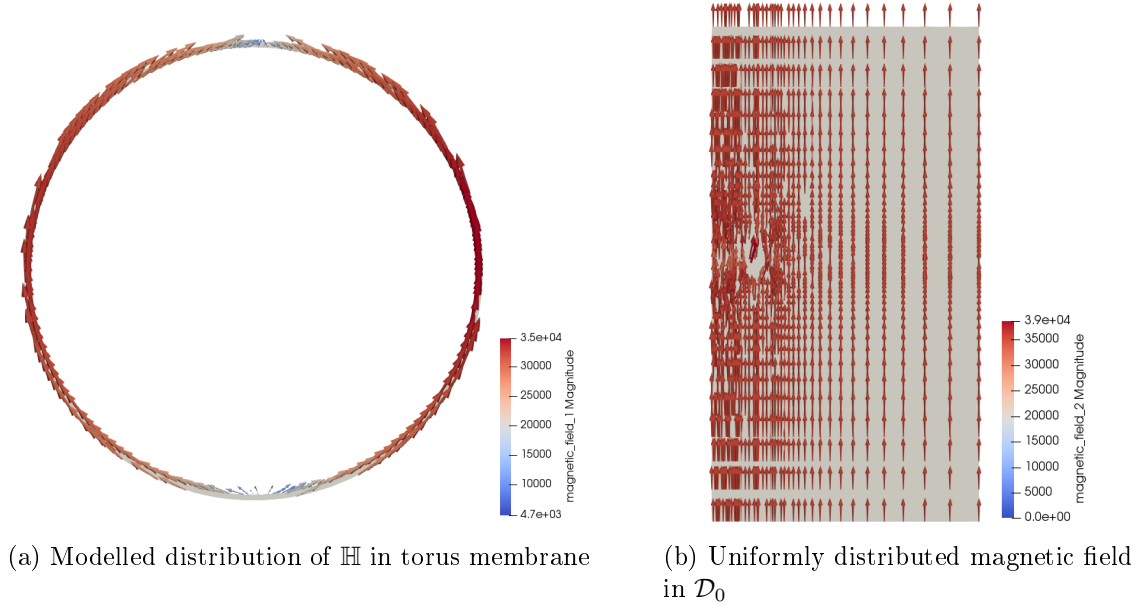


Figure 4: Resulting magnetic field \mathbb{H} for the coupled problem (Vectors are coloured and scaled to the magnitude of the magnetic field \mathbb{H})

formly distributed magnetic field in the coupled problem and to study the instabilities, a different approach was undertaken. In the new approach, we considered the top and bottom boundary of the free space $\partial\mathcal{S}_0$ as the south and the north pole of a permanent magnet, respectively. A constant potential $\bar{\phi}$ of same magnitude but opposite polarities was prescribed at the top and the bottom boundary as observed in Figure 3b. The resulting magnetic field in Figure 4b is uniformly distributed and vertically aligned. The important outcome of this approach, comparing Figure 4a to Figure 2b, is the absence of a concentrated magnetic field of high magnitude on any section of the torus membrane. Using the new approach we were able to generate a uniform magnetic field in the torus membrane. This will prove ideal to study the instability behaviour

under a quasi-static mechanical load.

4.2 Problem geometry and load application set up

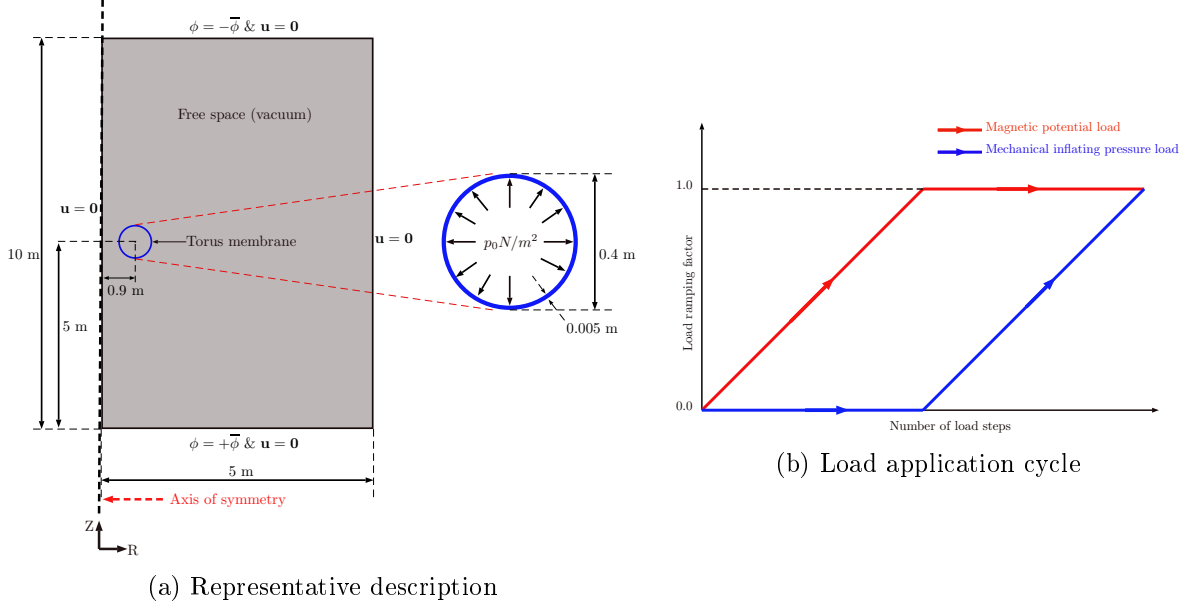


Figure 5: Coupled problem geometry and applied load set up

The problem geometry shown in Figure 5a is same as used in Task 1 and Task 2.1. However, now along with the finite elastic deformations of the circular cross-section torus membrane, we also model the magnetic scalar potential problem and study the coupled finite strain magneto-elastic deformations of this membrane immersed in the surrounding free space. The interactions between the displacement and magnetic fields and the response of the material for the coupled loads will be examined. We consider the external load application in uniformly increasing load steps as shown in Figure 5b. For the study of instabilities arising due to coupled loads, following [15], we first apply the scalar magnetic potential load $\phi = \bar{\phi}$ on the far-field free space boundary $\partial\mathcal{S}_0$ in the first half of the total number of load steps. The magnetic potential is increased linearly until the total desired magnetic potential is reached. In the next half of the total load cycle, the externally applied magnetic potential is kept constant. Thus, the established magnetic field \mathbb{H} from the first half load cycle remains constant in the second half cycle. A uniformly distributed inflating pressure load is applied on the inner interface of the torus magneto-elastic membrane as observed in Figure 5a. No mechanical load is applied in the first half of the total load application cycle. The mechanical inflating load is linearly increased with each load step in the second half of the remaining load steps until the total desired mechanical load value is reached. To model the instability behaviour with a simple set up and obtain initial understanding of the physics, we avoid the complex combined increasing load application here. Once the desired unstable deformations for a simple set up is achieved, one can then increase the complexities considered in the modelling and examine the behaviour.

The resulting magnetic field is observed in Figures 6a to 6c. As already stated, we observe the quadratic convergence of Newton solver only in close vicinity to the solution. The main advantage of the approach of linearly increasing the applied magnetic potential in small increments is that for each small increment the non-linear Newton solver would converge to a solution. Whereas if one were to apply such a large magnetic load in a single load step, we would observe no convergence and no solution corresponding to this large load value.

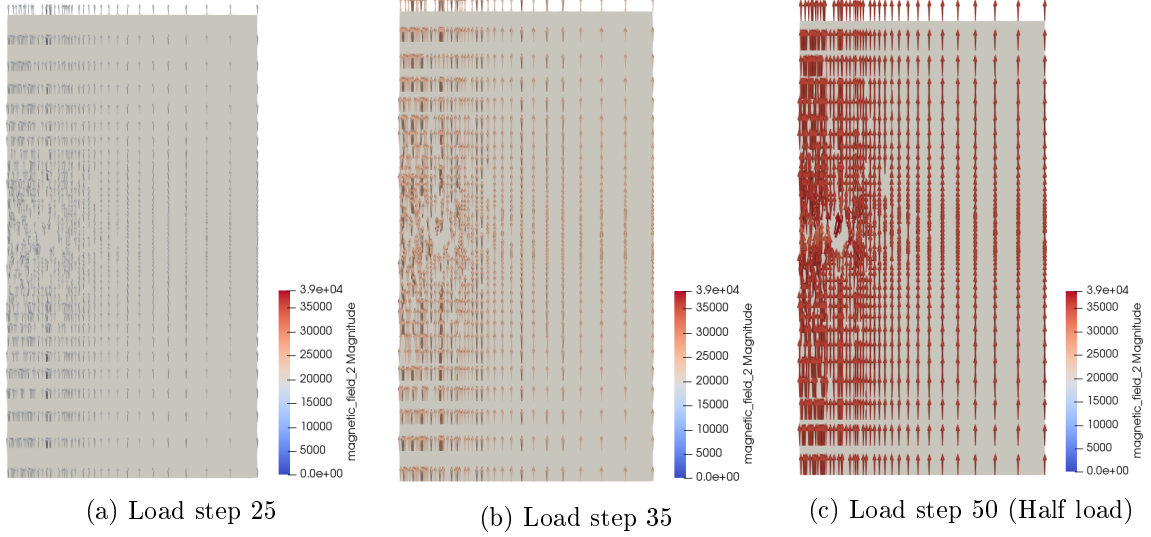


Figure 6: Increasing magnetic field \mathbb{H} with each load step in first half of the total load application cycle

5 Variational formulation

The corresponding system of partial differential equations (the strong forms of the local balance equations) for each field, the scalar-valued magnetic potential field in Task 1 and the vector-valued displacement field for an axisymmetric solid in Task 2.1, were described in details. The required boundary conditions to formulate a boundary-value problem were also mentioned for both the individual field (decoupled) problems. We now consider the fully-coupled problem of the (axisymmetric) magneto-elastic membrane immersed in a free space. The strong form of the complete system for the coupled problem in the total Lagrangian formulation is as follows:

$$\text{Kinematics : } \mathbb{H}, \mathbf{F}, \mathbf{C} := \mathbf{F}^T \cdot \mathbf{F}, \mathbf{E} := \frac{1}{2}(\mathbf{C} - \mathbf{I}) \quad (16)$$

$$\text{Equilibrium : } \text{Div} \mathbb{B} = 0 \quad (17)$$

$$\text{Div}(\mathbf{F} \cdot \mathbf{S}) + \mathbf{b}^p = \mathbf{0} \quad (18)$$

$$\text{Constitutive equation : } \mathbb{B} = - \frac{\partial \Psi(J, \mathbf{C}, \mathbb{H})}{\partial \mathbb{H}} \quad (19)$$

$$\mathbf{S} = 2 \frac{\partial \Psi(J, \mathbf{C}, \mathbb{H})}{\partial \mathbf{C}}. \quad (20)$$

The boundary conditions to be enforced for each field are:

$$\mathbf{N} \cdot \llbracket \mathbb{B} \rrbracket = 0 \text{ on } \partial \mathcal{S}_{0,\phi}, \quad (21)$$

$$\mathbf{u} = \mathbf{u}^p \text{ on } \partial \mathcal{S}_{0,\mathbf{u}}, \quad (22)$$

$$\mathbf{F} \cdot \mathbf{S} \cdot \mathbf{N} = \mathbf{t}^p \text{ on } \partial \mathcal{B}_{0,t}. \quad (23)$$

Equation (21) at the bounding surface of the free space material enforces the normal component of the referential magnetic induction vector field to remain continuous on the specified boundary [13]. This is a natural boundary condition in the unreformed configuration. Equation (22) is the homogeneous Dirichlet boundary condition for the displacement field. Here, the displacements on the free space boundary are constrained to zero. Equation (23) is the traction on the inner interface of the circular cross-section torus magneto-elastic membrane. From a mechanical perspective, this constitutes to a quasi-static inflating pressure load on the membrane and is analogues to an effect such as the air blown in a toy balloon to inflate the balloon.

Principle of stationary potential energy:

Based on the S.E.F. Equation (11), to derive the weak form of the governing equations, we define the total potential energy function as

$$\Pi = \Pi_{int} + \Pi_{ext}, \quad (24)$$

$$\text{with } \Pi_{int} = \int_{\mathcal{D}_0} \Psi(J, \mathbf{C}, \mathbb{H}) \, dV = \int_{\mathcal{B}_0} \Psi_0^{\text{elas}}(\mathbf{C}) + \mu_r \int_{\mathcal{B}_0} M_0(J, \mathbf{C}, \mathbb{H}) + \int_{\mathcal{S}_0} M_0(J, \mathbf{C}, \mathbb{H}), \quad (25)$$

$$\text{and } \Pi_{ext} = - \int_{\mathcal{B}_0} \mathbf{u} \cdot \mathbf{b}^p \, dV - \int_{\partial \mathcal{B}_{0,t}} \mathbf{u} \cdot \mathbf{t}^p \, dA - \int_{\partial \mathcal{S}_{0,\mathbb{B}}} \phi [\mathbb{B}_\infty \cdot \mathbf{N}_\infty] \, dA. \quad (26)$$

The internal energy contribution Equation (25) is a sum of total potential energy per unit volume due to magneto-elastic material's deformation and magnetisation and the magnetic energy stored in the free space. The external energy contribution Equation (26) accounts for the referential mechanical body and traction forces respectively, and the last term describes the magnetic induction prescribed on the far-field boundary of the free space material. Due to the assumption that the magnetic field and magnetic induction are co-aligned, the last term in Π_{ext} drops out.

The stationary (saddle-)point $\min_{\mathbf{u}} \max_{\phi} \Pi \implies \delta \Pi$ describes the equilibrium solution to the coupled boundary value problem. The stationary point $\min_{\mathbf{u}} \max_{\phi} \Pi$ is that point at which all the directional derivatives of the total potential energy vanish. Using the Gâteaux derivative we have

$$\begin{aligned} \delta \Pi &= D_{\delta \mathbf{u}} \Pi_{int} + D_{\delta \phi} \Pi_{int} + D_{\delta \mathbf{u}} \Pi_{ext} + D_{\delta \phi} \Pi_{ext} = 0, \\ &= \delta \Pi_{int} + \delta \Pi_{ext}. \end{aligned} \quad (27)$$

The components of the variation of the internal potential energy are given as [12]

$$D_{\delta \mathbf{u}} \Pi_{int} = \int_{\mathcal{D}_0} \delta \mathbf{E} : \mathbf{S} \, dV, \quad (28)$$

$$D_{\delta \phi} \Pi_{int} = - \int_{\mathcal{D}_0} \delta \mathbb{H} \cdot \mathbb{B} \, dV, \quad (29)$$

and that of the external potential energy are

$$D_{\delta \mathbf{u}} \Pi_{ext} = - \int_{\mathcal{B}_0} \delta \mathbf{u} \cdot \mathbf{b}^p \, dV - \int_{\partial \mathcal{B}_{0,t}} \delta \mathbf{u} \cdot \mathbf{t}^p \, dA, \quad (30)$$

$$D_{\delta \phi} \Pi_{ext} = 0. \quad (31)$$

The variations of the kinematic quantities are defined as

$$\delta \mathbf{F} = \nabla_0 \delta \mathbf{u}, \quad (32)$$

$$\delta \mathbf{E} = [\mathbf{F}^T \cdot \delta \mathbf{F}]^{\text{sym}}, \quad (33)$$

$$\delta \mathbb{H} = -\nabla_0 \delta \phi \quad \text{from Equation (1)}. \quad (34)$$

The second Piola-Kirchhoff stress \mathbf{S} in Equation (28) can further be split into two components, the total stress within the elastic body (membrane) and the Maxwell stress contribution from the free space (non-magnetisable) material respectively, as follows:

$$\mathbf{S} = \mathbf{S}^{\text{tot}} + \mathbf{S}^{\text{max}} =: 2 \frac{\partial \Psi(J, \mathbf{C}, \mathbb{H})}{\partial \mathbf{C}}, \quad (35)$$

$$\text{with } \mathbf{S}^{\text{tot}} = 2 \frac{\partial \Psi_0^{\text{elas}}(\mathbf{C})}{\partial \mathbf{C}} + 2\mu_r \frac{M_0(J, \mathbf{C}, \mathbb{H})}{\partial \mathbf{C}}, \quad (\text{note: } \mu_r > 1) \quad (36)$$

$$\text{and } \mathbf{S}^{\text{max}} = 2 \frac{M_0(J, \mathbf{C}, \mathbb{H})}{\partial \mathbf{C}} \quad (\text{note: } \mu_r = 1). \quad (37)$$

Similarly, the referential magnetic induction vector \mathbb{B} in Equation (29) can be split into the induction within the elastic solid and the induction in the free space material as

$$\mathbb{B} = \mathbb{B}^{\text{tot}} + \mathbb{B}^{\text{max}} =: -\frac{\partial \Psi(J, \mathbf{C}, \mathbb{H})}{\partial \mathbb{H}}, \quad (38)$$

$$\text{with } \mathbb{B}^{\text{tot}} = -\frac{\partial \Psi_0^{\text{elas}}(\mathbf{C})}{\partial \mathbb{H}} - \mu_r \frac{M_0(J, \mathbf{C}, \mathbb{H})}{\partial \mathbb{H}}, \quad (\text{note: } \mu_r > 1) \quad (39)$$

$$\text{and } \mathbb{B}^{\text{max}} = -\frac{M_0(J, \mathbf{C}, \mathbb{H})}{\partial \mathbb{H}}, \quad (\text{note: } \mu_r = 1). \quad (40)$$

Equations (27) to (31) collectively represent the equivalent weak form of the equilibrium equations of our interest as mentioned in Equations (17) and (18). The continuity of the normal magnetic induction as given in Equation (21) at the material interfaces is also satisfied within this formulation.

The variations in Equations (29) and (30) belong to the following space

$$\delta \mathbf{u} \in H^1(\overline{\mathcal{B}_0}), \quad \delta \phi \in H^1(\overline{\mathcal{B}_0} \cup \mathcal{S}_0), \quad (41)$$

with the constraints

$$\delta \mathbf{u} = \mathbf{0} \text{ on } \partial \mathcal{B}_{0,\mathbf{u}} \cup [\overline{\mathcal{S}_0} \setminus \Gamma_{0,\mathcal{BS}}], \quad \delta \phi = 0 \text{ on } \partial \mathcal{B}_{0,\phi} \text{ and } \partial \mathcal{S}_{0,\phi}, \quad (42)$$

where $\Gamma_{0,\mathcal{BS}} = \overline{\mathcal{S}_0} \cap \overline{\mathcal{B}_0}$ indicates the boundary of the magneto-elastic solid body exposed to the free space material. As the employed material law for the magneto-elastic material is non-linear Neo-Hookean, the linearisation of Equations (28) and (29) ($\delta \Pi_{\text{int}}$) is required within an iterative solution scheme such as the Newton-Raphson method to find the stationary point of the saddle-point system.

6 Linearisation of coupled problem

Assuming the state of the system is known at some load or time step t_{n-1} , the linearisation by employing the first-order Taylor expansion of the variation of total potential energy is given as: Find $\Delta \mathbf{u}$ and $\Delta \phi$ such that

$$\mathbf{L}[\delta \Pi]_{\phi_{i+1}, \mathbf{u}_{i+1}} = \delta \Pi \Big|_{\phi_i, \mathbf{u}_i} + D_{\Delta \phi} \left[D_{\delta \phi} \Pi_{\text{int}} + D_{\delta \mathbf{u}} \Pi_{\text{int}} \right] + D_{\Delta \mathbf{u}} \left[D_{\delta \phi} \Pi_{\text{int}} + D_{\delta \mathbf{u}} \Pi_{\text{int}} \right], \quad (43)$$

where $\Delta \{\cdot\} := \{\cdot\}_{i+1} - \{\cdot\}_i$ is the incremental change between the iterative solver iterations i and $i+1$ and the value of a quantity at the current Newton iteration at the currently unknown load/time state t_n is denoted as $\{\cdot\}_i^n = \{\cdot\}_i$.

Assuming dead load ($\mathbf{b}^p = \mathbf{0}$), the direct terms of linearisation are given as:

$$D_{\Delta \phi, \delta \phi}^2 \Pi_{\text{int}} = - \int_{\mathcal{D}_0} \delta \mathbb{H} \cdot \mathbf{D} \cdot \Delta \mathbb{H} \, dV, \quad (44)$$

$$D_{\Delta \mathbf{u}, \delta \mathbf{u}}^2 \Pi_{\text{int}} = \int_{\mathcal{D}_0} \Delta \delta \mathbf{E} : \mathbf{S} \, dV + \int_{\mathcal{D}_0} \delta \mathbf{E} : \mathfrak{C} : \Delta \mathbf{E} \, dV, \quad (45)$$

where $\Delta \delta \mathbf{E} = [\Delta \mathbf{F}^T \cdot \delta \mathbf{F}]^{\text{sym}}$, $\mathbf{D} := \frac{\partial \mathbb{B}}{\partial \mathbb{H}} = -\frac{\partial^2 \Psi(J, \mathbf{C}, \mathbb{H})}{\partial \mathbb{H} \otimes \partial \mathbb{H}}$ is the rank-2 magneto-static tensor and $\mathfrak{C} := 2 \frac{\partial \mathbf{S}}{\partial \mathbf{C}} = 4 \frac{\partial^2 \Psi(J, \mathbf{C}, \mathbb{H})}{\partial \mathbf{C} \otimes \partial \mathbf{C}}$ is the referential elastic tangent as derived earlier in Equation (15). The detailed linearisation of the kinematical quantity \mathbf{E} , i.e. the Green-Lagrange strain tensor, and the constitutive equation \mathbf{S} , the second Piola-Kirchhoff stress tensor is already discussed in Task 2.1 and the same result applies here.

The coupled terms arising from the linearisation are

$$D_{\Delta\phi, \delta\mathbf{u}}^2 \Pi_{int} = - \int_{\mathcal{D}_0} \delta\mathbf{E} : \mathbb{P} \cdot \Delta\mathbb{H} \, dV, \quad (46)$$

$$D_{\Delta\mathbf{u}, \delta\phi}^2 \Pi_{int} = - \int_{\mathcal{D}_0} \delta\mathbb{H} \cdot \mathbb{P}^T : \Delta\mathbf{E} \, dV, \quad (47)$$

where $\mathbb{P} := -\frac{\partial\mathbf{S}}{\partial\mathbb{H}} = -2\frac{\partial^2\Psi(J, \mathbf{C}, \mathbb{H})}{\partial\mathbf{C} \otimes \mathbb{H}}$ and $\mathbb{P}^T := 2\frac{\partial\mathbb{B}}{\partial\mathbf{C}} = -2\frac{\partial^2\Psi(J, \mathbf{C}, \mathbb{H})}{\partial\mathbb{H} \otimes \partial\mathbf{C}}$ are the referential magneto-elasticity tensors.

The final linear form of Equation (27) can be written as:

$$\begin{aligned} D_{\delta\phi}\Pi + D_{\Delta\phi, \delta\phi}^2\Pi + D_{\Delta\phi, \delta\mathbf{u}}^2\Pi &= \mathbf{0}, \\ D_{\delta\mathbf{u}}\Pi + D_{\Delta\mathbf{u}, \delta\mathbf{u}}^2\Pi + D_{\Delta\mathbf{u}, \delta\phi}^2\Pi &= \mathbf{0}. \end{aligned} \quad (48)$$

The derived forms for the terms \mathbf{D} and \mathbb{P} will be presented below. To derive \mathbf{D} , we first need to derive the referential magnetic induction vector as follows:

$$\begin{aligned} \mathbb{B} &= -\frac{\partial\Psi(J, \mathbf{C}, \mathbb{H})}{\partial\mathbb{H}} = -\frac{\partial M_0(J, \mathbf{C}, \mathbb{H})}{\partial\mathbb{H}} \\ &= \frac{\mu_0\mu_r}{2} \frac{\partial[J \mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}]}{\partial\mathbb{H}} \\ &= \frac{\mu_0\mu_r}{2} \frac{\partial[J C_{IJ}^{-1} H_I H_J]}{\partial H_K} \mathbf{E}_K \\ &= \frac{\mu_0\mu_r}{2} \left[J C_{IJ}^{-1} \frac{\partial H_I}{\partial H_K} H_J + J C_{IJ}^{-1} H_I \frac{\partial H_J}{\partial H_K} \right] \mathbf{E}_K \\ &= \frac{\mu_0\mu_r}{2} [J C_{IJ}^{-1} \delta_{IK} H_J + J C_{IJ}^{-1} H_I \delta_{JK}] \mathbf{E}_K \\ &= \frac{\mu_0\mu_r}{2} J [C_{JI}^{-1} \delta_{IK} H_J + C_{IJ}^{-1} \delta_{JK} H_I] \mathbf{E}_K \\ &= \frac{\mu_0\mu_r}{2} J [C_{JK}^{-1} H_J + C_{IK}^{-1} H_I] \mathbf{E}_K \\ &= \frac{\mu_0\mu_r}{2} J [C_{KJ}^{-1} H_J + C_{KI}^{-1} H_I] \mathbf{E}_K \end{aligned}$$

$$\mathbb{B} = \mu_0\mu_r J [\mathbf{C}^{-1} \cdot \mathbb{H}]. \quad (49)$$

The derivation for the rank-2 magnetic tensor \mathbf{D} is as follows:

$$\begin{aligned} \mathbf{D} &= \frac{\partial\mathbb{B}}{\partial\mathbb{H}} \\ &= \frac{\partial[\mu_0\mu_r J (\mathbf{C}^{-1} \cdot \mathbb{H})]}{\partial\mathbb{H}} \\ &= \mu_0\mu_r J \frac{\partial(C_{IJ}^{-1} H_J)}{\partial H_K} \mathbf{E}_I \otimes \mathbf{E}_K \\ &= \mu_0\mu_r J C_{IJ}^{-1} \frac{\partial H_J}{\partial H_K} \mathbf{E}_I \otimes \mathbf{E}_K \\ &= \mu_0\mu_r J C_{IJ}^{-1} \delta_{JK} \mathbf{E}_I \otimes \mathbf{E}_K \\ &= \mu_0\mu_r J C_{IK}^{-1} \mathbf{E}_I \otimes \mathbf{E}_K \end{aligned}$$

$$\mathbf{D} = \mu_0\mu_r J \mathbf{C}^{-1}. \quad (50)$$

The magneto-elasticity tensor quantity \mathbb{P} defines the sensitivity of the second Piola-Kirchhoff stress \mathbf{S} w.r.t. the applied referential magnetic field \mathbb{H} and can be derived as follows:

$$\mathbb{P} = -\frac{\partial \mathbf{S}}{\partial \mathbb{H}} = -\frac{\partial}{\partial \mathbb{H}} \left(2 \frac{\partial \Psi(J, \mathbf{C}, \mathbb{H})}{\partial \mathbf{C}} \right) = -2 \frac{\partial^2 \Psi(J, \mathbf{C}, \mathbb{H})}{\partial \mathbf{C} \otimes \partial \mathbb{H}}$$

Employing the result of Equation (12) for \mathbf{S} , we have

$$= \frac{\mu_0 \mu_r}{2} J \left[\mathbf{C}^{-1} \otimes \frac{\partial}{\partial \mathbb{H}} (\mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H}) \right] - \mu_0 \mu_r J \frac{\partial [(\mathbf{C}^{-1} \cdot \mathbb{H}) \otimes (\mathbf{C}^{-1} \cdot \mathbb{H})]^{sym}}{\partial \mathbb{H}}$$

Side calculation 1:

$$\begin{aligned} \frac{\partial (\mathbf{C}^{-1} : \mathbb{H} \otimes \mathbb{H})}{\partial \mathbb{H}} &= \frac{\partial (C_{IJ}^{-1} H_I H_J)}{\partial H_K} \mathbf{E}_K \\ &= [C_{IJ}^{-1} \delta_{IK} H_J + C_{IJ}^{-1} H_I \delta_{JK}] \mathbf{E}_K \\ &= [C_{JI}^{-1} \delta_{IK} H_J + C_{IJ}^{-1} \delta_{JK} H_I] \mathbf{E}_K \\ &= [C_{JK}^{-1} H_J + C_{IK}^{-1} H_I] \mathbf{E}_K \\ &= [C_{KJ}^{-1} H_J + C_{KI}^{-1} H_I] \mathbf{E}_K \\ &= 2[\mathbf{C}^{-1} \cdot \mathbb{H}] \end{aligned}$$

Side calculation 2:

$$\begin{aligned} \frac{\partial [(\mathbf{C}^{-1} \cdot \mathbb{H}) \otimes (\mathbf{C}^{-1} \cdot \mathbb{H})]^{sym}}{\partial \mathbb{H}} &= \frac{1}{2} \frac{\partial [C_{IM}^{-1} H_M C_{JN}^{-1} H_N + C_{JM}^{-1} H_M C_{IN}^{-1} H_N]}{\partial H_K} \mathbf{E}_I \otimes \mathbf{E}_J \otimes \mathbf{E}_K \\ &= \frac{1}{2} [C_{IM}^{-1} \delta_{MK} C_{JN}^{-1} H_N + C_{IM}^{-1} H_M C_{JN}^{-1} \delta_{NK}] \mathbf{E}_I \otimes \mathbf{E}_J \otimes \mathbf{E}_K \\ &\quad + \frac{1}{2} [C_{JM}^{-1} \delta_{MK} C_{IN}^{-1} H_N + C_{JM}^{-1} H_M C_{IN}^{-1} \delta_{NK}] \mathbf{E}_I \otimes \mathbf{E}_J \otimes \mathbf{E}_K \\ &= \frac{1}{2} [C_{IK}^{-1} C_{JN}^{-1} H_N + C_{IM}^{-1} H_M C_{JK}^{-1}] \mathbf{E}_I \otimes \mathbf{E}_J \otimes \mathbf{E}_K \\ &\quad + \frac{1}{2} [C_{JK}^{-1} C_{IN}^{-1} H_N + C_{JM}^{-1} H_M C_{IK}^{-1}] \mathbf{E}_I \otimes \mathbf{E}_J \otimes \mathbf{E}_K \end{aligned}$$

Observing the symmetry over the indices I and J , we have

$$\begin{aligned} &= [C_{IK}^{-1} C_{JN}^{-1} H_N + C_{IM}^{-1} H_M C_{JK}^{-1}] \mathbf{E}_I \otimes \mathbf{E}_J \otimes \mathbf{E}_K \\ &= \mathbf{C}^{-1} \otimes (\mathbf{C}^{-1} \cdot \mathbb{H}) + (\mathbf{C}^{-1} \cdot \mathbb{H}) \otimes \mathbf{C}^{-1} \end{aligned}$$

$$\mathbb{P} = \mu_0 \mu_r J [\mathbf{C}^{-1} \otimes (\mathbf{C}^{-1} \cdot \mathbb{H})] - \mu_0 \mu_r J [\mathbf{C}^{-1} \otimes (\mathbf{C}^{-1} \cdot \mathbb{H}) + (\mathbf{C}^{-1} \cdot \mathbb{H}) \otimes \mathbf{C}^{-1}]. \quad (51)$$

7 Space discretization by finite element method

We now discretize the variational form Equation (48) by introducing the standard Lagrangian finite element basis for the scalar-valued magnetic potential ϕ and the vector-valued displacement \mathbf{u} as

$$\phi(\mathbf{X}) \approx \phi^h(\mathbf{X}) = \sum_I \phi_I N_I(\mathbf{X}), \quad \mathbf{u}(\mathbf{X}) \approx \mathbf{u}^h(\mathbf{X}) = \sum_I u_I \mathbf{N}_I(\mathbf{X}), \quad (52)$$

$$\nabla_0 \phi(\mathbf{X}) \approx \nabla_0 \phi^h(\mathbf{X}) = \sum_I \phi_I \nabla_0 N_I(\mathbf{X}), \quad \nabla_0 \mathbf{u}(\mathbf{X}) \approx \nabla_0 \mathbf{u}^h(\mathbf{X}) = \sum_I u_I \nabla_0 \mathbf{N}_I(\mathbf{X}), \quad (53)$$

with $\phi_I \in \mathbb{R}$ and $u_I \in \mathbb{R}$. N_I and \mathbf{N}_I are, respectively, the scalar-valued and vector-valued shape functions corresponding to the global degree of freedom (support point) I . Let the collective solution vector be called as $\mathbf{d} = \{\phi; \mathbf{u}\}^T$. The shape functions belong to the Sobolev space which is defined as

$$H^1(\mathcal{D}_0; \mathbb{R}^{\dim}) = \left\{ \mathbf{d} : \mathcal{D}_0 \mapsto \mathbb{R} \left| \int_{\mathcal{D}_0} \|\mathbf{d}\|^2 + \|\nabla \mathbf{d}\|^2 \, d\mathcal{D}_0 < \infty \right. \right\}. \quad (54)$$

The discrete function spaces for the solution fields are given as

$$S^h = \left\{ \phi^h \in H^1, \phi^h|_{\partial \mathcal{S}_{0,\phi}} = \overline{\phi^h} \right\}, \quad (55)$$

$$\mathbf{W}^h = \left\{ \mathbf{u}^h \in H^1, \mathbf{u}^h|_{\partial \mathcal{B}_{0,\mathbf{u}} \cup \partial \mathcal{S}_{0,\mathbf{u}}} = \overline{\mathbf{u}^h} \right\}. \quad (56)$$

The variations and linearization of the discretized fields are given as

$$\delta \phi^h(\mathbf{X}) = \sum_I \delta \phi_I N_I(\mathbf{X}), \quad \delta \mathbf{u}^h(\mathbf{X}) = \sum_I \delta u_I \mathbf{N}_I(\mathbf{X}), \quad (57)$$

$$\Delta \phi^h(\mathbf{X}) = \sum_I \Delta \phi_I N_I(\mathbf{X}), \quad \Delta \mathbf{u}^h(\mathbf{X}) = \sum_I \Delta u_I \mathbf{N}_I(\mathbf{X}), \quad (58)$$

with $\delta \phi_I, \Delta \phi_I \in \mathbb{R}$ and $\delta u_I, \Delta u_I \in \mathbb{R}$.

The discrete function spaces for the variation of the solution fields are given as

$$T^h = \left\{ \delta \phi^h \in H^1, \delta \phi^h|_{\partial \mathcal{S}_{0,\phi}} = 0 \right\}, \quad (59)$$

$$\mathbf{V}^h = \left\{ \delta \mathbf{u}^h \in H^1, \delta \mathbf{u}^h|_{\partial \mathcal{B}_{0,\mathbf{u}} \cup \partial \mathcal{S}_{0,\mathbf{u}}} = \mathbf{0} \right\}. \quad (60)$$

The derivatives of the increments of the solution fields are given as

$$\nabla_0 \Delta \phi^h(\mathbf{X}) = \sum_I \Delta \phi_I \nabla_0 N_I(\mathbf{X}), \quad \nabla_0 \Delta \mathbf{u}^h(\mathbf{X}) = \sum_I \Delta u_I \nabla_0 \mathbf{N}_I(\mathbf{X}). \quad (61)$$

The resulting discretized system of equations for the final linearised variational form Equation (48) employing the results from Equations (28) to (31), Equations (44) to (47) and the definitions for the variations Equation (34) can be written in the form of the following L.H.S. and R.H.S.:

$$\begin{aligned} \text{L.H.S.:} = & - \sum_I \sum_J \delta \phi_I \int_{\mathcal{D}_0} [\nabla_0 N_I(\mathbf{X}) \cdot \mathbf{D} \cdot \nabla_0 N_J(\mathbf{X})] \cdot \Delta \phi_J \, dV \\ & + \sum_I \sum_J \delta u_I \int_{\mathcal{D}_0} [[\mathbf{F}^T \cdot \nabla_0 \mathbf{N}_I(\mathbf{X})] : \mathbb{P} \cdot \nabla_0 N_J(\mathbf{X})] \cdot \Delta \phi_J \, dV \\ & + \sum_I \sum_J \delta \phi_I \int_{\mathcal{D}_0} [\nabla_0 N_I(\mathbf{X}) \cdot \mathbb{P}^T : [\mathbf{F}^T \cdot \nabla_0 \mathbf{N}_J(\mathbf{X})]] \cdot \Delta u_J \, dV \\ & + \sum_I \sum_J \delta u_I \int_{\mathcal{D}_0} [[\nabla_0 \mathbf{N}_I^T(\mathbf{X}) \cdot \nabla_0 \mathbf{N}_J(\mathbf{X})]^{\text{sym}} : \mathbf{S}] \cdot \Delta u_J \, dV \\ & + \sum_I \sum_J \delta u_I \int_{\mathcal{D}_0} [[\mathbf{F}^T \cdot \nabla_0 \mathbf{N}_I(\mathbf{X})]^{\text{sym}} : \mathfrak{C} : [\mathbf{F}^T \cdot \nabla_0 \mathbf{N}_J(\mathbf{X})]^{\text{sym}}] \cdot \Delta u_J \, dV. \end{aligned} \quad (62)$$

$$\begin{aligned}
\text{R.H.S.:} = & - \sum_I \delta u_I \int_{\mathcal{D}_0} \left[[\mathbf{F}^T \cdot \nabla_0 \mathbf{N}_I(\mathbf{X})]^{\text{sym}} : \mathbf{S} \right] dV \\
& - \sum_I \delta \phi_I \int_{\mathcal{D}_0} [\nabla_0 N_I(\mathbf{X}) \cdot \mathbb{B}] dV \\
& + \sum_I \delta u_I \int_{\partial \mathcal{B}_{0,t}} [\mathbf{N}_I(\mathbf{X}) \cdot \mathbf{t}^p] dA.
\end{aligned} \tag{63}$$

The resulting discretized equations Equations (62) and (63) must hold for all arbitrary variations $\delta \phi_I$ and δu_I . The algebraic system to be solved at time/load step t_n and Newton iterate i is

$$\begin{bmatrix} \mathbf{K}_{\phi\phi} & \mathbf{K}_{\phi\mathbf{u}} \\ \mathbf{K}_{\mathbf{u}\phi} & \mathbf{K}_{\mathbf{u}\mathbf{u}} \end{bmatrix} \begin{bmatrix} \Delta \mathbf{d}_\phi \\ \Delta \mathbf{d}_\mathbf{u} \end{bmatrix} = \begin{bmatrix} -\mathbf{R}_\phi \\ -\mathbf{R}_\mathbf{u} \end{bmatrix} \implies \mathbf{K} \cdot \Delta \mathbf{d} = -\mathbf{R}. \tag{64}$$

The solution update is then performed as follows

$$\mathbf{d}_{i+1}^n = \mathbf{d}_i^n + \Delta \mathbf{d}^n. \tag{65}$$

Applying the Gauss quadrature rule for the numerical integration and also considering the transformation needed for the axisymmetric formulation (as previously discussed in Task 1 and 2.1), the final cell wise FE assembly is given as follows:

$$\begin{aligned}
K_{IJ} = & - \sum_q [\nabla_0 N_I(q) \cdot \mathbf{D} \cdot \nabla_0 N_J(q)] \text{ C.S.F. } J \text{ } w(q) \\
& + \sum_q \left[[\mathbf{F}^T \cdot \nabla_0 \mathbf{N}_I(q)] : \mathbb{P} \cdot \nabla_0 N_J(q) \right] \text{ C.S.F. } J \text{ } w(q) \\
& + \sum_q \left[\nabla_0 N_I(q) \cdot \mathbb{P}^T : [\mathbf{F}^T \cdot \nabla_0 \mathbf{N}_J(q)] \right] \text{ C.S.F. } J \text{ } w(q) \\
& + \sum_q \left[[\nabla_0 \mathbf{N}_I^T(q) \cdot \nabla_0 \mathbf{N}_J(q)]^{\text{sym}} : \mathbf{S} \right] \text{ C.S.F. } J \text{ } w(q) \\
& + \sum_q \left[[\mathbf{F}^T \cdot \nabla_0 \mathbf{N}_I(q)]^{\text{sym}} : \mathfrak{C} : [\mathbf{F}^T \cdot \nabla_0 \mathbf{N}_J(q)]^{\text{sym}} \right] \text{ C.S.F. } J \text{ } w(q),
\end{aligned} \tag{66}$$

and with $\mathbf{f} := -\mathbf{R}$

$$\begin{aligned}
f_I = & - \sum_q \left[[\mathbf{F}^T \cdot \nabla_0 \mathbf{N}_I(q)]^{\text{sym}} : \mathbf{S} \right] \text{ C.S.F. } J \text{ } w(q) \\
& - \sum_q [\nabla_0 N_I(q) \cdot \mathbb{B}] \text{ C.S.F. } J \text{ } w(q) \\
& + \sum_q [\mathbf{N}_I(q) \cdot \mathbf{t}^p] \text{ C.S.F. } J \text{ } w(q),
\end{aligned} \tag{67}$$

where q are the local quadrature points with corresponding weights $w(q)$ and the scalar $\text{C.S.F.} := 2\pi R$ is the co-ordinate scaling factor arising from the transformation of the 3D integrals to the axisymmetric (2.5D) integrals. R is the axial component of the distance of the local quadrature point q from the axis of symmetry. Equations (66) and (67) represents the final FE assembly we have implemented for the axisymmetric fully-coupled magneto-elastic problem of our interest.

8 Implementation details

8.1 Saddle point system

At any Newton iteration i and time/load step t_n the algebraic equations to solve are as represented in Equation (64). Consider the scalar-valued magnetic potential solution block vector \mathbf{d}_ϕ

be of size p and the vector-valued displacement solution block vector \mathbf{d}_u for an axisymmetric formulation be of size q . Then the total number of unknowns, called as number of global DoFs, will be $n_{dofs} = p + q$. For the case where the same order finite elements are employed for both the fields, for e.g., for a total number of support points n_d , for linear Lagrange finite element (Q_1) used for the solution field ϕ with $p = n_d$ and bi-linear Lagrange finite elements ($Q_1 \times Q_1$) for the solution field \mathbf{u} with $q = 2n_d$, then the total number of unknowns would be $n_{dofs} = 3n_d$. By definition, a support point is a point p_i such that for a shape function N_j (finite element families based on the Lagrange interpolation) it holds $N_j(p_i) = \delta_{ij}$. The corresponding tangent matrix blocks will be of the following dimensions:

$$\mathbf{K}_{\phi\phi} \in \mathbb{R}^{p \times p}, \mathbf{K}_{\phi u} \in \mathbb{R}^{p \times q}, \mathbf{K}_{u\phi} \in \mathbb{R}^{q \times p}, \mathbf{K}_{uu} \in \mathbb{R}^{q \times q}. \quad (68)$$

The system of equations in Equation (64) represents a saddle point system for the coupled multi-physics problem of our interest. Saddle point systems arise when a certain quantity such as the energy of a continuum body has to be minimized, subject to a set of linear constraints. The constraints typically represent some basic conservation law such as the balance law of linear momentum in our case of non-linear solid mechanics. Because saddle point systems can be derived as equilibrium conditions for a physical system, they are sometimes also referred to a *equilibrium equations* [3]. We therefore briefly discuss the saddle point systems and also mention the necessary requirements to be satisfied for a linear system of equations to be classified as a saddle point system.

For a general linear system

$$\begin{bmatrix} \mathbf{A} & \mathbf{B} \\ \mathbf{C} & \mathbf{D} \end{bmatrix} \begin{bmatrix} \mathbf{x} \\ \mathbf{y} \end{bmatrix} = \begin{bmatrix} \mathbf{f} \\ \mathbf{g} \end{bmatrix} \implies \mathbf{K} \cdot \mathbf{u} = \mathbf{r} \quad (69)$$

equivalent to Equation (64) to be classified as a (generalized) saddle point problem, the individual blocks $\mathbf{A}, \mathbf{B}, \mathbf{C}, \mathbf{D}$ of the tangent matrix \mathbf{K} have to satisfy one or more of the following conditions [3]:

C1 \mathbf{A} is symmetric: $\mathbf{A} = \mathbf{A}^T$

C2 Symmetric part of \mathbf{A} , $\mathbf{A}^{sym} = \frac{1}{2}(\mathbf{A} + \mathbf{A}^T)$, is positive semidefinite

C3 $\mathbf{B} = \mathbf{C}$

C4 \mathbf{D} is symmetric and positive semidefinite

C5 $\mathbf{D} = \mathbf{0}$ (zero matrix)

When all the above conditions are satisfied, the tangent matrix \mathbf{K} is symmetric positive semidefinite and we have a symmetric linear system of equations. Consider the following minimization problem:

$$J(\mathbf{u}) = \frac{1}{2} \langle \mathbf{K} \cdot \mathbf{u}, \mathbf{u} \rangle - \langle \mathbf{r}, \mathbf{u} \rangle, \quad (70)$$

subject to

$$\mathbf{C} \cdot \mathbf{x} = \mathbf{g}, \quad (71)$$

with $\langle \cdot, \cdot \rangle$ denoting the standard inner product in \mathbb{R}^{p+q} . Note that

$$\nabla J(\mathbf{u}) = \mathbf{K} \cdot \mathbf{u} - \mathbf{r}. \quad (72)$$

Any solution $(\mathbf{x}_*, \mathbf{y}_*)^T$ of the general case (satisfying all of the conditions C1-C5), is a saddle point of the Lagrangian defined as

$$\mathcal{L}(\mathbf{x}, \mathbf{y}) = \frac{1}{2} \langle \mathbf{K} \cdot \mathbf{u}, \mathbf{u} \rangle - \langle \mathbf{r}, \mathbf{u} \rangle + (\mathbf{C} \cdot \mathbf{x} - \mathbf{g})^T \cdot \mathbf{y}. \quad (73)$$

The saddle point $(\mathbf{x}_*, \mathbf{y}_*)^T \in \mathbb{R}^{p+q}$ satisfies

$$\mathcal{L}(\mathbf{x}_*, \mathbf{y}) \leq \mathcal{L}(\mathbf{x}_*, \mathbf{y}_*) \leq \mathcal{L}(\mathbf{x}, \mathbf{y}_*) \quad \forall \mathbf{x} \in \mathbb{R}^p \text{ \& } \forall \mathbf{y} \in \mathbb{R}^q, \quad (74)$$

or equivalently,

$$\min_{\mathbf{x}} \max_{\mathbf{y}} \mathcal{L}(\mathbf{x}, \mathbf{y}) = \mathcal{L}(\mathbf{x}_*, \mathbf{y}_*) = \max_{\mathbf{x}} \min_{\mathbf{y}} \mathcal{L}(\mathbf{x}, \mathbf{y}). \quad (75)$$

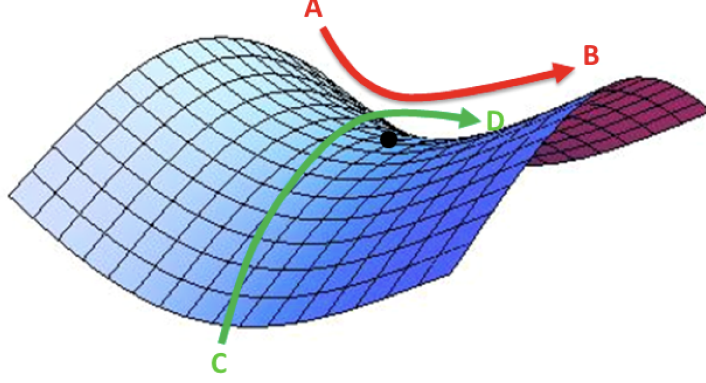


Figure 7: Saddle point over a 3D surface [14]

A better understanding of Equations (74) and (75) can be observed in Figure 7. Depending upon how one cuts the surface moving along the direction A to B or from C to D (orthogonal direction to A to B), the critical point looks like a local minima or a local maxima, but in reality it is neither. It is a saddle point.

Equation (64) for the coupled multi-physics problem of magneto-elastic membrane in free space is a special case of the (generalized) saddle point system. Here, the conditions C1-C4 are satisfied, but not C5 which arises in the discretization of equations describing slightly compressible solids [3].

8.2 Numerical solution of saddle point systems

To solve the linear system of equations Equation (64), one of the following approach can be taken:

- Direct solver solving the complete system monolithically.
- Global iterative solver with a global preconditioner constructed for the tangent matrix \mathbf{K} .
- Sequentially solve for each unknown field ϕ and \mathbf{u} exploiting the tangent matrix's block structure.

Below we explain the direct solver and the iterative solution method exploiting the block structure that were implemented. Before we discuss the details of the solution methods, it is important to highlight the properties of each block in the tangent matrix \mathbf{K} . This will also explain the motive for the choice of block to proceed with iterative solution method detailed in the further section.

As observed in the finite element discretized form for the coupled problem, the block for purely magnetic scalar potential contribution $\mathbf{K}_{\phi\phi} = - \int_{\mathcal{D}_0} \nabla_0 \mathbf{N}_I \cdot \mathbf{D} \cdot \nabla_0 \mathbf{N}_J$ results in a symmetric negative-definite matrix of size $p \times p$. The block for purely non-linear elastic contribution $\mathbf{K}_{\mathbf{u}\mathbf{u}} = \int_{\mathcal{D}_0} [[\nabla_0^T \mathbf{N}_I \cdot \nabla_0 \mathbf{N}_J] : \mathbf{S} + [\mathbf{F}^T \cdot \nabla_0 \mathbf{N}_I] : \mathbf{C} : [\mathbf{F}^T \cdot \nabla_0 \mathbf{N}_J]]$ represents a symmetric positive-definite matrix of size $q \times q$. For the considered axisymmetric problem, we know that

for any given total number of support points n_d , $p < q$ given that we solve for a single scalar-valued magnetic potential ϕ and a vector-valued displacement $(u_r, u_z)^T$. Thus, the size of block $\mathbf{K}_{\phi\phi}$ is always less than the block $\mathbf{K}_{\mathbf{uu}}$ (unless we solve for a 1D problem). The blocks resulting from the coupling between the two fields, namely $\mathbf{K}_{\phi\mathbf{u}}$ and $\mathbf{K}_{\mathbf{u}\phi}$ are symmetric negative-definite matrices with sizes $p \times q$ and $q \times p$, respectively and are transposes of each other. Thus, one can assemble one block and store the other as the transpose of the assembled block to save computations. Due to the sparsity arising in each individual block, the structure of the tangent matrix \mathbf{K} is an unsymmetric sparse banded block matrix.

8.2.1 Direct solver

This category of solvers is also known as ‘coupled’ or ‘all at once’ methods. Coupled solvers deal with the system such as Equation (64) as a whole, computing both the fields ϕ and \mathbf{u} simultaneously and without making any explicit use of reduced systems. In most cases, due to the ease of implementation, the direct solver is employed. One doesn’t have to care about the properties of the tangent matrix \mathbf{K} and also about the properties of individual blocks.

We use a sparse direct solver called UMFPACK [1], which is part of the SuiteSparse library [11]. Interface to this solver is provided in the `deal.II` [16] library in the form of the class **SparseDirectUMFPACK**. UMFPACK is a set of routines for solving unsymmetric sparse linear systems of the form $\mathbf{A} \cdot \mathbf{x} = \mathbf{b}$. It employs the unsymmetric multifrontal method and direct sparse LU factorization. It is heavily used as a built-in routine in MATLAB® and appears as `lu` and $\mathbf{x} = \mathbf{A} \setminus \mathbf{b}$ (back slash operator). It is important to note that this solver is a serial solver and therefore one cannot employ parallel (MPI) data structures for the vectors and reap the benefits of distributed memory parallelism for a large system of equations. Thus, solution time for a large system using such a serial direct solver would be high compared to a parallelized iterative solver in most cases. But for our problem of interest, in axisymmetric formulation it was observed that the computation time for the total solution was comparable to that of a parallelized iterative solver mentioned in the next section.

8.2.2 Segregated iterative solver using Schur complement reduction

The other category of solvers is the so called segregated solver which computes both the unknown fields ϕ and \mathbf{u} separately. This approach involves the solution of two linear systems of size smaller than $p + q$ which are termed as *reduced systems*. One reduced system is formed for the field ϕ and the other reduced system for the field \mathbf{u} . Depending upon the number of unknown fields, for example, in cases of a Lagrange multiplier, a separate reduced system for that unknown field is also formed and solved. Here, we shall look at one of the representatives of such a segregated approach known as the Schur complement reduction which we implemented for the solution of the fully-coupled magneto-elastic problem of our interest.

The Schur complement reduction is based on the block LU factorization of the sparse block tangent matrix \mathbf{K} . Consider the saddle point system of our interest from Equation (64):

$$\mathbf{K}_{\phi\phi} \cdot \Delta \mathbf{d}_\phi + \mathbf{K}_{\phi\mathbf{u}} \cdot \Delta \mathbf{d}_\mathbf{u} = -\mathbf{R}_\phi, \quad \mathbf{K}_{\mathbf{u}\phi} \cdot \Delta \mathbf{d}_\phi + \mathbf{K}_{\mathbf{uu}} \cdot \Delta \mathbf{d}_\mathbf{u} = -\mathbf{R}_\mathbf{u}. \quad (76)$$

If the block $\mathbf{K}_{\phi\phi}$ is square and non-singular (invertible), which in our case is true, the saddle point matrix \mathbf{K} admits the following block triangular factorization:

$$\mathbf{K} = \begin{bmatrix} \mathbf{K}_{\phi\phi} & \mathbf{K}_{\phi\mathbf{u}} \\ \mathbf{K}_{\mathbf{u}\phi} & \mathbf{K}_{\mathbf{uu}} \end{bmatrix} = \begin{bmatrix} \mathbf{I} & \mathbf{0} \\ \mathbf{K}_{\mathbf{u}\phi}\mathbf{K}_{\phi\phi}^{-1} & \mathbf{I} \end{bmatrix} \begin{bmatrix} \mathbf{K}_{\phi\phi} & \mathbf{0} \\ \mathbf{0} & \mathbf{S} \end{bmatrix} \begin{bmatrix} \mathbf{I} & \mathbf{K}_{\phi\phi}^{-1}\mathbf{K}_{\phi\mathbf{u}}^T \\ \mathbf{0} & \mathbf{I} \end{bmatrix}, \quad (77)$$

where \mathbf{I} and $\mathbf{0}$ are the unit identity matrix and null matrix of appropriate size, respectively. The matrix \mathbf{S} is the Schur complement of block $\mathbf{K}_{\phi\phi}$ in \mathbf{K} and is defined as:

$$\mathbf{S} = \mathbf{K}_{\mathbf{uu}} - \mathbf{K}_{\mathbf{u}\phi}\mathbf{K}_{\phi\phi}^{-1}\mathbf{K}_{\phi\mathbf{u}} \equiv \mathbf{D} - \mathbf{C}\mathbf{A}^{-1}\mathbf{B} \text{ from Equation (69)}. \quad (78)$$

With the magnetic potential stiffness block $\mathbf{K}_{\phi\phi}$ and the total stiffness matrix \mathbf{K} being square and invertible, by the block triangular factorization in Equation (77) the Schur complement \mathbf{S} is also invertible. Pre-multiplying both the sides of the first equation in Equation (76) by $\mathbf{K}_{u\phi}\mathbf{K}_{\phi\phi}^{-1}$, we obtain

$$\mathbf{K}_{u\phi} \cdot \Delta \mathbf{d}_\phi + \mathbf{K}_{u\phi} \mathbf{K}_{\phi\phi}^{-1} \mathbf{K}_{\phi u} \cdot \Delta \mathbf{d}_u = -\mathbf{K}_{u\phi} \mathbf{K}_{\phi\phi}^{-1} \cdot \mathbf{R}_\phi. \quad (79)$$

Using $\mathbf{K}_{u\phi} \cdot \Delta \mathbf{d}_\phi = -\mathbf{R}_u - \mathbf{K}_{uu} \cdot \Delta \mathbf{d}_u$ from the second equation in Equation (76), after rearranging we see

$$\left(\mathbf{K}_{uu} - \mathbf{K}_{u\phi} \mathbf{K}_{\phi\phi}^{-1} \mathbf{K}_{\phi u} \right) \cdot \Delta \mathbf{d}_u = \mathbf{K}_{u\phi} \mathbf{K}_{\phi\phi}^{-1} \cdot \mathbf{R}_\phi - \mathbf{R}_u \implies \mathbf{S} \cdot \Delta \mathbf{d}_u = \mathbf{R}'_u, \quad (80)$$

with the modified right-hand side vector $\mathbf{R}'_u := \mathbf{K}_{u\phi} \mathbf{K}_{\phi\phi}^{-1} \cdot \mathbf{R}_\phi - \mathbf{R}_u$ arising from the condensation step. In terms of the general representation as in Equation (69), we arrive at

$$(\mathbf{D} - \mathbf{C} \mathbf{A}^{-1} \mathbf{B}) \cdot \mathbf{y} = \mathbf{g} - \mathbf{C} \mathbf{A}^{-1} \mathbf{f} \implies \mathbf{S} \cdot \mathbf{y} = \mathbf{g}'. \quad (81)$$

Equations (80) and (81) represent a reduced system of order q for the solution update in displacement field $\Delta \mathbf{d}_u$. It is important to note that unless $-\mathbf{R}_\phi \equiv \mathbf{f} = \mathbf{0}$, pre-processing the condensed right-hand side vector $\mathbf{R}'_u \equiv \mathbf{g}'$ requires solving another linear system of equation of the form $\mathbf{A} \cdot \mathbf{v} = \mathbf{f}$. Once the solution (or an approximation) $\Delta \mathbf{d}_u$ of the reduced system Equation (80) is computed, we then post-process the solution update for the other field $\Delta \mathbf{d}_\phi$ using the solution from the first update $\Delta \mathbf{d}_u$ as

$$\mathbf{K}_{\phi\phi} \cdot \Delta \mathbf{d}_\phi = -\mathbf{R}_\phi - \mathbf{K}_{\phi u} \cdot \Delta \mathbf{d}_u. \quad (82)$$

Equation (82) represents the other reduced system of size p that needs to be solved for the magnetic potential solution update. Algorithm 1 highlights the algorithmic steps needed to solve any saddle point system using the segregated iterative solver. The algorithm is explained for the fully-coupled magneto-elastic problem of our interest, solving for the displacement field first and then for the magnetic potential, but can be applied for any general saddle point system such as Equation (69).

Algorithm 1: Schur complement reduction

1. Define the inverse $\mathbf{K}_{\phi\phi}^{-1}$ using a solver with preconditioner.
 2. Define the Schur complement $\mathbf{S} = \mathbf{K}_{uu} - \mathbf{K}_{u\phi} \mathbf{K}_{\phi\phi}^{-1} \mathbf{K}_{\phi u}$.
 3. Define the inverse of the Schur complement \mathbf{S}^{-1} using another solver with a preconditioner to compute the approximate inverse operation of \mathbf{S} .
 4. Perform the pre-processing step to condense the right-hand side vector $\mathbf{R}'_u := \mathbf{K}_{u\phi} \mathbf{K}_{\phi\phi}^{-1} \cdot \mathbf{R}_\phi - \mathbf{R}_u$.
 5. Solve for the solution update $\Delta \mathbf{d}_u$: $\Delta \mathbf{d}_u = \mathbf{S}^{-1} \cdot \mathbf{R}'_u$.
 6. Post-process the solution for the other field: $\Delta \mathbf{d}_\phi = \mathbf{K}_{\phi\phi}^{-1} (-\mathbf{R}_\phi - \mathbf{K}_{\phi u} \cdot \Delta \mathbf{d}_u)$.
-

Choice of the block to compute the Schur complement of \mathbf{K} :

The choice of the block $\mathbf{K}_{\phi\phi}$ of size $p \times p$ to proceed with the Schur complement of \mathbf{K} is due to the small size of the block compared to the other diagonal block \mathbf{K}_{uu} of size $q \times q$, with $p < q$ as mentioned in the previous section. The motive behind the choice of the block of small size is the need to compute the inverse of the chosen block in computing the Schur complement \mathbf{S} as observed in Equation (78). Computational cost of computing the inverse of a matrix of size

$q \times q$ exceeds that of the cost for a matrix of size $p \times p$. One also needs to take into account the lower bandwidth of the scalar magnetic potential stiffness matrix block compared to that of the displacement stiffness matrix block [13].

Typically this inversion of the chosen block matrix is performed by using a robust Krylov subspace iterative solver such as the Conjugate Gradient method with some form of preconditioning. The CG method works on only symmetric positive-definite matrices [9]. Whereas the block $\mathbf{K}_{\phi\phi}$ and $\mathbf{K}_{\phi\mathbf{u}}$ of the first equation in Equation (76) are symmetric negative-definite matrices. In order to compute the inverse $\mathbf{K}_{\phi\phi}^{-1}$ using the CG iterative solver we need to transform the matrix $\mathbf{K}_{\phi\phi}$ to a positive-definite matrix. We do this by multiplying the first equation in Equation (76) by a factor of -1. This leads to a system of equations as

$$-\mathbf{K}_{\phi\phi} \cdot \Delta \mathbf{d}_\phi - \mathbf{K}_{\phi\mathbf{u}} \cdot \Delta \mathbf{d}_\mathbf{u} = \mathbf{R}_\phi, \quad (83)$$

with symmetric positive-definite matrix blocks. The matrix block $\mathbf{K}_{\phi\phi}$ is preconditioned to reduce the condition number and thus have a good convergence rate within the iterative solver computing an approximation to the inverse $\mathbf{K}_{\phi\phi}^{-1}$. We have employed the Trilinos [5] linear algebra suite for the parallel and efficient data structures of vectors, matrices, preconditioners and solvers. Jacobi, SSOR and the Algebraic Multigrid (AMG) [6] preconditioners were used from the Trilinos suite. Depending on a user input parameter one of the three would be used. To compute the inverse $\mathbf{K}_{\phi\phi}^{-1}$ a reduced-iteration CG solver was employed. The linear transformations such as the scaling of matrix with a factor of -1, forming the inverse operator $\mathbf{K}_{\phi\phi}^{-1}$ and the Schur complement \mathbf{S} was carried out using the class **LinearOperator** from the `deal.II` library. Lazy evaluation of linear transformations and expressions using vectors and matrices is performed by this class. The lazy evaluation of an expression helps in avoiding any intermediate storage of temporary objects. The class stores the sequence of operations that need to be performed on the vector/matrix object and executes them only when the value of the object is required. The class **LinearOperator** provides several member functions that aid the user implementing a Schur complement reduction solver. The member function `linear_operator()` was used on each block of the tangent matrix \mathbf{K} to transform the underlying Trilinos sparse matrix to a **LinearOperator** data structure. The function `inverse_operator()`, which takes the matrix of which inverse is to be computed, the iterative linear solver and the preconditioner for the matrix as arguments, was employed to form the inverse operator $\mathbf{K}_{\phi\phi}^{-1}$. The Schur complement was defined using the member function `schur_complement()` which takes the four matrix blocks as arguments required to define the Schur complement $\mathbf{S} := \mathbf{D} - \mathbf{CA}^{-1}\mathbf{B}$.

Another reduced-iteration CG solver was used with one of the three preconditioner to define the inverse operator for the Schur complement \mathbf{S}^{-1} . To pre-process the condensed right-hand side vector as mentioned in Algorithm 1, the member function `condense_schur_rhs()` of the class **LinearOperator** was employed. To post-process the solution update for the second field the member function `postprocess_schur_solution()` was employed. Thus, in total two different iterative solvers with respective preconditioners were implemented within the Schur complement reduction method. An inner solver to compute $\mathbf{K}_{\phi\phi}^{-1}$ and an outer solver to compute \mathbf{S}^{-1} .

9 Test case and Results

9.1 Unit test problem

9.2 Torus problem

With mechanical load applied first, followed by magnetic load. Results. Conclusion.

With magnetic load applied first, followed by mechanical load (to observe mechanically induced instabilities in the membrane). Results and conclusions.

References

- [1] Timothy A Davis. “Algorithm 832: UMFPACK V4. 3—an unsymmetric-pattern multifrontal method”. In: *ACM Transactions on Mathematical Software (TOMS)* 30.2 (2004), pp. 196–199.
- [2] A. Dorfmann and R. W. Ogden. “Nonlinear magnetoelastic deformations”. In: *The Quarterly Journal of Mechanics and Applied Mathematics* 57.4 (2004), pp. 599–622. DOI: 10.1093/qjmam/57.4.599. eprint: /oup/backfile/content_public/journal/qjmam/57/4/10.1093/qjmam/57.4.599/2/570599.pdf. URL: <http://dx.doi.org/10.1093/qjmam/57.4.599>.
- [3] Michele Benzi, Gene H. Golub, and Jörg Liesen. “Numerical solution of saddle point problems”. In: *Acta Numerica* 14 (May 2005), pp. 1–137. DOI: 10.1017/s0962492904000212.
- [4] A. Dorfmann and R. W. Ogden. “Some problems in nonlinear magnetoelasticity”. In: *Zeitschrift für angewandte Mathematik und Physik ZAMP* 56.4 (July 2005), pp. 718–745. ISSN: 1420-9039. DOI: 10.1007/s00033-004-4066-z. URL: <https://doi.org/10.1007/s00033-004-4066-z>.
- [5] Michael A Heroux et al. “An overview of the Trilinos project”. In: *ACM Transactions on Mathematical Software (TOMS)* 31.3 (2005), pp. 397–423.
- [6] Michael W Gee et al. *ML 5.0 smoothed aggregation user’s guide*. Tech. rep. Technical Report SAND2006-2649, Sandia National Laboratories, 2006.
- [7] Peter Wriggers. *Nonlinear Finite Element Methods*. Springer-Verlag GmbH, Sept. 24, 2008. ISBN: 3540710000. URL: https://www.ebook.de/de/product/7511919/peter_wriggers_nonlinear_finite_element_methods.html.
- [8] Raymond Ogden and David Steigmann. *Mechanics and electrodynamics of magneto-and electro-elastic materials*. Vol. 527. Springer Science & Business Media, 2011.
- [9] Stanislaw H. Zak Edwin K. P. Chong. *An Introduction to Optimization*. JOHN WILEY & SONS INC, Jan. 14, 2013. 640 pp. ISBN: 1118279018. URL: https://www.ebook.de/de/product/19579661/edwin_k_p_chong_stanislaw_h_zak_an_introduction_to_optimization.html.
- [10] Luis Dorfmann and Ray W. Ogden. *Nonlinear Theory of Electroelastic and Magnetoelastic Interactions*. Springer US, 2014. DOI: 10.1007/978-1-4614-9596-3.
- [11] Timothy A Davis et al. “Suitesparse: a suite of sparse matrix software”. In: URL <http://faculty.cse.tamu.edu/davis/suitesparse.html> (2015).
- [12] Prashant Saxena, Jean-Paul Pelteret, and Paul Steinmann. “Modelling of iron-filled magneto-active polymers with a dispersed chain-like microstructure”. In: *European Journal of Mechanics - A/Solids* 50 (Mar. 2015), pp. 132–151. DOI: 10.1016/j.euromechsol.2014.10.005.
- [13] Jean-Paul Pelteret et al. “Computational electro-elasticity and magneto-elasticity for quasi-incompressible media immersed in free space”. In: *International Journal for Numerical Methods in Engineering* 108.11 (June 2016), pp. 1307–1342. DOI: 10.1002/nme.5254.
- [14] Nikhil Buduma. “Fundamentals of Deep Learning”. In: O’Reilly Media, Inc., 2017. Chap. 4. ISBN: 9781491925607.
- [15] Narravula Harshavardhan Reddy and Prashant Saxena. “Limit points in the free inflation of a magnetoelastic toroidal membrane”. In: *International Journal of Non-Linear Mechanics* 95 (2017), pp. 248–263.
- [16] Giovanni Alzetta et al. “The deal.II Library, Version 9.0”. In: *Journal of Numerical Mathematics* (June 2018). DOI: 10.1515/jnma-2018-0054.

- [17] Narravula Harshavardhan Reddy and Prashant Saxena. “Instabilities in the axisymmetric magnetoelastic deformation of a cylindrical membrane”. In: *International Journal of Solids and Structures* 136 (2018), pp. 203–219.