SEA regression report summary

Sample ID
C60-20-glass-□□□- 1

Details	
Software and regression log	
Software about	Semilab - Spectroscopic Ellipsometry Analyzer - SEA
Software version	1.8.0.4
Officially licensed to	Linyang Jiangsu
Operator	operator
Date and time of regression	07-04-2026 16:54
Comments	

Layer structure	
Overview	

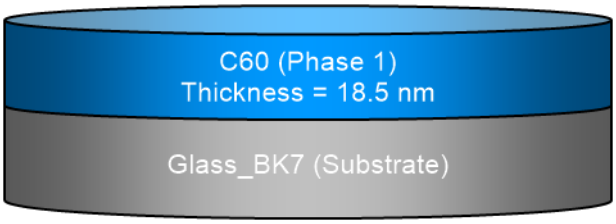

Optical model	
Phase 1	C60
Dispersion law	Tauc-Lorentz
	Lorentz
	Lorentz

Regression results

Measurement information				
Measurement file path	C:\Users\jijun.zhang\Desktop\□□□□□□\ C60-20-glass-□□□-1.smdx			
Angle of Incidence	64.6°			
Regression details				
Regression 1 (EllipsoReflectance)				
Wavelength range	260.19 - 899.93 nm			
Angle of Incidence	64.6°			
Fit to	Ψ, Δ			
Angular Aperture	0°			
Fit algorithm	LMA			
Results				
Parameters	Value	Fitted	2 σ confidence limit	Unit
Model				
AOI Shift	0			°
Angular Aperture	0			°
Phase 1 (C60)				
Thickness	18.494	X	0.07288	nm
A (eV)	25.25319			eV
E0 (eV)	4.7205			eV
C (eV)	1.34603			eV
Eg (eV)	2.22511	X	0.0039054	eV
f	0.35695			
E0 (eV)	3.55858			eV
Γ (eV)	0.43402	X	0.0030298	eV
f	0.26273			
E0 (eV)	2.7432			eV
Γ (eV)	0.58411	X	0.006296	eV
Eps_inf	1.93708			
Derived parameters	Value			
Phase 1 (C60)				
n @ 632.8 nm	2.107			
k @ 632.8 nm	0.0476			
Substrate (Glass_BK7)				
n @ 632.8 nm	1.5151			
k @ 632.8 nm	0			
Fit quality				
R^2	0.99551			
RMSE	0.19526			

Regression graphs

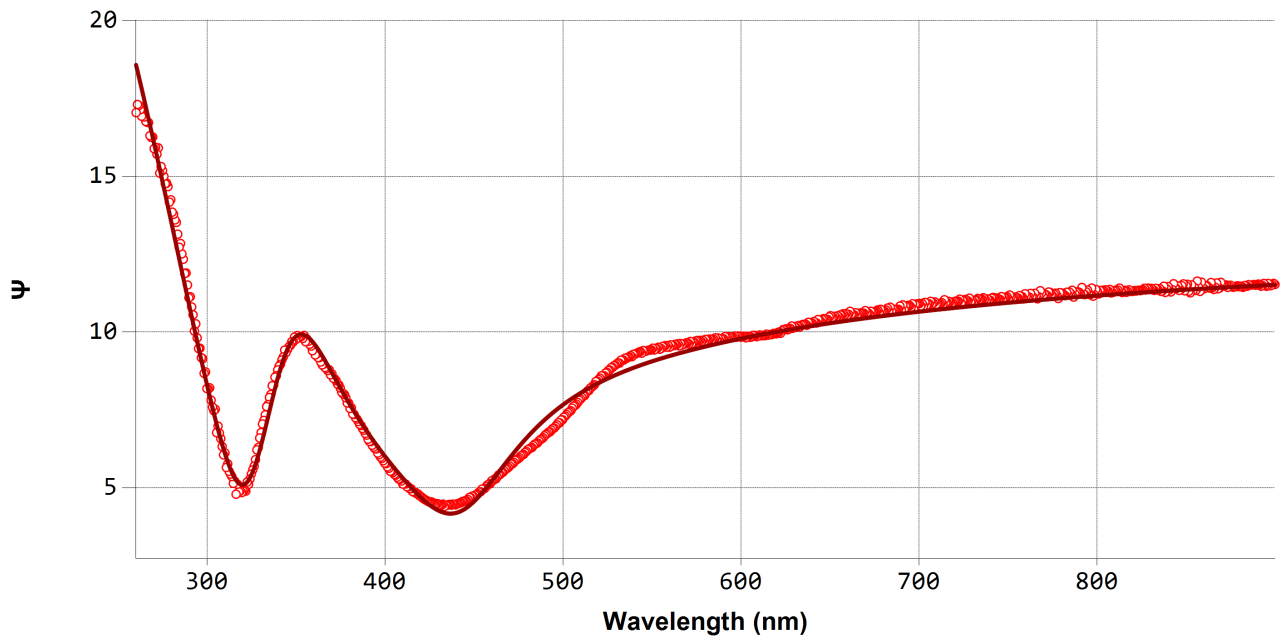

—	C60-20-glass-□□□- 1 Measured	—	C60-20-glass-□□□- 1 After Fit

Regression graphs

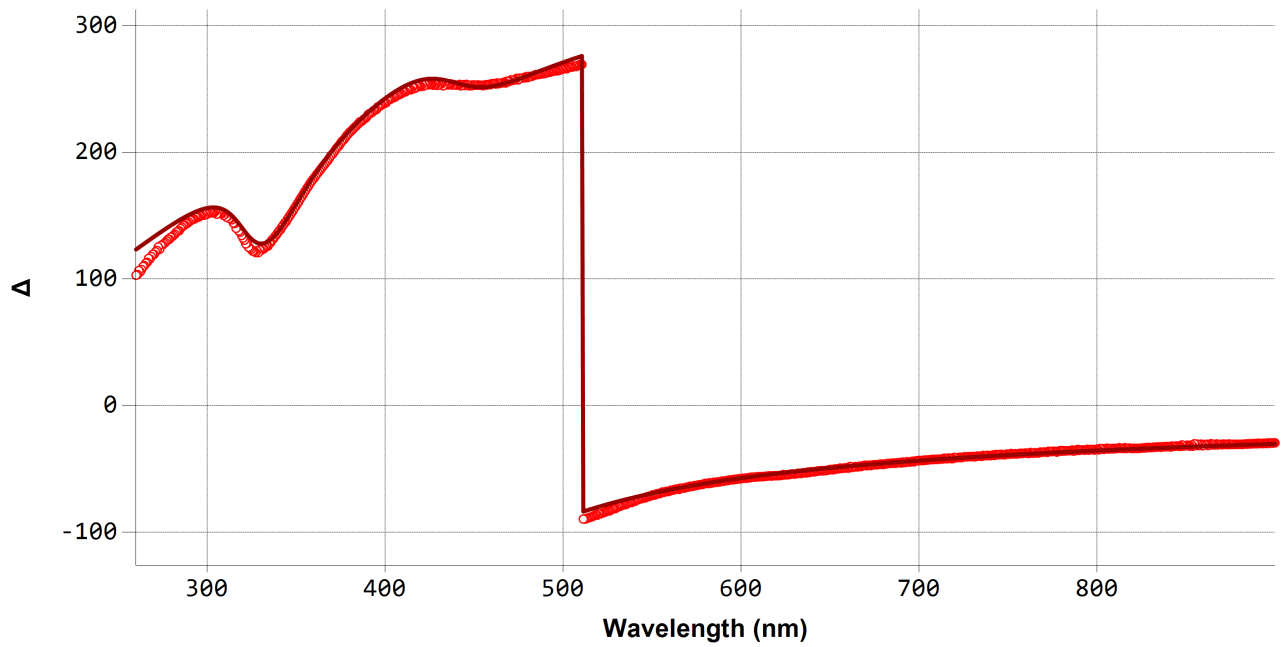

—	C60-20-glass-□□□- 1 Measured	—	C60-20-glass-□□□- 1 After Fit

Phase 1 (C60) - Dispersion graphs

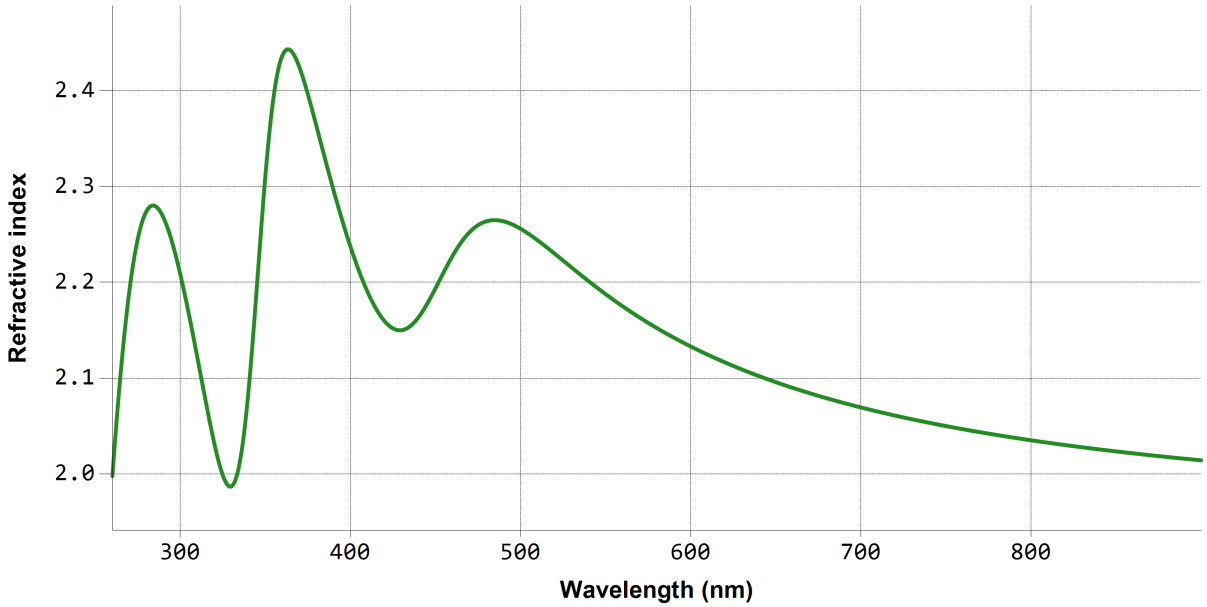

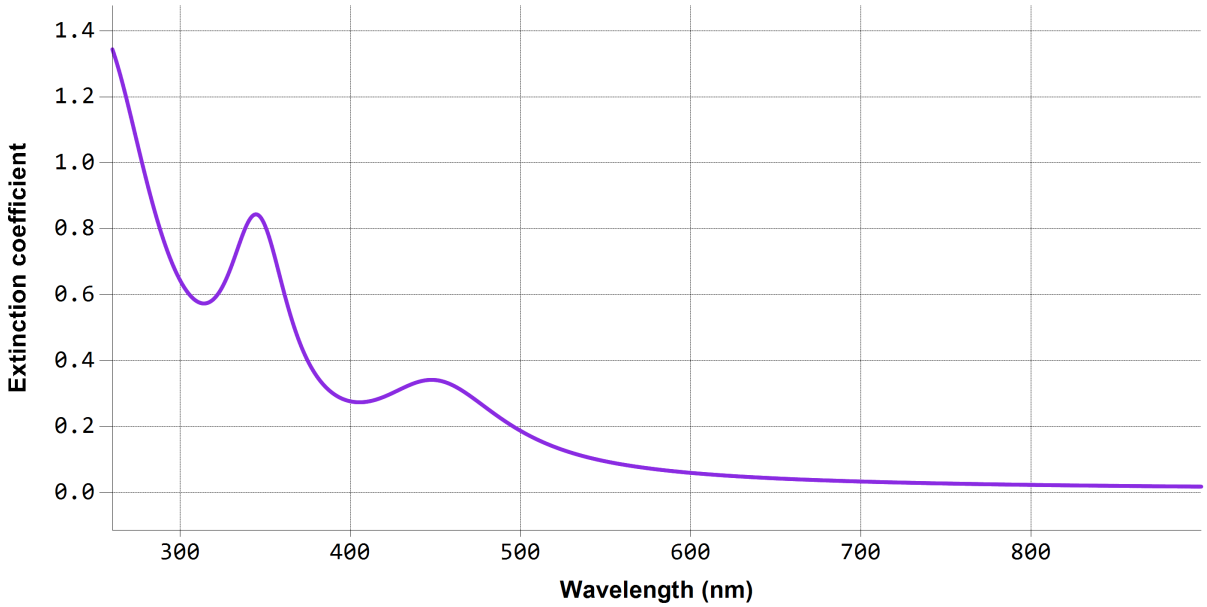

Substrate (Glass_BK7) - Dispersion graphs

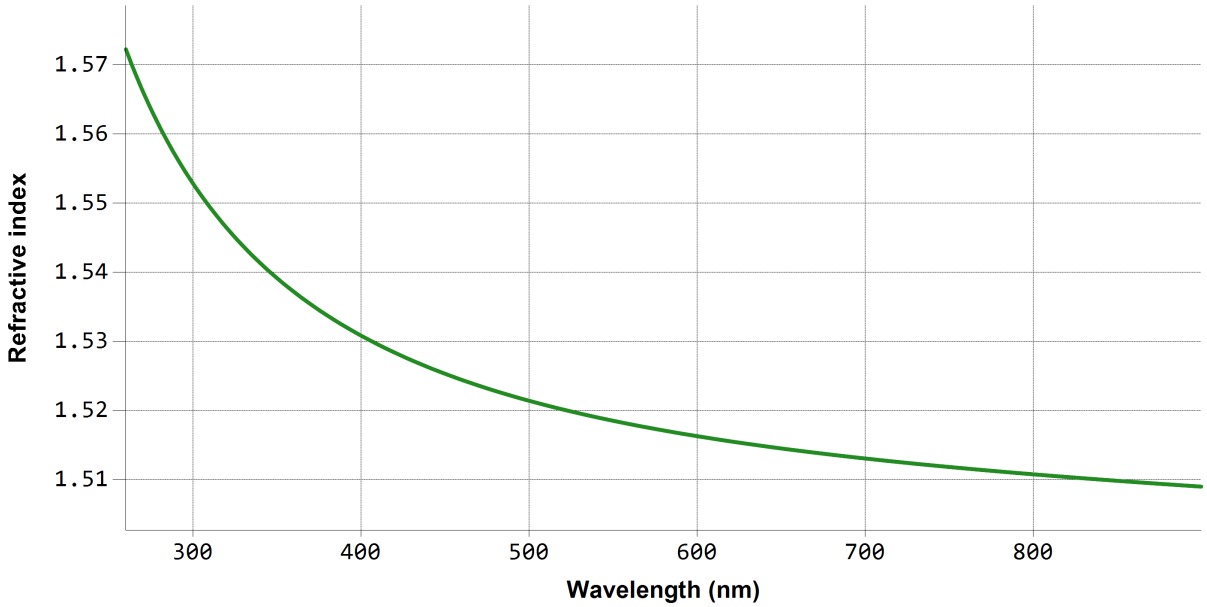

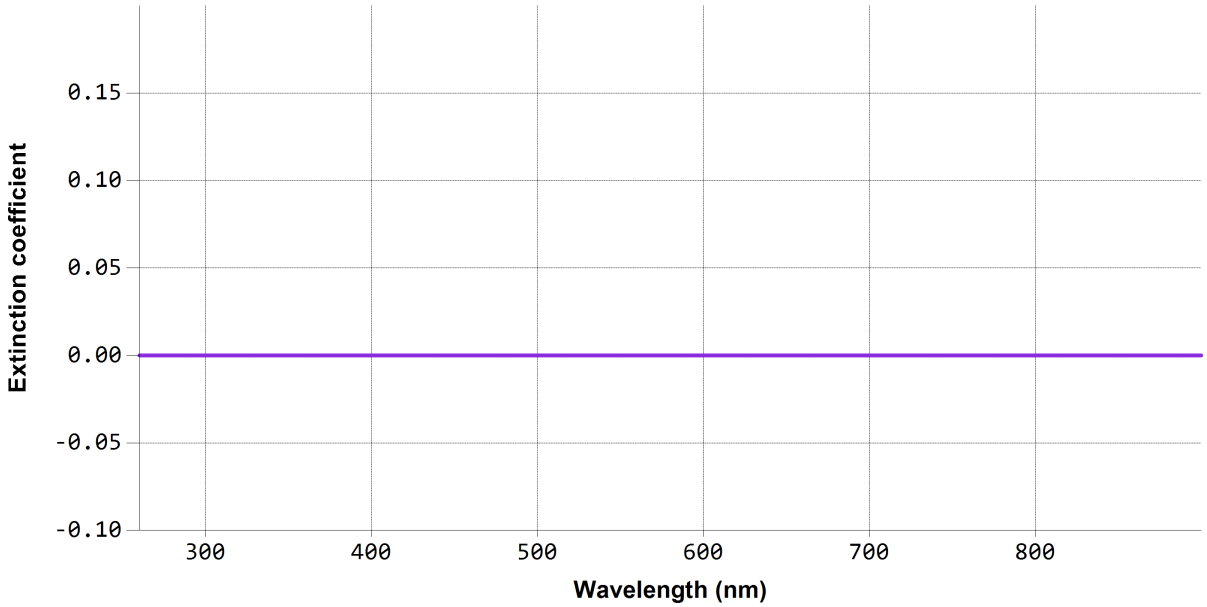

Correlation coefficients				
	Ph1 - C60 - Thickness	Ph1 - Tauc-Lorentz[1] - Eg (eV)	Ph1 - Lorentz[2] - Γ (eV)	Ph1 - Lorentz[3] - Γ (eV)
Ph1 - C60 - Thickness	1	0.6691	0.2204	0.1306
Ph1 - Tauc-Lorentz[1] - Eg (eV)		1	-0.0547	0.2206
Ph1 - Lorentz[2] - Γ (eV)			1	0.1771
Ph1 - Lorentz[3] - Γ (eV)				1