SEA regression report summary

Sample ID
1-3

Details	
Software and regression log	
Software about	Semilab - Spectroscopic Ellipsometry Analyzer - SEA
Software version	1.8.0.4
Officially licensed to	Linyang Jiangsu
Operator	operator
Date and time of regression	07-04-2026 16:48
Comments	

Layer structure	
Overview	

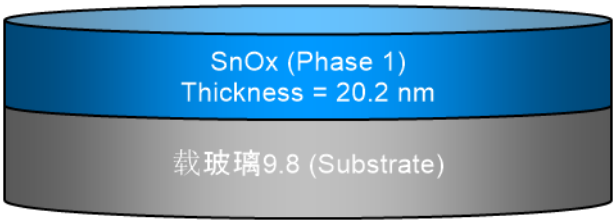

Optical model	
Phase 1	SnOx
Dispersion law	Lorentz
	Tauc-Lorentz

Regression results

Measurement information				
Measurement file path	C:_Result\2026□2~3□\ 20260327\SnOx\1-3.smdx			
Angle of Incidence	64.6°			
Regression details				
Regression 1 (EllipsoReflectance)				
Wavelength range	280.47 - 899.93 nm			
Angle of Incidence	64.6°			
Fit to	Ψ, Δ			
Angular Aperture	0°			
Fit algorithm	LMA			
Results				
Parameters	Value	Fitted	2 σ confidence limit	Unit
Model				
AOI Shift	0			°
Angular Aperture	0			°
Phase 1 (SnOx)				
Thickness	20.156	X	0.31921	nm
f	1.04429			
E0 (eV)	9.91314	X	0.57219	eV
Γ (eV)	5	X	0.75072	eV
A (eV)	0			eV
E0 (eV)	10			eV
C (eV)	5			eV
Eg (eV)	0			eV
Eps_inf	2.45093			
Derived parameters	Value			
Phase 1 (SnOx)				
n @ 632.8 nm	1.878			
k @ 632.8 nm	0.0297			
Substrate (□□□9.8)				
n @ 632.8 nm	1.4817			
k @ 632.8 nm	0.0043			
Fit quality				
R^2	0.98323			
RMSE	0.28621			

Regression graphs

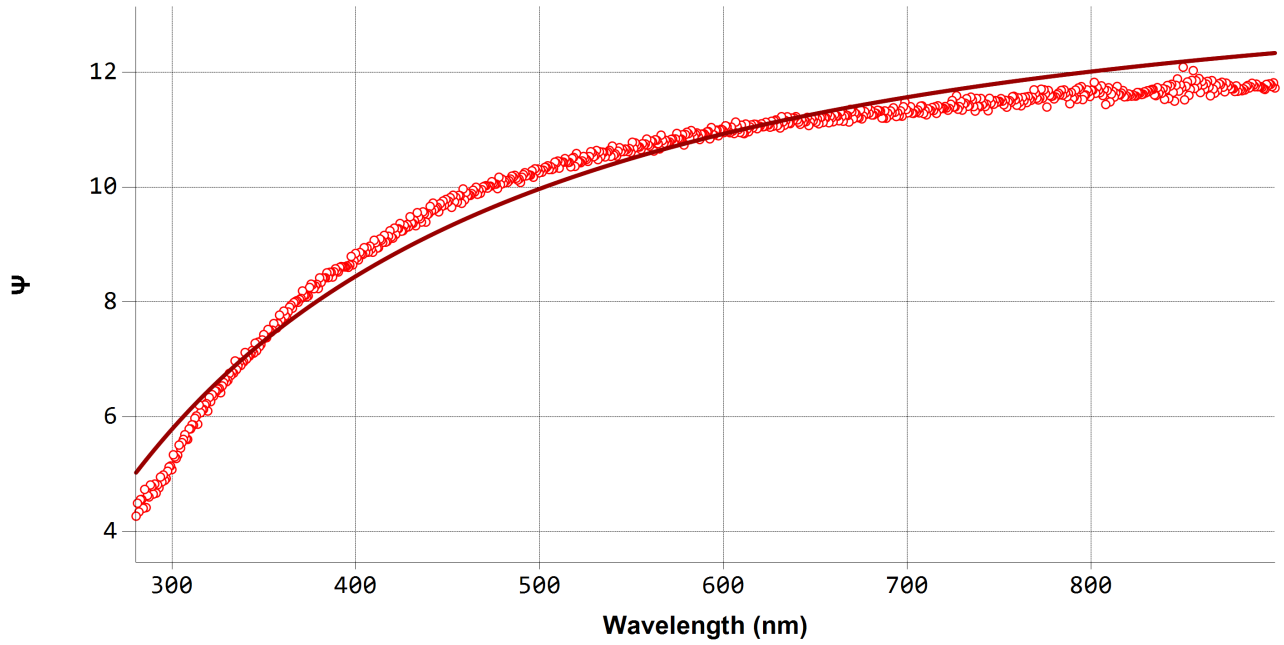

—	1-3 Measured	—	1-3 Fit

Regression graphs

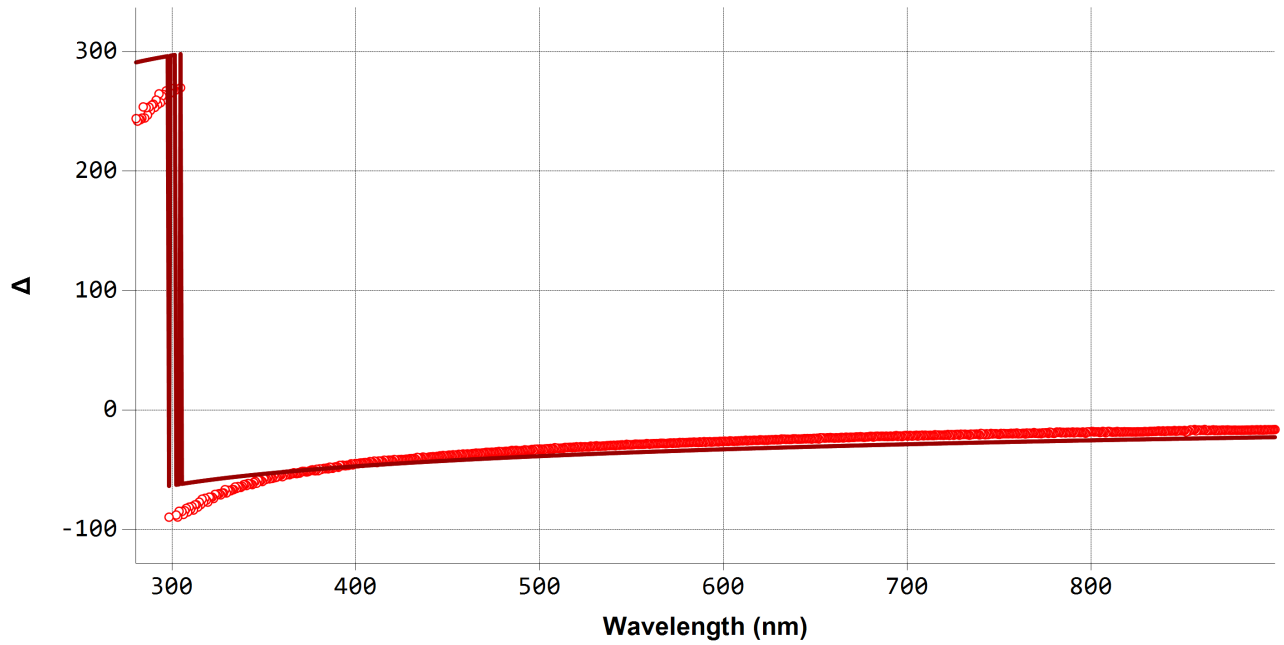

—	1-3 Measured	—	1-3 Fit

Phase 1 (SnOx) - Dispersion graphs

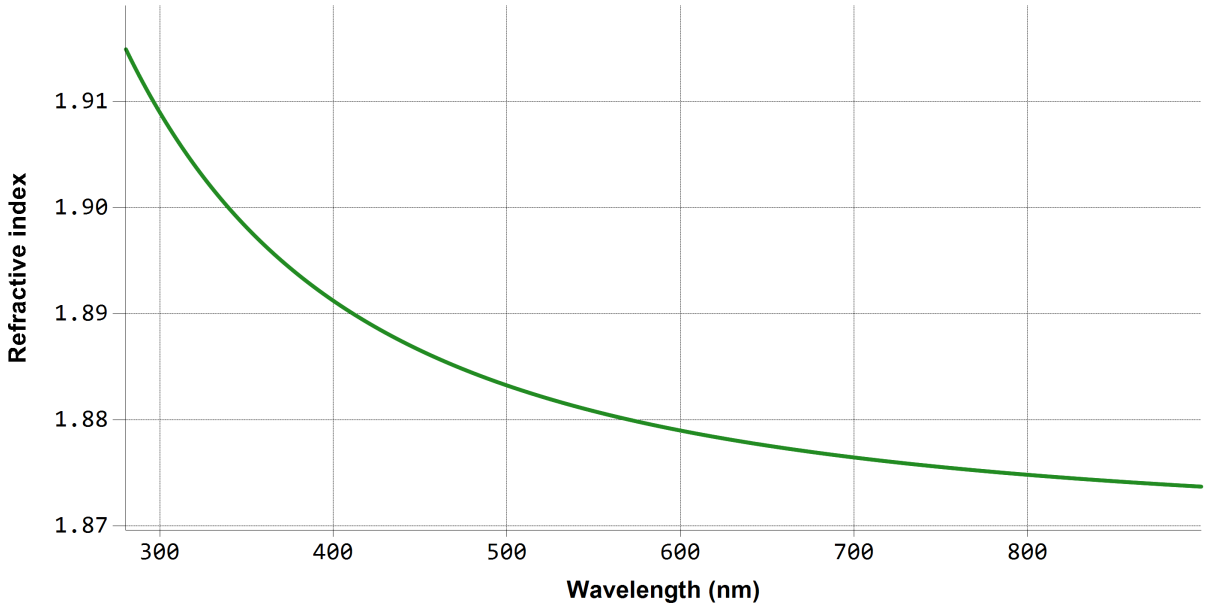

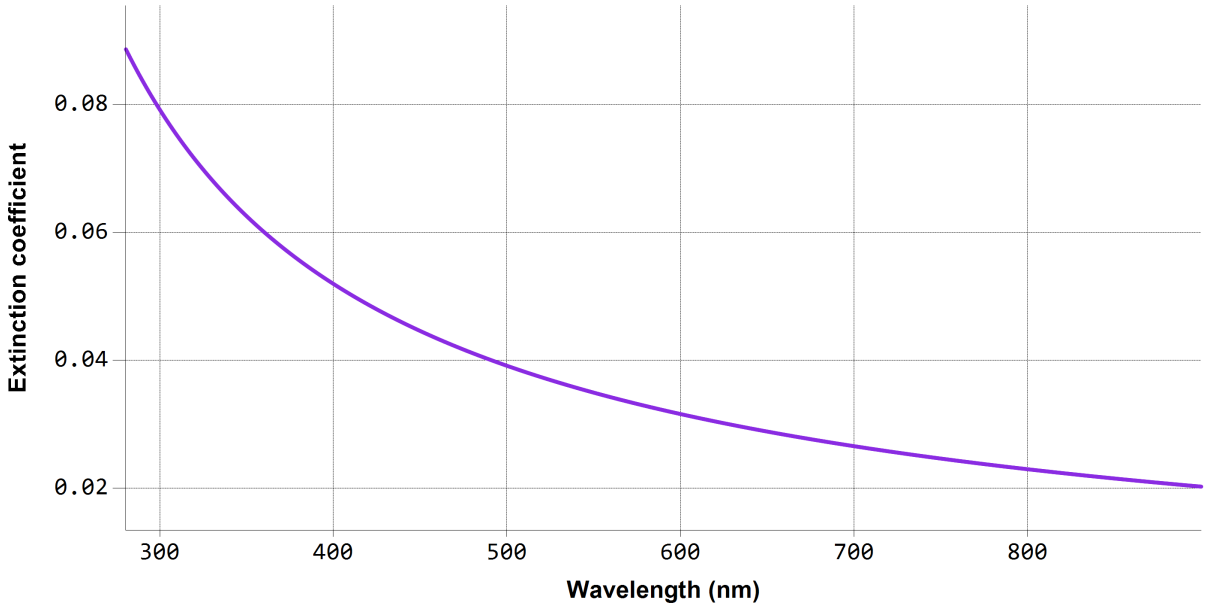

Substrate (□□□9.8) - Dispersion graphs

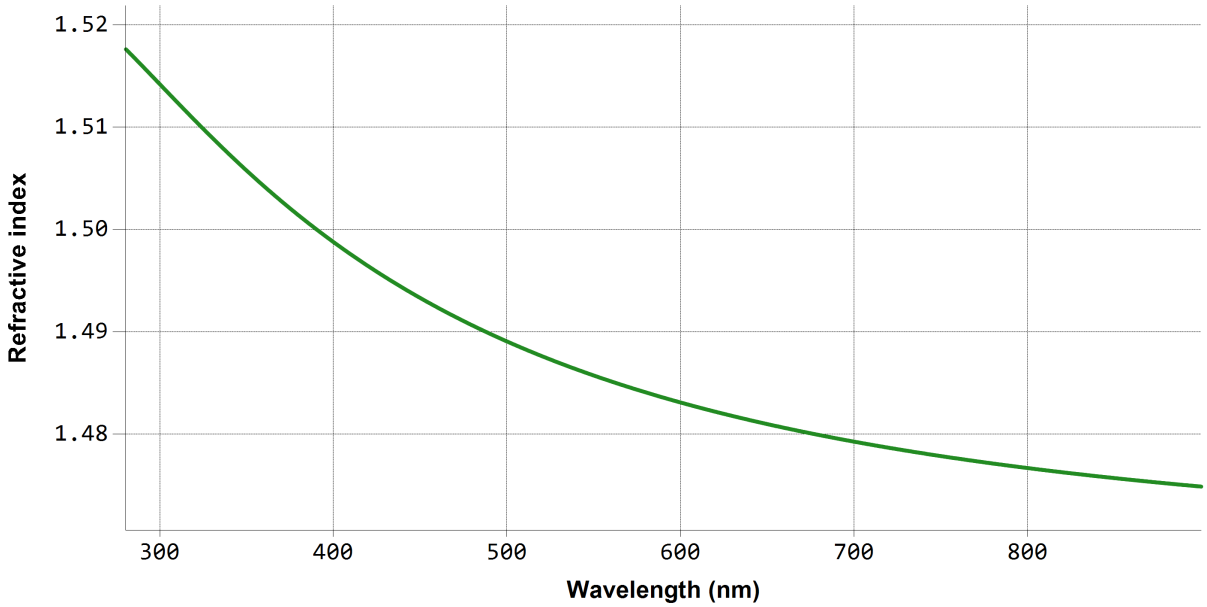

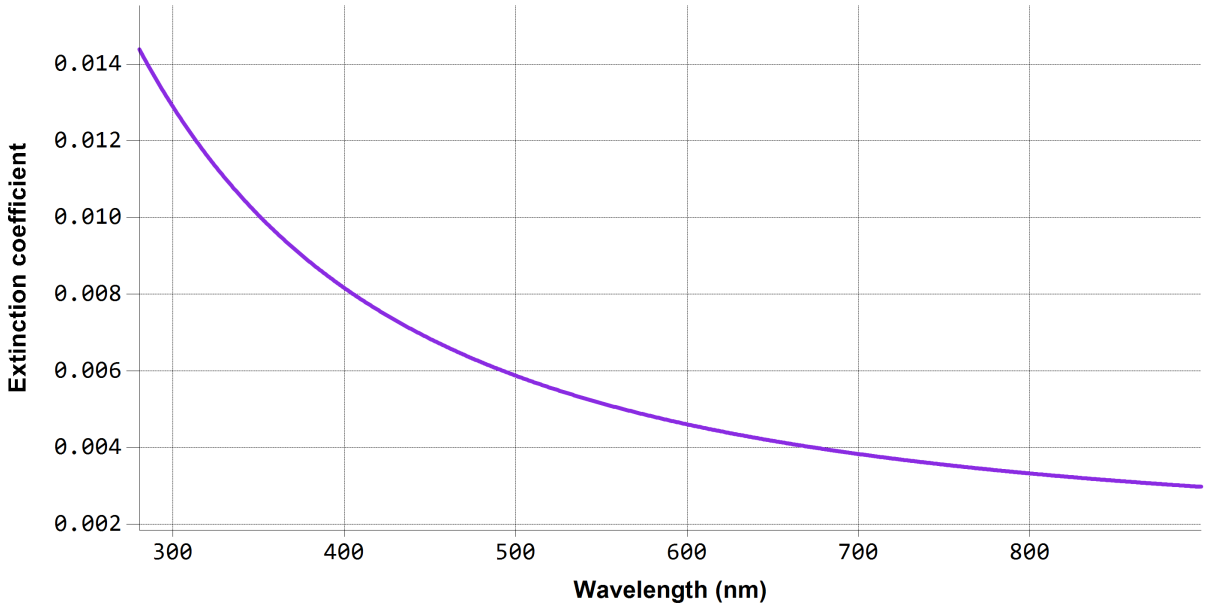

Correlation coefficients			
	Ph1 - SnOx - Thickness	Ph1 - Lorentz[1] - E0 (eV)	Ph1 - Lorentz[1] - Γ (eV)
Ph1 - SnOx - Thickness	1	0.2944	-0.1539
Ph1 - Lorentz[1] - E0 (eV)		1	0.8886
Ph1 - Lorentz[1] - Γ (eV)			1