

1本目	亜鉛電気メッキ		強度区分4.8	4.8電気メッキ		
トルクTf[N/m]	CH1	CH2		圧縮ひずみ $\varepsilon 1$	ねじりひずみ $\varepsilon 2$	F[N]
0	0	0		0	0	0
5	179	78		0.0000895	0.0000195	2502.211
10	310	120		0.000155	0.00003	4333.438
15	470	163		0.000235	0.00004075	6570.05
20				0	0	0
25				0	0	0
30						
35						
40						
	圧縮ひずみ		ねじりひずみ			

2本目	亜鉛電気メッキ		強度区分8.8	8.8亜鉛電気メッキ		
トルクTf[N/m]	CH1	CH2		圧縮ひずみ $\varepsilon 1$	ねじりひずみ $\varepsilon 2$	F[N]
0	0	0		0	0	0
5	116	40		0.000058	0.00001	1621.544
10	237	89		0.0001185	0.00002225	3312.983
15	370	138		0.000185	0.0000345	5172.167
20	495	177		0.0002475	0.00004425	6919.521
25	650	210		0.000325	0.0000525	9086.24

3本目	溶融亜鉛メッキ		強度区分8.8	8.8溶融亜鉛メッキ		
トルクTf[N/m]	CH1	CH2		圧縮ひずみ $\varepsilon 1$	ねじりひずみ $\varepsilon 2$	F[N]
0	0	0		0	0	0
5	150	44		0.000075	0.000011	2096.825
10	278	101		0.000139	0.00002525	3886.115
15	420	200		0.00021	0.00005	5871.109
20	555	280		0.0002775	0.00007	7758.251
25	680	340		0.00034	0.000085	9505.605

	scm435					
4本目	四三酸化鉄メッキ		強度区分10.9	10.9四三酸化鉄メッキ		
トルクTf[N/m]	CH1	CH2		圧縮ひずみ $\varepsilon 1$	ねじりひずみ $\varepsilon 2$	F[N]
0	0	0		0	0	0
5	265	98		0.0001325	0.0000245	3704.39
10	543	169		0.0002715	0.00004225	7590.505
15	807	225		0.0004035	0.00005625	11280.92

20	1053	278	0.0005265	0.0000695	14719.71
25	1338	298	0.000669	0.0000745	18703.68
30	1513	342	0.0007565	0.0000855	21149.97
35	1742	363	0.000871	0.00009075	24351.12

5本目 四三酸化鉄メッキ強度区分12.9 12.9四三酸化鉄メッキ

トルクTf[N/m]	CH1	CH2	圧縮ひずみ $\varepsilon 1$	ねじりひずみ $\varepsilon 2$	F[N]
0	0	0	0	0	0
5	267	87	0.0001335	0.00002175	3732.348
10	453	161	0.0002265	0.00004025	6332.41
15	652	235	0.000326	0.00005875	9114.198
20	887	285	0.0004435	0.00007125	12399.22
25	1171	300	0.0005855	0.000075	16369.21
30	1475	345	0.0007375	0.00008625	20618.78
35	1667	358	0.0008335	0.0000895	23302.71
40	1760	360	0.00088	0.00009	24602.74

Tw[Nm]	Ts[Nm]	μw	μs
0	0	0	0
2.109728	2.890271863	0.155207	0.230396
3.245736	6.754264405	0.137876	0.327638
4.408791	10.59120915	0.123526	0.340507
0	20	#DIV/0!	#DIV/0!
0	25	#DIV/0!	#DIV/0!

ボルト軸力F[N]

Tw[Nm]	Ts[Nm]	μw	μs
0	0	0	0
1.081912	3.918088135	0.122821	0.534296
2.407254	7.5927461	0.133755	0.504307
3.732596	11.26740407	0.132845	0.476995
4.78746	15.21254	0.127361	0.481821
5.680037	19.31996271	0.115074	0.464421



Tw[Nm]	Ts[Nm]	μw	μs	多分誤差あり
0	0	0	0	
1.190103	3.809896949	0.086092	0.38989	
2.731827	7.268172541	0.10663	0.402735	
5.409559	9.590440675	0.13976	0.345676	
7.573383	12.42661695	0.14807	0.338021	
9.196251	15.80374915	0.146748	0.352682	





ねじ部のトルクTs [Nm]



Tw[Nm]	Ts[Nm]	μw	μs
0	0	0	0
2.650684	2.349315931	0.131719	0.104881
4.571078	5.42892237	0.110855	0.124405
6.085754	8.914245759	0.099307	0.142473

7.519287	12.48071254	0.094034	0.156373
8.060243	16.93975661	0.079329	0.170301
9.250346	20.74965355	0.080511	0.188465
9.81835	25.18164983	0.074221	0.201244



Tw[Nm]	Ts[Nm]	μ w	μ s
0	0	0	0
2.353158	2.646841694	0.116059	0.122945
4.354695	5.645304743	0.126589	0.16688
6.356232	8.643767793	0.128378	0.180589
7.708622	12.29137796	0.114443	0.19093
8.114339	16.88566101	0.09125	0.200628
9.33149	20.66851016	0.08331	0.193607
9.683111	25.31688881	0.076492	0.213854
9.737207	30.26279322	0.072855	0.248462

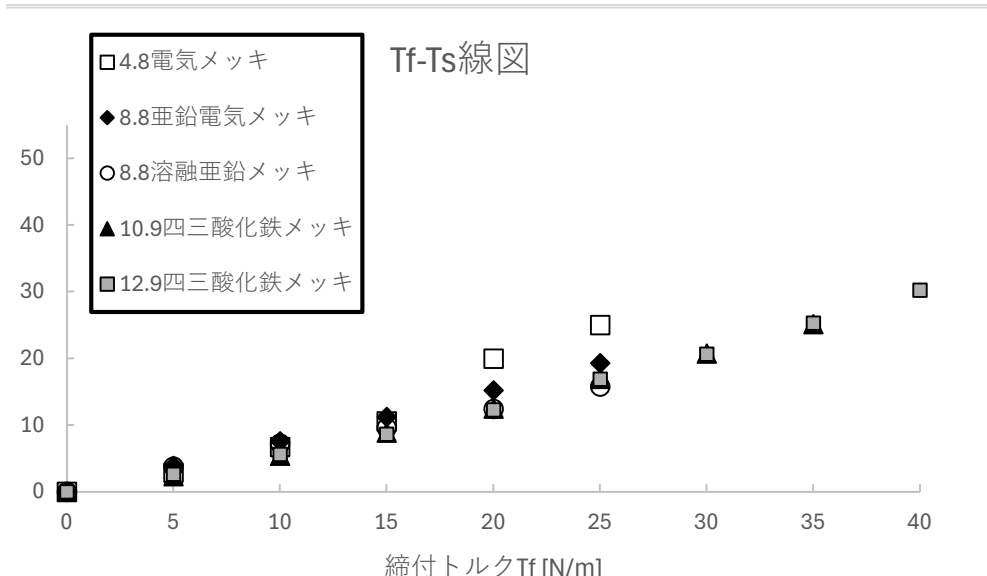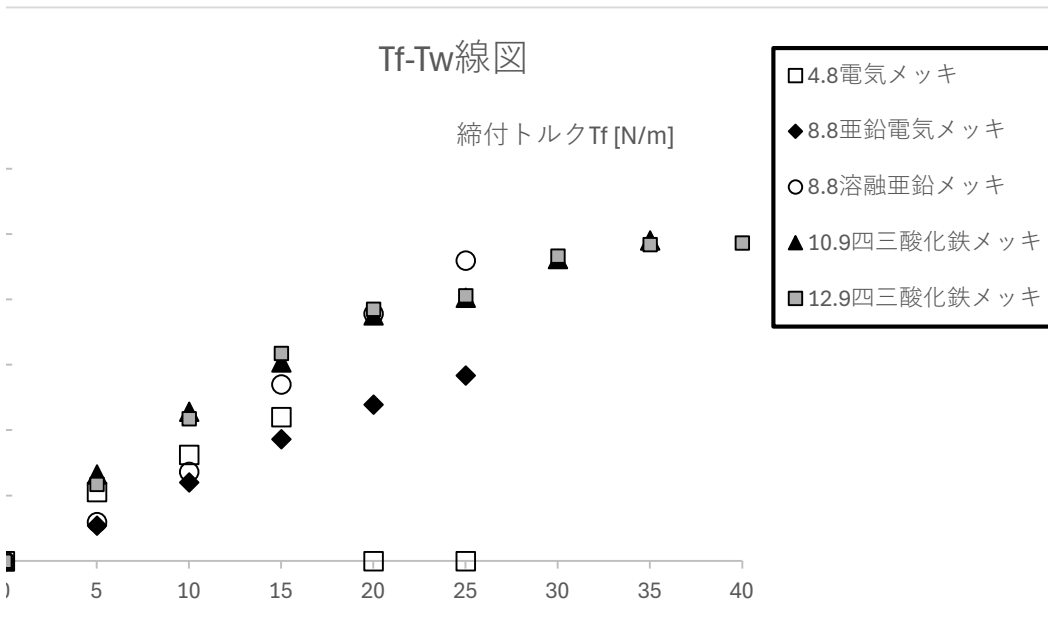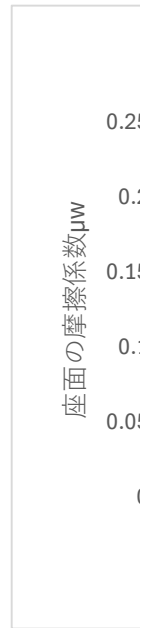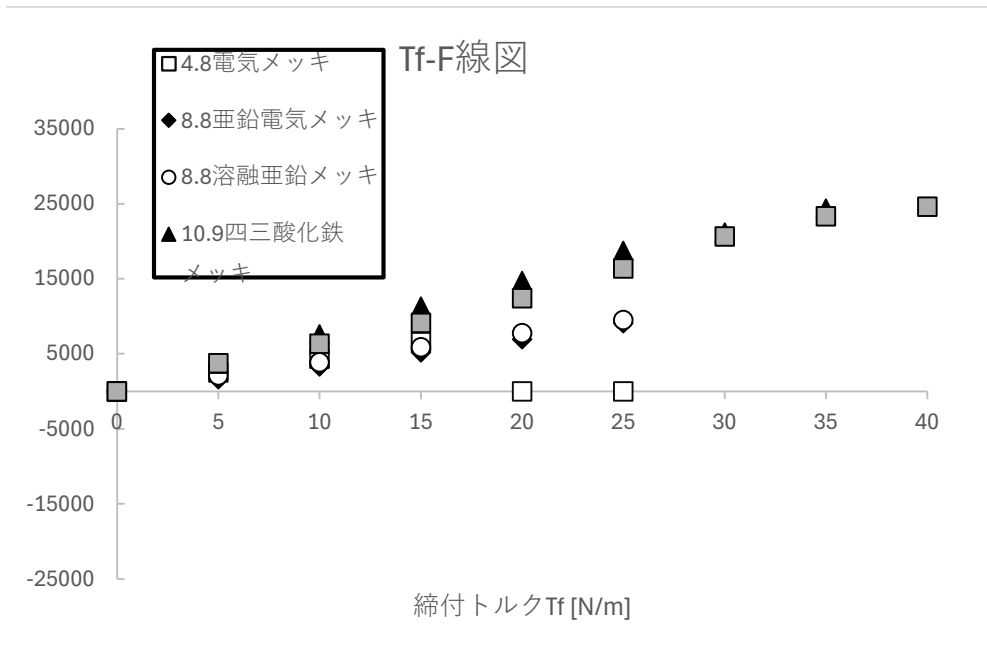

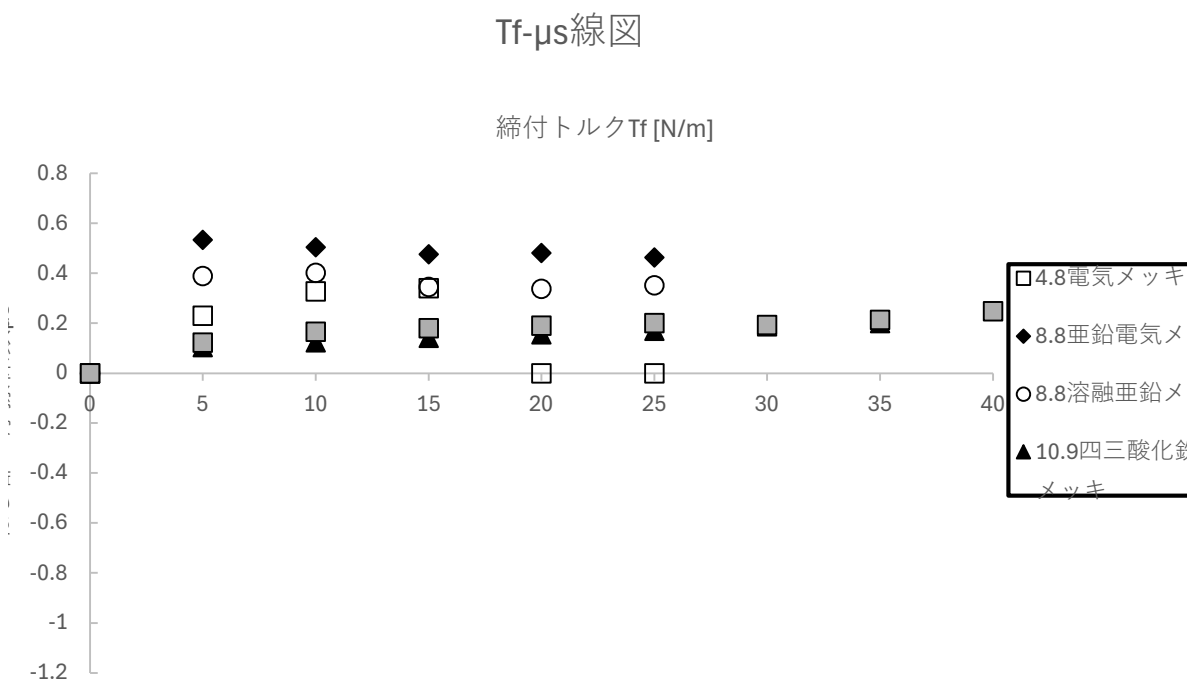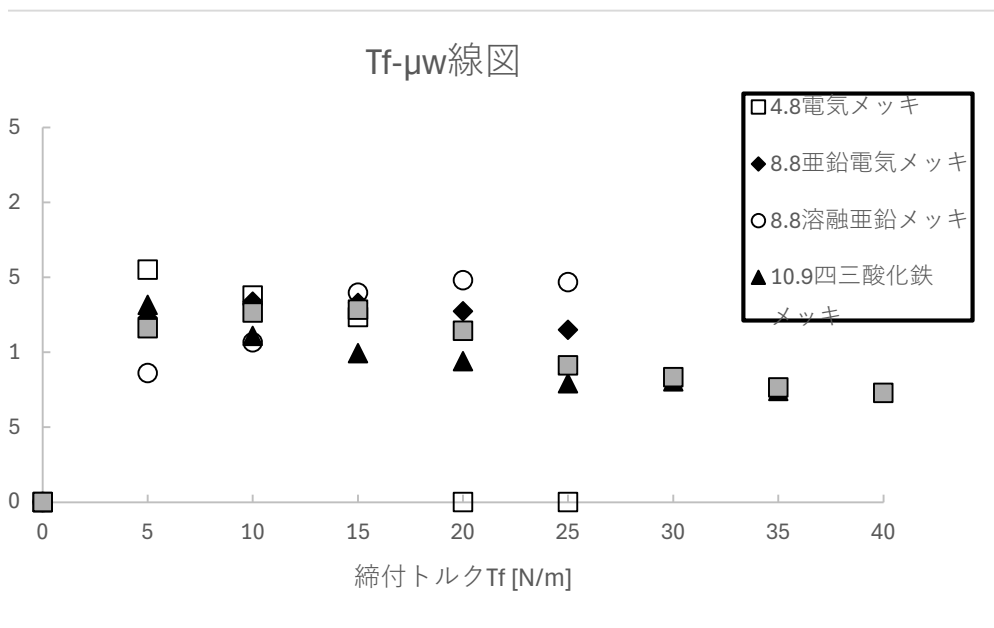

ツキ

ツキ

失